

PD IEC/PAS 63015:2016



BSI Standards Publication

Definition of “Low-Halogen” for electronic products

National foreword

This Published Document is the UK implementation of IEC/PAS 63015:2016.

The UK participation in its preparation was entrusted to Technical Committee GEL/111, Electrotechnical environment committee.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.

Published by BSI Standards Limited 2016

ISBN 978 0 580 91373 0

ICS 01.040.71; 13.030.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This Published Document was published under the authority of the Standards Policy and Strategy Committee on 31 August 2016.

Amendments/corrigenda issued since publication

Date	Text affected
-------------	----------------------



PUBLICLY AVAILABLE SPECIFICATION

PRE-STANDARD

Definition of “Low-Halogen” for electronic products

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 01.040.71; 13.030.10

ISBN 978-2-8322-3471-6

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references.....	6
3 Terms, definitions and abbreviated terms	7
4 Requirements for low-halogen electronic products.....	8
5 Compliance process for low-halogen electronic materials and components	9
6 Marking and labeling for “low-halogen” electronic products	9
6.1 Marking of printed boards.....	9
6.2 Marking of mechanical plastics	9
6.3 Marking of passive and solid-state devices, cables, and other components of an electronic product.....	9
6.4 Marking of electronic products	10
Annex A (informative) Where BFRs, CFRs, and PVC are used in electronic or electrical products	11
Annex B (informative) Suggested test protocols – Low-halogen process flow	12
B.1 Low halogen process flow	12
B.2 Low halogen process flow verbiage	13
Annex C (informative) Clarification for including only bromine and chlorine in the definition of low-halogen materials	14
Annex D (informative) Differences between JS709B and JS709A.....	15
Bibliography	16
 Table A.1 – General presence of bromine and chlorine in BFRs, CFRs, and PVC in electronics and electrical products	 11

INTERNATIONAL ELECTROTECHNICAL COMMISSION

DEFINITION OF “LOW-HALOGEN” FOR ELECTRONIC PRODUCTS

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

A PAS is a technical specification not fulfilling the requirements for a standard, but made available to the public.

IEC PAS 63015, submitted by JEDEC/ECA has been processed by IEC technical committee 111: Environmental standardization for electrical and electronic products and systems. It is based on Joint JEDEC/ECA Standard No. 709B. The structure and editorial rules used in this PAS reflect the practice of the organization which submitted it.

The text of this PAS is based on the following document:

This PAS was approved for publication by the P-members of the committee concerned as indicated in the following document

Draft PAS	Report on voting
111/382/PAS	111/417/RVD

Following publication of this PAS, the technical committee or subcommittee concerned may transform it into an International Standard.

This PAS shall remain valid for an initial maximum period of 3 years starting from the publication date. The validity may be extended for a single period up to a maximum of

3 years, at the end of which it shall be published as another type of normative document, or shall be withdrawn.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

Halogenated polymeric materials and compounds are used in various engineering applications, including flame retardation. Several decades of use have proven these materials and compounds to be reliable and cost-effective. The electronic industry seeks to reduce the overall environmental impact of our products by working to develop reliable and cost-effective alternatives to these materials and compounds. However, the timetable for broad-scale adoption of low-halogen materials is difficult to predict, because applications such as complex multilayer PCBs and large molded integrated circuits will require further investigation and qualification of new materials.

The halogen group contains fluorine, chlorine, bromine, iodine, and astatine; however, this document will use the term “low-halogen” to refer only to bromine and chlorine to be consistent with the International Electrotechnical Commission (IEC) and IPC definitions of “halogen-free” (see Clause 2). Refer to Annex C for further explanation for exclusion of astatine, iodine and fluorine. In this document, the term “low-halogen” is used to identify a material that contains low concentrations of bromine and chlorine from brominated and chlorinated flame retardants (BFRs, CFRs) and polyvinyl chloride (PVC).

DEFINITION OF “LOW-HALOGEN” FOR ELECTRONIC PRODUCTS

1 Scope

This document provides terms and definitions for “low-halogen” electronic products that have the potential to contain the halogens bromine (Br) and chlorine (Cl) from the use of BFRs, CFRs, and PVC, and recommends methods for marking and labeling. This standard may be applied to all nonmetallic and nonceramic materials within electronic products including, but not limited to, materials in the following components commonly found in electronic products:

- 1) transistors, integrated circuits, modules consisting mainly of integrated circuits (e.g. multichip, hybrid), and memory modules;
- 2) resistors, capacitors, relays, inductors, and connectors;
- 3) printed circuit board assemblies (PCBAs) including components;
- 4) plastic in cables, sockets, switches and external wiring;
- 5) mechanical plastics (enclosures, fans, etc.);
- 6) films, tapes, inks, and adhesives;
- 7) soldering flux residues (when present);
- 8) sound, shock, and vibration dampeners (foams, resins, etc.).

This document establishes the maximum concentration level for the halogens bromine (Br) and chlorine (Cl) from the use of BFRs, CFRs, and PVC. While the halogen group contains fluorine, chlorine, bromine, iodine, and astatine, this document will use the term “low-halogen” to refer only to bromine and chlorine. Refer to Annex C for further explanation for exclusion of astatine, iodine and fluorine.

NOTE The definition of “low-halogen” is different from the term “halogen-free” as described in IEC 61249-2 sectional standard related to non-halogenated base material and as defined in the J-STD-609A marking and labeling standard; standards that pertain only to printed boards and are currently in use in the electronics and solid-state industries.

BFRs, CFRs, and PVC in materials that may be used during processing, in product delivery systems, or in packaging, but do not remain within the final product are not included in the scope of this document.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62321: 2008, *Electrotechnical products – Determination of levels of six regulated substances (lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls, polybrominated diphenyl ethers)*

EN 14582:2007-06, *Characterization of waste – Halogen and sulphur content – Oxygen combustion in closed systems and determination methods*

IEC 61249-2 (all parts), *Materials for printed boards and other interconnecting structures*

IPC-T-50, *Terms and Definitions for Interconnecting and Packaging Electronic Circuits*

IPC-4101, *Specification for Base Materials for Rigid and Multilayer Printed Boards*

IPC/JEDEC J-STD-609, *Marking and Labeling of Components, PCBs and PCBA's to Identify Lead (Pb), Pb-free and Other Attributes*

ISO 11469:2000, *Plastics – Generic identification and marking of plastics products*

ISO 1043-4:1998, *Plastics – Symbols and abbreviated terms – Part 4: Flame retardants*

JESD88, *JEDEC Dictionary of Terms for Solid-state Technology*

JPCA–ES–01, *Test Method for Halogen Free Materials*

3 Terms, definitions and abbreviated terms

For the purposes of this document, the terms, definitions and abbreviated terms given in JESD88 and/or IPC-T-50 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

At	astatine
BFR	brominated flame retardant
Br	bromine
Cl	chlorine
CFR	chlorinated flame retardant
F	fluorine
FR	flame retardant
I	iodine
IC	ion chromatography
IEC	International Electrotechnical Commission
ISO	International Organization for Standardization
PBDE	polybrominated diphenyl ether
PCB	printed circuit board
PCBA	printed circuit board assembly
PPM	parts per million
PTFE	polytetrafluoroethylene
PVC	polyvinyl chloride
TBBPA	tetrabromobisphenol-A
XRF	X-ray fluorescence

3.1

block polymer

substance composed of block macromolecules

[SOURCE: IUPAC]

3.2 brominated/chlorinated flame retardants BFR/CFR

flame retardants that contain bromine and/or chlorine

Note 1 to entry: These compounds are typically added to or reacted into polymers such as certain epoxy resins and thermoplastics to reduce their flammability. Examples include, but are not limited to, tetrabromobisphenol-A (TBBPA), brominated epoxy resins, and polybrominated diphenyl ethers (PBDEs).

3.3 congener

member of the same kind, class or group of compounds with similar structures and similar chemical properties

3.4 copolymer

polymer derived from more than one species of monomer

[SOURCE: IUPAC]

3.5 electronic device

device whose operation depends on the conduction of electrons and/or holes in vacuum, gas, or semiconductor

Note 1 to entry: Examples of electronic devices include transistors, integrated circuits, hybrid integrated circuits, and modules containing active electronic components.

3.6 electronic product

item containing one or more electronic devices performing major functions

3.7 low-halogen

meeting the criteria established in Clause 4 of this document

Note 1 to entry: Low halogen electronic products may still contain some halogens, providing, of course, that each material in them meets the requirements in Clause 4.

3.8 plastic

any of a group of synthetic or natural organic compounds produced by polymerization, optionally combined with additives (organic or inorganic fillers, modifiers, etc.) into a homogeneous material capable of being molded, extruded, or cast into various shapes and films

3.9 polymer alloy

polymer blend (considered to be an alloy) that contains either a crystallizable component or two relatively rigid or amorphous polymers

4 Requirements for low-halogen electronic products

The halogens fluorine (F), iodine (I), and astatine (At) are not covered by this document (see annex C). Bromine (Br) and chlorine (Cl) refer to all oxidation states of these elements. Bromine (Br) and chlorine (Cl) in materials that may be used during processing but do not remain within the final product are not included in this definition.

For an electronic product to be defined as “low-halogen”, each material within the product shall meet all of the following requirements.

- 1) Each material within an electronic product, (excluding printed board laminates) shall contain < 1 000 ppm (0,1 %) by weight of bromine if the bromine source is from BFRs and < 1 000 ppm (0,1 %) by weight of chlorine if the chlorine source is from CFRs, PVC, PVC congeners, PVC block polymers, PVC copolymers, or polymer alloys containing PVC. Higher concentrations of bromine and chlorine are allowed in plastics contained within electronic products (other than printed board laminates contained within those devices) as long as their sources are not flame retardants, PVC, PVC congeners, PVC block polymers, PVC copolymers, or polymer alloys containing PVC.
- 2) All printed board laminates contained within electronic and electrical products, including those within a passive or solid-state device shall meet the “halogen-free” requirements for Br and Cl as defined in the most current version of one of the following specifications: IEC 61249-2, IPC-4101, JPCA-ES-01.

NOTE See Annex A for a list of likely uses of flame retardants, PVC, PVC congeners, PVC block polymers, PVC copolymers, or polymer alloys containing PVC within electronic products.

5 Compliance process for low-halogen electronic materials and components

An electronic product often contains many materials/components from a complex and global supply chain. Therefore, all individual entities or suppliers within the chain have to be required to take responsibility for ensuring that the materials/components that they supply meet the requirements of this document. Each supplier/individual entity within the supply chain is only responsible to prove compliance to their respective customer for the material/component that they supply. Any material/component that is declared to be “low-halogen” as per Clause 4 herein shall be supported by proof that substantiates the claim.

Since there is not a single, simple, cost-effective, and reliable test method that covers the spectrum of materials/components included in electronic products, customers and suppliers should mutually agree on the best method to demonstrate compliance to this document. If analytical testing is used, elemental Br and Cl analysis is the most expedient and cost effective to perform (IEC 62321 provides screening and analytical test methods for some but not all of the substances within the scope of this document). If results detect Br or Cl above 1 000 ppm threshold, the supplier should determine if the source of the Br or Cl is from flame retardants, PVC, PVC congeners, PVC block polymers, PVC copolymers, or polymer alloys containing PVC. The proof of compliance documents may include material declarations, datasheets and/or analytical data.

6 Marking and labeling for “low-halogen” electronic products

6.1 Marking of printed boards

If all materials used in the fabrication of a finished printed board laminate contained within a passive or solid-state device meet the requirements in Clause 4, item 1), and if marking is required, the marking shall be in accordance with J-STD-609.

6.2 Marking of mechanical plastics

Mechanical plastic parts contained within a passive or solid-state device may be marked/labeled in accordance with ISO 11469:2000. Compositions containing flame retardants may be marked as per ISO 1043-4:1998.

6.3 Marking of passive and solid-state devices, cables, and other components of an electronic product

Marking is not required on passive or solid-state devices to denote low-halogen status. As an alternative, a part numbering scheme may be used to denote “low-halogen” solid-state devices.

6.4 Marking of electronic products

Marking is not required to denote the low-halogen status.

Annex A (informative)

Where BFRs, CFRs, and PVC are used in electronic or electrical products

Brominated flame retardants (BFRs) and, less frequently, chlorinated flame retardants (CFRs) are added to thermoplastics, insulation materials, component mold compounds, solder masks, printed board laminates, and other plastic materials to achieve a desired flame retardancy (e.g., UL 94 V-0). In addition, polyvinyl chloride (PVC) is commonly used as the base resin for certain cable jacketing and vibration dampening materials. Table A.1 is provided for informative purposes only.


Table A.1 – General presence of bromine and chlorine in BFRs, CFRs, and PVC in electronics and electrical products

Part type	Examples
Mechanical plastic parts (thermoplastics and elastomers)	BFRs/CFRs used in certain acrylonitrile butadiene styrene (ABS), acrylonitrile butadiene acrylester (ASA), high-impact polystyrene (HIPS), polycarbonate (PC), polystyrene (PS), polyimide (PI), polyamide (PA), polybutylene terephthalate (PBT), polypropylene (PP), polyethylene (PE), styrene ethylene butadiene styrene (SEBS) resins, and chloroprene rubber
Cables	BFRs used in cable/wire insulation material PVC used in cable/wire jacketing and overmold
Printed boards, rigid and flexible	BFRs added or reacted into FR-4, other epoxy resins, polyamide, and adhesives
Electronic components *	BFRs added or reacted into FR-4 and other epoxy resins, mold compounds, plastic packages, thermal interface materials, die attach, and underfills
Connectors	BFRs used in certain flame-rated PBT and PA resins
Films, adhesives, tapes	PVC used in certain magnetic tapes
Conduits	BFR's used in polypropylene (PP)
Sound, shock, and vibration dampeners (foams, resins, etc.,)	PVC used in shock absorbing or vibration dampening resins
* Plastic in construction of various components (actives, discrettes, hybrids, ICs, and passives, etc.).	

Annex B (informative)

Suggested test protocols – Low-halogen process flow

B.1 Low halogen process flow

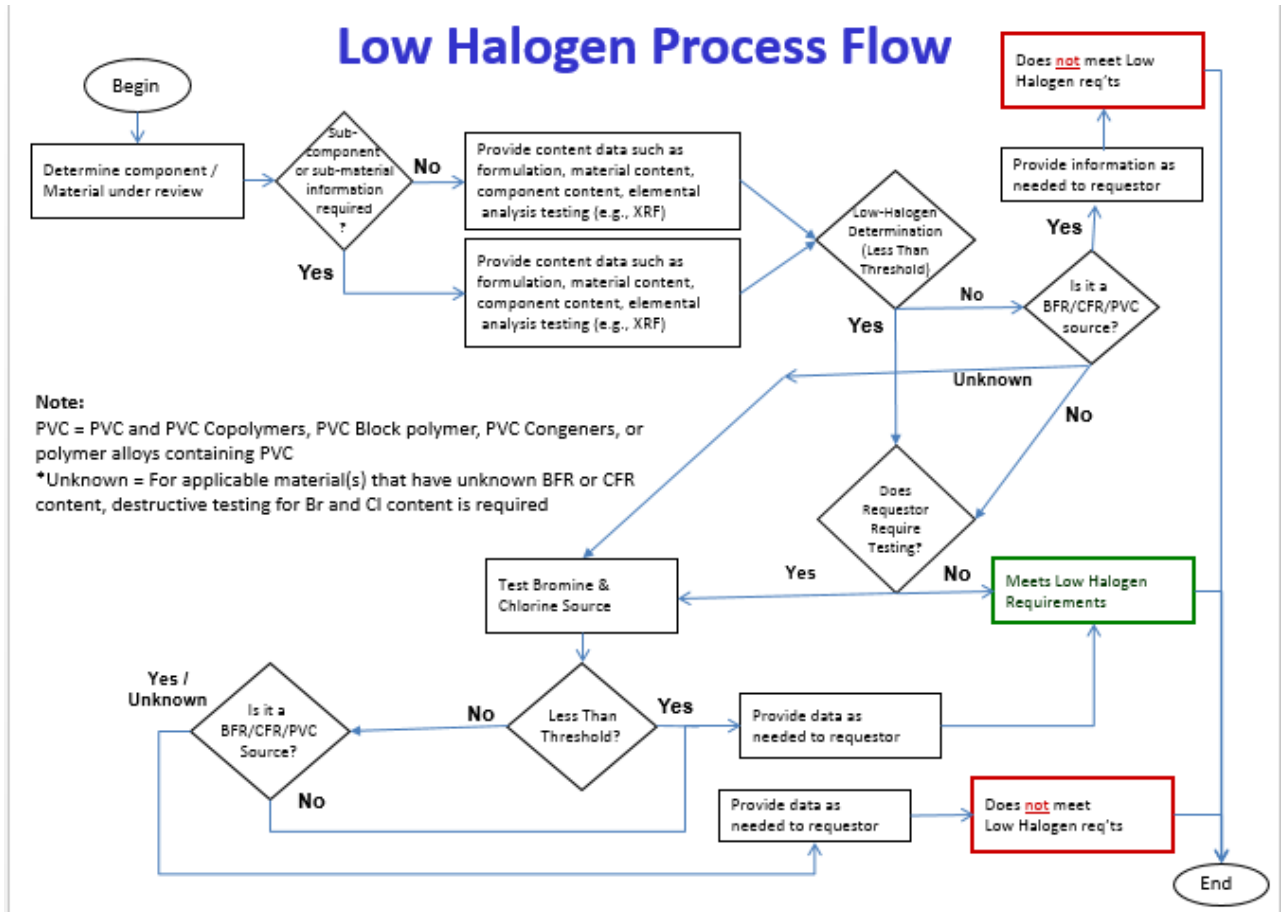

B.2 Low halogen process flow verbiage

Summary of Low Halogen Compliance Determination

Determine the material or component under review for low-halogen requirements

Is sub-material/sub-component information required?

No: Supplier provides content data such as formulation, material content, component content, XRF results

Go to “low-halogen” determination (Less Than Threshold)

Yes: Supplier provides content data such as formulation, material content, component content, XRF results for the sub-material / sub-component.

Go to “low-halogen” determination (Less Than Threshold)

“low-halogen” determination: **Does the information provided meet “low-halogen” requirements?**

No: **Is Br or Cl from a BFR/CFR/PVC* source?**

Yes: Fails “low-halogen” requirements

Provide information if needed

End “low-halogen” determination process

No: Go to “Does requestor require testing?” (To prove compliance, destructive testing is required)

Unknown: Go to “Test Bromine & Chlorine Source” (To prove compliance, destructive testing is required)

Yes – **Does Requestor require testing?**

If No: Passes “low-halogen” requirements

End “low-halogen” determination process

If Yes: perform testing to determine elemental Cl/Br levels.

Does it meet “low-halogen” thresholds?

Yes: Passes “low-halogen” requirements

Provide information as needed

End “low-halogen” determination process

No: **Is it from a BFR/CFR/PVC** source?**

No: Passes “low-halogen” requirements

Provide information as needed

End “low-halogen” determination process

Yes / *Unknown: Fails “low-halogen” requirements

Provide information as needed

End “low-halogen” determination process

End “low-halogen” determination process

***Unknown** - For applicable materials that have an unknown status for Cl or Br being from a BFR/CFR/PVC** source, it fails “low-halogen” requirements

****PVC** - PVC or PVC copolymers

Annex C (informative)

Clarification for including only bromine and chlorine in the definition of low-halogen materials

Halogens are not as a group generally hazardous to the environment, so to include all halogens would create demands for verifications that are not needed.

Astatine is radioactive with a half-life of less than nine hours and the estimated total amount in the world is approximately 30 grams, so is of no interest for electronic or electrical products.

Iodine containing FRs have very good flame retardant properties. The trend is that for the halogens the FR properties increase as you go down the Group VII elements. However, for electronic and electrical type of applications, the iodine containing FR decomposes at a temperature that is too low to be very effective. This is primarily a result of the weak carbon-to-iodine bond.

The brominated and chlorinated flame retardants are normally organic substances that are both persistent and bio-accumulative. Therefore, it is necessary to focus on this usage of halogens in electronic and electrical products.

As PVC cannot always be collected to be combusted under controlled circumstances, there is a market demand to be able to choose whether or not the product may contain PVC therefore this specific application of chlorine is included.

PTFE (i.e. Teflon®) is commonly used in electronics, but as this material is not bio-accumulative, there is within the current knowledge, no need to include fluorine in the definition of “low-halogen”.

Annex D (informative)

Differences between JS709B and JS709A

Annex D briefly describes most of the changes made in JS709B, compared to its predecessor, JS709A (May 2012). Some minor editorial changes like punctuation changes are not included.

The major differences are the addition of clarifying definitions and acronyms, the citing of more pertinent industry standards and adding clarity to the scope and annexes.

Bibliography

IEC 61189-2, *Test methods for electrical materials, printed boards and other interconnection structures and assemblies – Part 2: Test methods for materials for interconnection structures*

IEC 61249-2-21, *Materials for printed boards and other interconnecting structures – Part 2-21: Reinforced base materials, clad and unclad – Non-halogenated epoxide woven E-glass reinforced laminated sheets of defined flammability (vertical burning test), copper-clad*

IEC 61249-2-22, *Materials for printed boards and other interconnecting structures – Part 2-22, Reinforced base materials clad and unclad – Modified non-halogenated epoxide woven E-glass laminated sheets of defined flammability (vertical burning test), copper-clad*

IEC 61249-2-23, *Materials for printed boards and other interconnecting structures – Part 2-23, Reinforced base materials, clad and unclad – Non-halogenated phenolic cellulose paper reinforced laminated sheets, economic grade, copper clad*

IEC 61249-2-26, *Materials for printed boards and other interconnecting structures – Part 2-26, Reinforced base materials clad and unclad – Non-halogenated epoxide non-woven/woven E-glass reinforced laminated sheets of defined flammability (vertical burning test), copper-clad*

IPC-TM-650 TM 2.3.41, *Test Method for Total Halogen Content in Base Materials*

IPC/WP/TR-584A IPC, *White Paper and Technical Report on the Use of Halogenated Flame Retardants in Printed Circuit Boards and Assemblies*

MC-001, *Guideline of Halogen Free Epoxy Molding Compound for Semiconductor*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK