



BSI Standards Publication

# Nanomanufacturing — Key control characteristics

Part 4-4: Nano-enabled electrical energy storage — Thermal characterization of nanomaterials, nail penetration method

### **National foreword**

This Published Document is the UK implementation of IEC/TS 62607-4-4:2016.

The UK participation in its preparation was entrusted to Technical Committee NTI/1, Nanotechnologies.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.

Published by BSI Standards Limited 2016

ISBN 978 0 580 91370 9

ICS 07.120

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This Published Document was published under the authority of the Standards Policy and Strategy Committee on 30 November 2016.

### **Amendments/corrigenda issued since publication**

<b>Date</b>	<b>Text affected</b>
-------------	----------------------

---



# TECHNICAL SPECIFICATION



---

**Nanomanufacturing – Key control characteristics –  
Part 4-4: Nano-enabled electrical energy storage – Thermal characterization of  
nanomaterials, nail penetration method**

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

---

ICS 07.120

ISBN 978-2-8322-3712-0

**Warning! Make sure that you obtained this publication from an authorized distributor.**

## CONTENTS

FOREWORD .....	3
INTRODUCTION .....	5
1 Scope .....	6
2 Normative references .....	6
3 Terms and definitions .....	6
4 Sample preparation .....	8
4.1 General sample requirements .....	8
4.2 Pre-treatment.....	8
4.3 Puncture nail construction.....	9
4.4 Puncture nail temperature and isolation verification .....	9
5 Measurement of electric properties .....	10
5.1 Equipment and testing site requirements.....	10
5.2 Measurement system requirements.....	10
5.3 Sample setup.....	11
5.4 Puncture method.....	11
5.5 Design of testing method .....	12
6 Data analysis / interpretation of result.....	13
6.1 Samples classification from the results .....	13
6.1.1 Reference sample (without nanomaterials) .....	13
6.1.2 Test sample (with nanomaterials) .....	13
6.2 Data analysis .....	13
Annex A (informative) Data report example.....	15
Bibliography.....	17
Figure 1 – Schematic view of puncture nail .....	9
Figure 2 – Schemetic view of puncture nail and the heated metal block .....	10
Figure 3 – The puncture through depth of cell.....	11
Figure 4 – Flow chart of reference sample test procedures .....	12
Figure 5 – Voltage and temperatures versus time plot.....	13
Figure 6 – Repeatability plot of voltage and temperature versus time.....	14
Figure 7 – Performance comparison plot of voltage and temperature versus time .....	14
Table 1 – Hazard level description .....	12
Table A.1 – Anode specifications .....	15
Table A.2 – Cathode specifications .....	15
Table A.3 – Electrolyte specifications.....	15
Table A.4 – Separator specifications.....	15
Table A.5 – Cell specification.....	15
Table A.6 – Sample analysis.....	16

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**NANOMANUFACTURING –  
KEY CONTROL CHARACTERISTICS –****Part 4-4: Nano-enabled electrical energy storage – Thermal  
characterization of nanomaterials, nail penetration method**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

The main task of IEC technical committees is to prepare International Standards. In exceptional circumstances, a technical committee may propose the publication of a Technical Specification when

- the required support cannot be obtained for the publication of an International Standard, despite repeated efforts, or
- the subject is still under technical development or where, for any other reason, there is the future but no immediate possibility of an agreement on an International Standard.

Technical Specifications are subject to review within three years of publication to decide whether they can be transformed into International Standards.

IEC TS 62607-4-4, which is a Technical Specification, has been prepared by IEC technical committee 113: Nanotechnology for electrotechnical products and systems.

The text of this Technical Specification is based on the following documents:

Enquiry draft	Report on voting
113/306/DTS	113/329/RVC

Full information on the voting for the approval of this Technical Specification can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 62607 series, published under the general title *Nanomanufacturing – Key control characteristics*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- transformed into an International Standard,
- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

**IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.**

## INTRODUCTION

Energy storage devices are becoming increasingly important for many applications such as consumer devices, electric vehicles and aircrafts. Energy storage devices with high performance and reliability are the key factors to earn the confidence of customers. Also, in smart grid and renewable energy applications, where energy efficiency and reliable power supplies are critical, an energy storage system is an essential device. There are many types of energy storage devices for various applications. Lithium-ion batteries are the most popular and promising energy storage devices for portable electronics, consumer electronics, military, electric vehicle and aerospace applications. It is a good test carrier for performance and reliability characteristics.

One of the characteristics that draws the attention of users is the thermal runaway behaviour when a short circuit occurs inside the energy storage devices due to a manufacturing process defect, improper operation or external shocks. The poor control of manufacturing process may cause the energy storage device's internal defects, such as particle impurity, defects of separator, burr of electrodes or a prominence of conductive arms. Energy storage devices operated under abnormal conditions, such as quick charging or piercing by external objects, may cause an internal short circuit. Large current generated short circuit will generate an abnormal exothermic reaction and a local temperature rise, but the temperature of the short circuit spot drops due to heat transfer. These effects cause the energy storage device's temperature to continue to rise rapidly. If it reaches thermal runaway temperature, it usually leads to fire and explosion of the energy storage devices. The event can result in damage to personnel and equipment. In the worst case scenario, this may hamper the development of such type of energy storage devices.

In order to prevent such a scenario, nanomaterial additives have been used to prevent thermal runaway to ensure the reliability and safety of energy storage devices. The nanomaterial additives may mix with active materials of electrodes, electrolyte, coated on the surface of electrodes or separator.

This document specifies general testing procedures and requirements for the assessment of thermal runaway performance and risk associated with the nano-enabled energy storage devices prepared by employing nanomaterial additives, and serves as the basis for further developing particular product specific standards. This method covers only large temperature rises in cell temperature caused by shorting of the anode and cathode. This method does not generally cover thermal runaway due to other causes such as high external temperature and is not a general method to prevent thermal runaway.

## **NANOMANUFACTURING – KEY CONTROL CHARACTERISTICS –**

### **Part 4-4: Nano-enabled electrical energy storage – Thermal characterization of nanomaterials, nail penetration method**

#### **1 Scope**

This part of IEC 62607, which is a Technical Specification, provides a measurement method for thermal runaway quality level test for nano-enabled energy storage devices. This method uses comparative measurement to enable a manufacturer to decide whether or not the nanomaterial additives used in energy storage devices are resilient against the thermal runaway caused by a faulty or accidental low resistance connection between two or several internal points depending on the number of stacking electrode layers of the test sample. The nanomaterial additives may mix with the materials of positive and negative electrodes, electrolyte, coated on electrodes or separator. This document includes definitions of terminology, test sample, puncture nail requirements, test procedures, data analysis and methods of interpretation of results and a case study.

This document does not apply directly to the safety testing for energy storage device products due to complex safety design schemes embedded in these products.

#### **2 Normative references**

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 9001:2015, *Quality management systems – Requirements*

ISO 14001:2015, *Environmental management systems – Requirements with guidance for use*

ISO 26000:2010, *Guidance on social responsibility*

ISO/TS 80004-1:2015, *Nanotechnologies – Vocabulary – Part 1: Core terms*

ISO/TS 80004-2:2015, *Nanotechnologies – Vocabulary – Part 2: Nano-objects*

ISO/TS 80004-4:2011, *Nanotechnologies – Vocabulary – Part 4: Nanostructured materials*

IEC TS 80004-9:2016, *Nanotechnologies – Vocabulary – Part 9: Nano-enabled electro-technical products and systems*

#### **3 Terms and definitions**

For the purposes of this document, the terms and definitions given in ISO 9001, ISO 14001, ISO 26000, the core terms of ISO/TS 80004-1, ISO/TS 80004-2, ISO/TS 80004-4, IEC TS 80004-9 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:



- IEC Electropedia: available at [http://http://www.electropedia.org/](http://www.electropedia.org/)
- ISO Online browsing platform: available at <http://www.iso.org/obp>

### 3.1

#### **nanoscale**

length range approximately from 1 nm to 100 nm

[SOURCE: ISO/TS 80004-1:2015, 2.1]

### 3.2

#### **nanomaterial**

material with any external dimension in the nanoscale or having internal structure or surface structure in the nanoscale

[SOURCE: ISO/TS 80004-1:2015, 2.4]

### 3.3

#### **nano-object**

discrete piece of material with one, two or three external dimensions in the nanoscale

[SOURCE: ISO/TS 80004-1:2015, 2.5]

### 3.4

#### **nanomaterial additive**

nanomaterial, added in small quantities to a part of a device, to improve or otherwise modify one or more properties

### 3.5

#### **nano composite material**

multiphase material where one of the phases has one, two or three dimensions of less than nanoscale

### 3.6

#### **nano-enabled**

exhibiting function or performance only possible with nanotechnology

[SOURCE: ISO/TS 80004-1:2015, 2.15]

### 3.7

#### **nano-enhanced**

exhibiting function or performance intensified or improved by nanotechnology

[SOURCE: ISO/TS 80004-1:2015, 2.16]

### 3.8

#### **open circuit voltage**

difference in electrical potential voltage between the terminals of a cell or battery measured when the circuit is open (no-load condition) and no external current is flowing

[SOURCE: ISO 17546:2016, 3.26]

### 3.9

#### **short circuit**

circuit with the impedance of less than 1 m $\Omega$  applied between the output terminal and ground

[SOURCE: ISO 27027:2014, 3.13]

**3.10****cell**

single energy or charge-storing unit within a pack of cells that form the energy storage device

**3.11****capacity**

electric charge which a cell or battery can deliver under specified discharge conditions

Note 1 to entry: The SI unit for electric charge, or quantity of electricity, is the coulomb (1 C = 1 A·s) but in practice, capacity is usually expressed in ampere hours (Ah).

[SOURCE: IEC 60050-482:2004, 482-03-14]

**3.12****separator**

non-conductive semi-permeable film or grid to separate two electrodes to prevent them from contacting each other and short-circuiting but which allows the passage of ions through it

**3.13****SOC****state of charge**

status of available energy in the energy storage device

Note 1 to entry: SOC is usually expressed as a percentage.

**4 Sample preparation****4.1 General sample requirements**

Testing samples shall be fully activated energy storage device cells. The shape (usually prismatic or cylindrical), the inner structures (usually stacked or rolled), anode/cathode materials, electrolyte and separator are based on manufacturers' design and requirements. In order to establish distinguishable nano-enabled or nano-enhanced function, two sets of samples should be prepared. Set one is without nanomaterial additives (reference sample), the other set is with nanomaterial additives (test sample). The minimum number of cells are 20 and 10, respectively, for appropriate statistical significance. The nanomaterial additives could be blended into anode/cathode materials, electrolyte and surface of the separator. Apart from nanomaterial additives, the two test samples should be the same (for example, size, assembly method and structure, capacity, materials, etc). The specifications of the test sample should be illustrated.

**4.2 Pre-treatment**

Pre-treatment should be performed for reference sample and test sample to select the qualified samples for thermal runaway test. The pre-treatment processes are as follows.


- 1) Prepare 20 reference samples.
- 2) Prepare 10 test samples.
- 3) Perform three charge/discharge cycles according to 1,0 °C or self-defined conditions, the temperature should be controlled at  $(25 \pm 5)$  °C.
- 4) The sample should be fully charged (100 % SOC) and kept at  $(25 \pm 5)$  °C for one hour. The mean, standard deviation and variation coefficient of the electric capacity can be calculated from 1,0 °C discharge curve. If the variation coefficient is larger than 3 %, the sample batch is not qualified for thermal runaway test. Another batch of samples should be selected for pre-treatment.
- 5) If electric capacity of the sample is outside the range of mean  $\pm 1,5$  sigma, it is not qualified for thermal runaway test.

- 6) The total number of reference samples for thermal runaway test should be larger than 10; the total number of test samples for thermal runaway test should be larger than three.
- 7) Different manufacture (designed) nanomaterial additive samples should be pre-treated separately according to steps 2) to 5).

#### 4.3 Puncture nail construction

Several important factors, such as nail diameter, material, cone angle, etc., will affect the test results. It is crucial to standardize the nail structures in order to have reliable quantitative data for comparison. The design is to embed a thermocouple inside a puncture nail in order to reliably record the temperature around the nail apex. Nail structures are described as follows.

- 1) The outer diameter of the nail is 2,5 mm, the tapered length is 2 mm, the cone angle is  $64^\circ$ , the inner diameter of the nail is 1 mm and the depth is equal to the cylindrical length (excluding taper).
- 2) The length of the nail (including taper) must be 10 mm longer than the energy storage device's height.
- 3) Thermocouple is embedded inside the nail inner cylinder (high temperature thermocouple is recommended). The inner wall of the nail is coated with thermal insulated magnesium oxide (MgO) to prevent measurement interference.
- 4) The puncture nail material is made of AISI 300 series stainless steel. The other parts connecting to the puncture nail should be mechanically strong, corrosion/fire resistant and easy to maintain.
- 5) The schematic view of the puncture nail is illustrated in Figure 1.

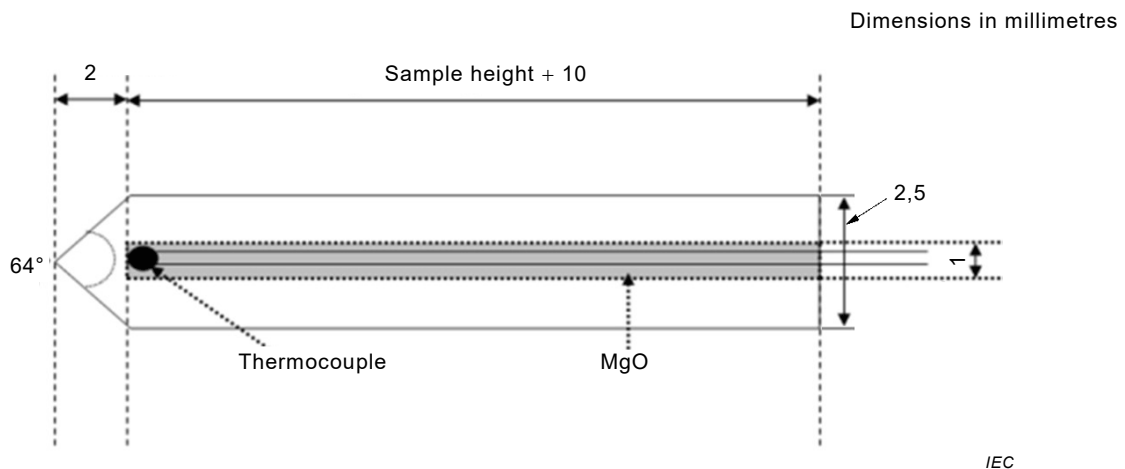


**Figure 1 – Schematic view of puncture nail**

#### 4.4 Puncture nail temperature and isolation verification

In order to ensure the temperature reading at the puncture point and minimize the reading interference from non ideal MgO thermal isolation, the puncture nail temperature and isolation verification procedure need to be performed. The procedures are as follows.

- 1) Select a good thermal conducting metal block (thickness about 20 mm) with a hole at the top, the diameter of the hole is 2,5 mm with depth equal to 10 mm.
- 2) The metal block is heated to  $160^\circ\text{C}$ . Thermal equilibrium of the metal block is checked with two thermocouples, one is at the top and the other is at the side as shown in Figure 2. Insert the nail in to the hole of the metal block when thermal equilibrium of the metal block is reached. Wait until the reading of the thermocouple of the nail is stable.
- 3) The construction of the puncture nail is acceptable if the temperature reading of the nail is  $\pm 3^\circ\text{C}$  at  $160^\circ\text{C}$ .

- 4) The electric insulation is tested with a multimeter after the puncture nail has cooled to room temperature.
- 5) The schematic view of the puncture nail and the heated metal block is illustrated in Figure 2.

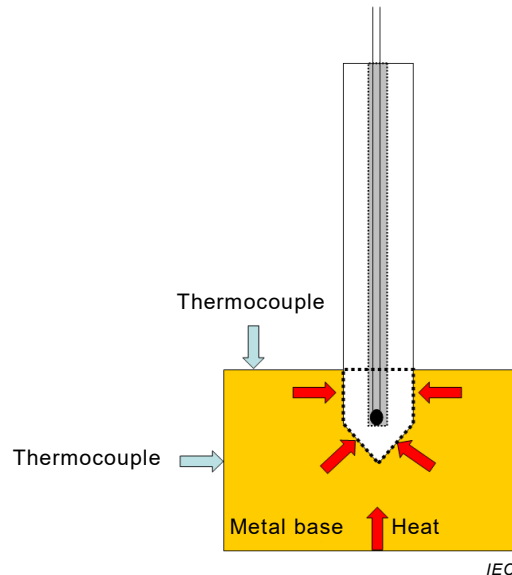

**Figure 2 – Schematic view of puncture nail and the heated metal block**

## 5 Measurement of electric properties

### 5.1 Equipment and testing site requirements

The safety requirements for different samples are quite different. The measurement equipment should be able to be applied to various samples, yet it can achieve consistent accuracy. Generally, the equipment can provide adequate puncture force for different hardness samples. The measurement should also provide safe observation setup for dangerous results (such as smoke, fire and explosion, etc.). The equipment requirements and recommendations are as follows.

- 1) The maximum controlled displacement velocity of the servo motor should be equal to or larger than 50 mm/s, the minimum should be equal to or less than 0,1 mm/s, the error should be less than 5 %.
- 2) The puncture force shall be at least 5 000 N (It can puncture a soda metal can.).
- 3) The testing site shall be well sealed and the temperature shall be controlled in  $(25 \pm 5) ^\circ\text{C}$  range.
- 4) The testing site should be smoke, fire and explosion resistant, with good ventilation and good pressure relief.
- 5) The testing site shall have an isolated observation window; a video camera or other image collection device can be used to record the event.

### 5.2 Measurement system requirements

The short circuit occurs very quickly. The voltage and temperature readings are very important to properly decide the results from these indicators. In order to record real time response of the sample, the measurement system shall satisfy the following requirements and recommendations.

- 1) The measurement system shall record voltage, temperature and nail position as a function of time.

- 2) Temperature and voltage sampling rate should be larger than 100 Hz (100 records per second).
- 3) Voltage sensitivity should be better than  $\pm 50$  mV; the thermocouple can withstand temperatures higher than 1 000 °C.

### 5.3 Sample setup


There are various shapes and structures of the samples. The sample setup requirements are different for different shapes. A clear description of the sample setup is thus required. The following sessions describe the setup for general sample shapes, cylinder and square. The general principles can be applied to other shapes.

- 1) When punctured the sample shall not rotate, move or deform. The sample can be placed on the insulated and flame resistant surface. If needed (for cylindrical type cell), the sample can be fixed with fixture, but cannot affect the heat radiation and thermal expansion.
- 2) The heat shrink film, if any, is removed to prevent measurement interference.
- 3) A thermocouple is to be placed at the top surface of the sample. The position should be near the puncture point without affecting puncture procedure. The thermocouple should be fixed to avoid position shift due to smoke, fire or explosion.
- 4) The voltage signal is monitored by connecting to the terminals of the meter.

### 5.4 Puncture method

There are different kinds of sample assembly patterns, such as stacked and spiral. If the puncture depth is different, the damage inside the sample will be different. The measuring temperature point will also be different. These will cause inconsistent results. It is important to define the puncture direction and depth. The puncture method is as follows.

- 1) The nail puncture direction is perpendicular to the sample's electrode plane. The direction can be Z-axis (vertical) or XY-axis (horizontal). The puncture speed and force should follow the test specification described in 5.5 1).
- 2) The puncture through depth of cell is 4 mm, as shown in Figure 3.

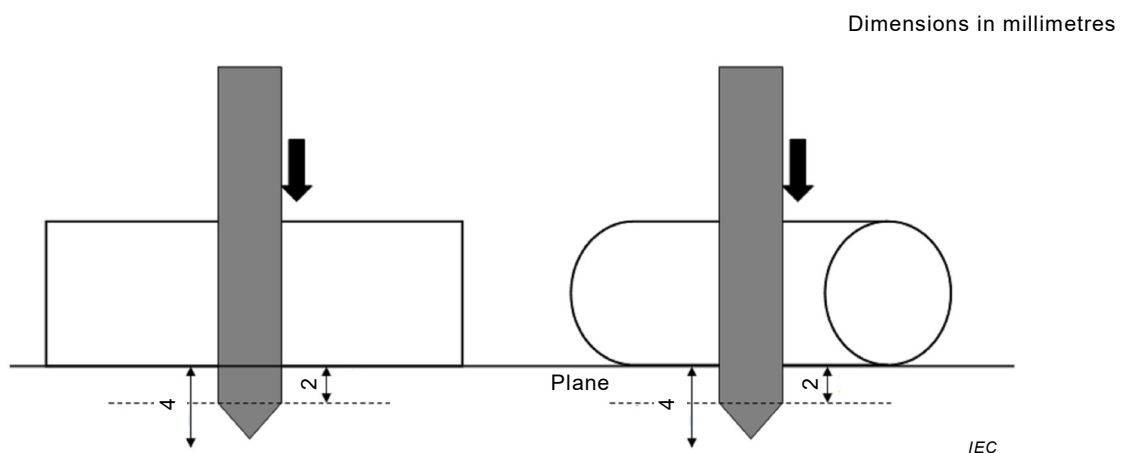


**Figure 3 – The puncture through depth of cell**

- 3) The recording of voltage and temperature is synchronized with the movement of the nail.
- 4) Once the temperature is stable, the sample can be removed. The puncture nail should not be reused and should be discarded.

**5.5 Design of testing method**

The testing method is a comparative methodology with two different samples, one is the reference sample (without nanomaterial), the other one is the test sample (with nanomaterial). The test procedures are as follows.

- 1) The puncture nail punctures the reference sample at several different speeds between 0,1 mm/s and 50 mm/s. The starting test speed is 25 mm/s, the following speed selection is based on high/low hazard levels dichotomy. Figure 4 shows the flow chart of test procedures. The high/low hazard levels are described in Table 1. The recommended number of tests is four to five for the reference sample and three to five for the test sample.
- 2) Repeat process 1) two to four times for repeatability test.
- 3) If the repeatability result fails, select another batch of reference samples and test again.
- 4) Temperature, voltage data and hazard level should be recorded.

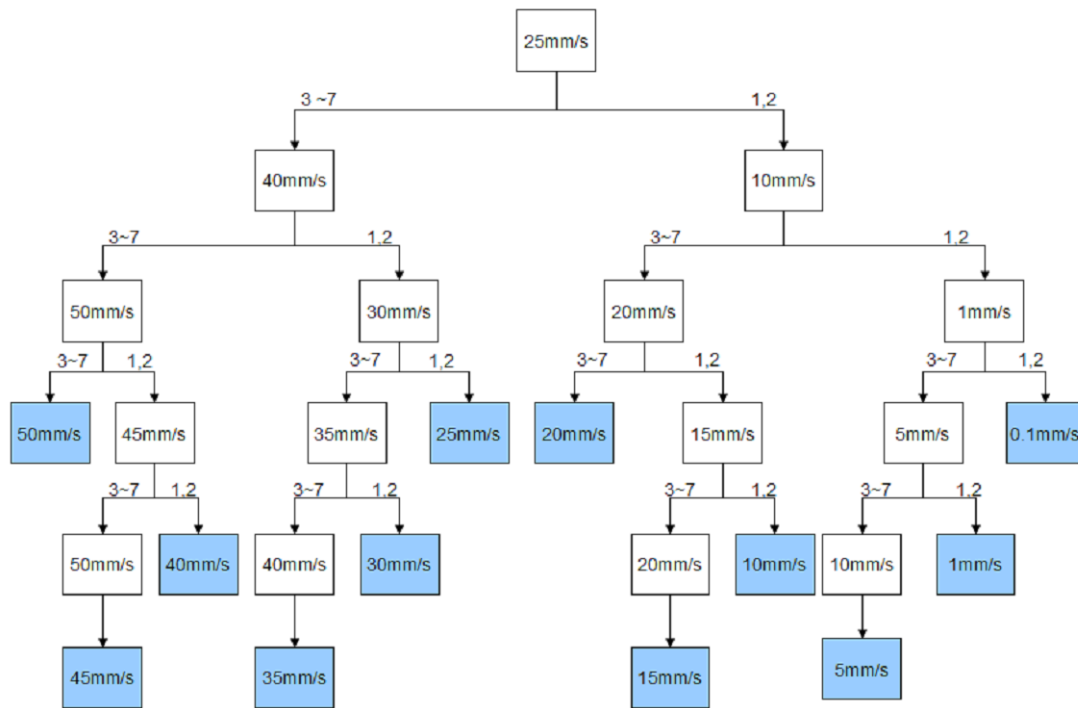

IEC

**Figure 4 – Flow chart of reference sample test procedures**

**Table 1 – Hazard level description**

Hazard level	Results	Abbreviation	Description
1	No smoke, no fire	P	No significant change in appearance
2	Vent	V	Electrolyte evaporation
3	Smoke	S	Swelling, the appearance of charred, emitting smoke
4	Spark + smoke	SS	Smoke and sparks
5	Heavy smoke	HS	A lot of smoke coming out
6	Fire	F	On fire
7	Explosion	EX	Explosion

## 6 Data analysis / interpretation of result

### 6.1 Samples classification from the results

#### 6.1.1 Reference sample (without nanomaterials)


- 1) Results P and V are low temperature safe zone.
- 2) Results S, SS, HS and F are high temperature danger zone. HS and F results will cause the greatest hazard.

#### 6.1.2 Test sample (with nanomaterials)

- 1) If the results of the reference samples and test samples are P or V, it indicates that the nanomaterial additive does not contain performance enabled or enhanced functionality.
- 2) If the results of the reference samples and test samples are S or SS or HS, it indicates that the nanomaterial additive does not contain performance enabled or enhanced functionality.
- 3) If the results of reference samples are S or SS or HS, and the results of test samples are F or EX, it indicates that the nanomaterial additive worsens the performance.
- 4) If the results of reference samples are S or SS or HS, and the results of test samples are P or V, it indicates that the nanomaterial additive does contain performance enabled or enhanced functionality.
- 5) If the results of reference samples are F or EX, and the results of test samples are S or SS or HS, it indicates that the nanomaterial additive contains limited performance enabled or enhanced functionality.
- 6) If the results of reference samples are F or EX, and the results of test samples are P or V, it indicates that the nanomaterial additive contains performance enabled or enhanced functionality.

### 6.2 Data analysis


- 1) Single test sample plot: to create a plot of voltage and temperatures versus time. The temperatures include surface and puncture point temperature. This plot can analyse voltage drop and temperature increment when puncture is initiated as shown in Figure 5.

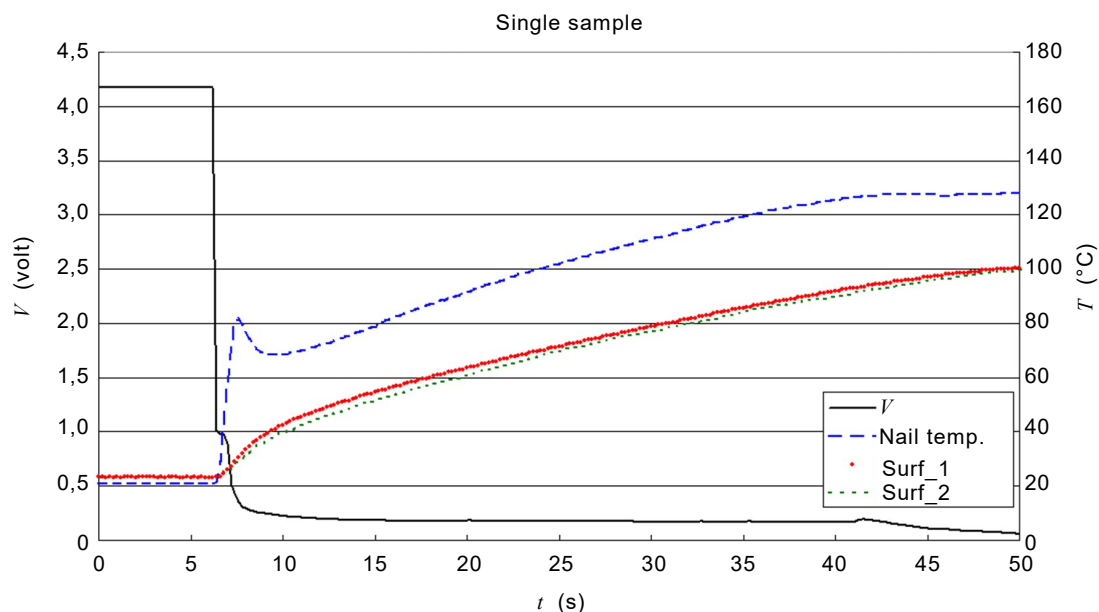

IEC


Figure 5 – Voltage and temperatures versus time plot

- 2) Repeatability plot: to create a plot of voltage and temperature versus time of multiple samples. The temperature includes only puncture point temperature. This plot can analyse whether the repeatability is good or not as shown in Figure 6.

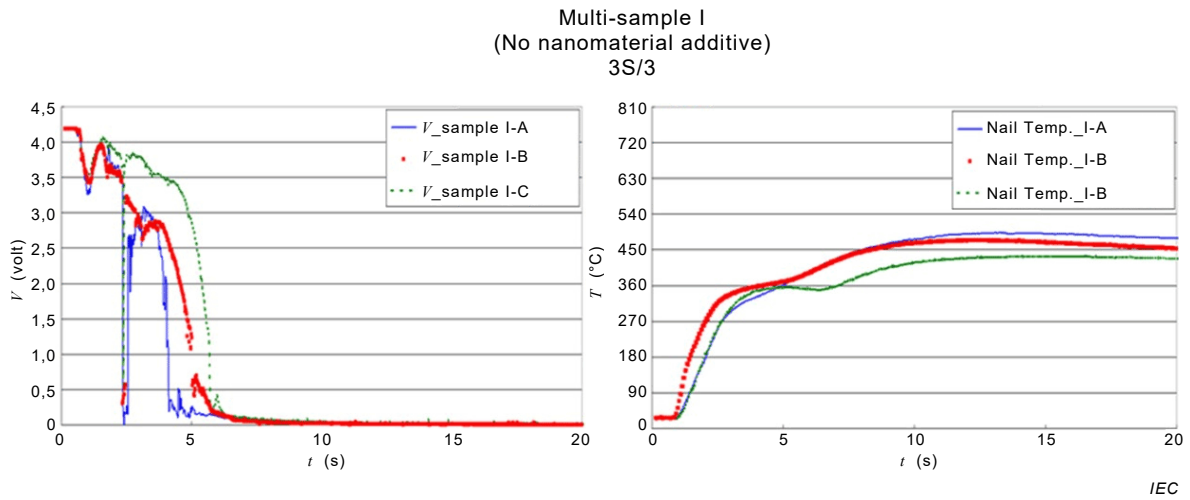

**Figure 6 – Repeatability plot of voltage and temperature versus time**

- 3) Performance comparison plot: to create a plot of voltage and temperature versus time of different types of nanomaterial additive samples. The temperature includes only puncture point temperature. Samples with different types of nanomaterial additive are plotted together for comparison. This plot can determine whether the performance is improved or not due to nanomaterial additive as shown in Figure 7. If the test results are difficult to discriminate, further quantitative analysis of nail temperature can discriminate the performance change.

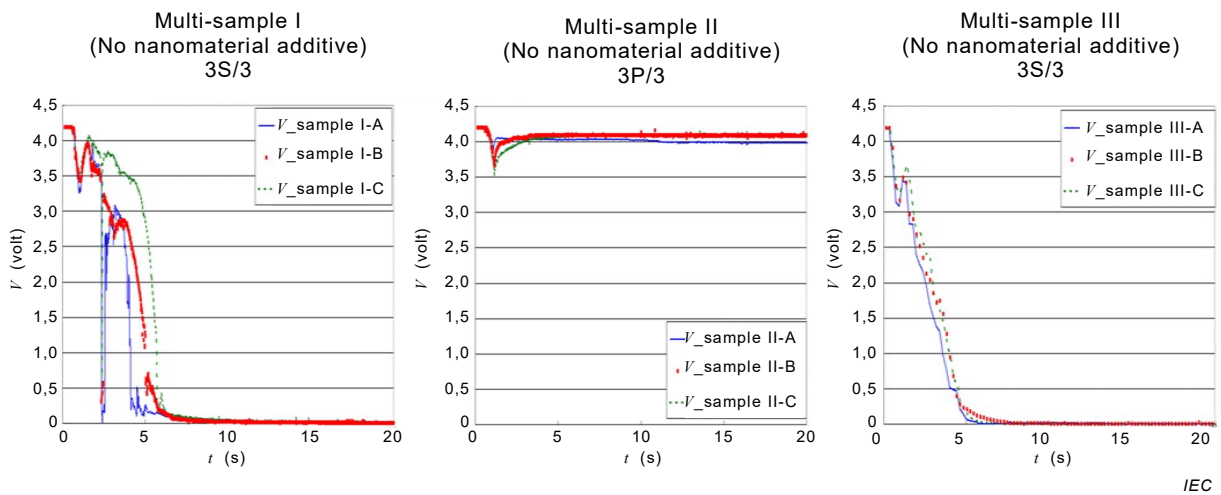

**Figure 7 – Performance comparison plot of voltage and temperature versus time**



## Annex A (informative)

### Data report example

Tables A.1 to A.5 illustrate the specification table examples for anode, cathode, electrolyte, separator and cell. Table A.6 illustrates the sample analysis table for different additives.

**Table A.1 – Anode specifications**

Sample	Anode material	Energy density	Thickness of Al foil	Nanomaterial
1	same	same	same	X
2				P-1
3				P-2

**Table A.2 – Cathode specifications**

Sample	Cathode material	Energy density	Thickness of Cu foil	Nanomaterial
1	same	same	same	X
4				N-1
5				N-2

**Table A.3 – Electrolyte specifications**

Sample	Electrolyte formula	Nanomaterial
1	same	X
6		E-1
7		E-2

**Table A.4 – Separator specifications**

Sample	Material	Aperture	Shutdown temperature	Coating
1	same	same	same	X
8				C-1
9				C-2

**Table A.5 – Cell specification**

sample	Electrode structure	Container	Capacity	size
1	same	same	same	same
2				
3				
4				
5				
6				
7				
8				
9				

**Table A.6 – Sample analysis**

	<b>Anode additive</b>	<b>Cathode additive</b>	<b>Electrolyte additive</b>	<b>Separator coating</b>
1	X	X	X	X
2	P-1	X	X	X
3	P-2	X	X	X
4	X	N-1	X	X
5	X	N-2	X	X
6	X	X	E-1	X
7	X	X	E-2	X
8	X	X	X	C-1
9	X	X	X	C-2

NOTE Shading for sample 1 indicates no nanomaterial additive for performance comparison. Shading for other samples indicates the specific nanomaterial additive added.

## Bibliography

IEC TS 62844, *Guidelines for quality and risk assessment for nano-enabled electrotechnical products*<sup>1</sup>

---

---

<sup>1</sup> Under preparation. Stage at the time of publication: IEC DTS 62844:2014.





# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

## Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

## Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Useful Contacts

### Customer Services

**Tel:** +44 345 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 345 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

### BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK