



BSI Standards Publication

Rubber — Measurement of the aromaticity of oil in reclaimed rubbers

National foreword

This Published Document is the UK implementation of ISO/TR 16314:2010.

The UK participation in its preparation was entrusted to Technical Committee PRI/23, Test methods for rubber and non-black compounding ingredients.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 70974 6

ICS 83.040.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This Published Document was published under the authority of the Standards Policy and Strategy Committee on 28 February 2011.

Amendments issued since publication

Date	Text affected
------	---------------

**Rubber — Measurement of the aromaticity
of oil in reclaimed rubbers**

*Caoutchouc — Détermination de l'aromaticité des huiles dans
les caoutchoucs régénérés*



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Reagents and materials	1
4.1 Extraction solvent	1
4.2 Sample preparation reagents	1
5 Apparatus	2
6 Procedure	2
6.1 Sample extraction	2
6.2 Purification of extract	3
6.3 NMR analysis	3
7 Calculation	4
8 Test report	5
Annex A (informative) ¹ H NMR analysis results for typical reclaimed rubbers	6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

In exceptional circumstances, when a technical committee has collected data of a different kind from that which is normally published as an International Standard ("state of the art", for example), it may decide by a simple majority vote of its participating members to publish a Technical Report. A Technical Report is entirely informative in nature and does not have to be reviewed until the data it provides are considered to be no longer valid or useful.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO/TR 16314 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 3, *Raw materials (including latex) for use in the rubber industry*.

Rubber — Measurement of the aromaticity of oil in reclaimed rubbers

WARNING — Persons using this document should be familiar with normal laboratory practice. This document does not purport to address all the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

1 Scope

This Technical Report provides a method for the selective determination of polyaromaticity of oil in reclaimed rubbers. The method is based on nuclear magnetic resonance (NMR) spectrometry.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1407, *Rubber — Determination of solvent extract*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

polycyclic aromatic hydrocarbon

PAH

organic compound consisting of two or more aromatic rings, certain carbon atoms of which are common to two or three rings

4 Reagents and materials

All reagents shall be of recognized analytical grade unless otherwise specified.

4.1 Extraction solvent

4.1.1 Acetone.

4.2 Sample preparation reagents

4.2.1 *n*-Hexane.

4.2.2 Methylene chloride.

4.2.3 Nitrogen, purity > 99,9 %, for protecting the extract from oxidation during drying.

4.2.4 CDCl₃, 99,9 %, NMR grade.

4.2.5 Hexamethyldisiloxane (HMDS), 99,5 %, NMR grade, or **tetramethylsilane (TMS)**, 99,5 %.

5 Apparatus

5.1 Analytical balance, accurate to 0,1 mg.

5.2 Extraction apparatus, as specified in ISO 1407.

5.3 Steam bath.

5.4 Extract purification apparatus, consisting of the items specified in 5.4.1 to 5.4.5:

5.4.1 2 cm³, 5 cm³ and 25 cm³ or 30 cm³ syringes, with conical end fittings, compatible with solid-phase extraction (SPE) columns for manual purification operations.

5.4.2 SPE cartridge containing 500 mg of silica gel.¹⁾

5.4.3 Laboratory glassware.

5.4.4 (Optional) Solid-phase extraction equipment, connected to a vacuum pump, for simultaneous purification of many extracts.

5.4.5 Disposable needles.

5.5 NMR spectrometer, at least 200 MHz, preferably with the following acquisition parameters:

- probe: ¹H;
- pulse phase: 30°;
- spectral width: – 2 ppm to +12 ppm;
- number of scans: 256;
- relaxation delay: 2 s.

6 Procedure

6.1 Sample extraction

6.1.1 The laboratory sample shall be of sufficient size to provide at least 350 mg of extracted oil.

6.1.2 Pass the sample between the rolls of a laboratory mill to reduce its thickness to less than 0,7 mm or, alternatively, cut the sample in pieces smaller than 1 mm × 1 mm × 2 mm.

1) VARIAN BOND ELUT JR-SI, 500 mg, part number 12162037B, is an example of a suitable product available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of this product. Equivalent products may be used.

6.1.3 Wrap the sample in a small filter paper and insert it in the extractor (5.2) or fill the extractor with the small cut pieces. Fill the flask of the extractor with acetone (4.1.1) and extract for 8 h.

6.1.4 Evaporate the extract to dryness under a stream of nitrogen (4.2.3) to prevent oxidation.

6.2 Purification of extract

6.2.1 Weigh, to the nearest 0,1 mg, $100 \text{ mg} \pm 5 \text{ mg}$ of dry extract into a vial and dissolve it in 1 cm^3 of methylene chloride (4.2.2). There may be some insoluble matter.

6.2.2 Condition the SPE cartridge (5.4.2) by injecting 5 cm^3 of *n*-hexane (4.2.1) onto it using a 5 cm^3 syringe (5.4.1).

6.2.3 When nearly all the *n*-hexane has drained out, transfer quantitatively the methylene chloride solution onto the SPE cartridge and start collecting the eluate in a beaker or glass bottle. Use an additional $0,5 \text{ cm}^3$ of methylene chloride to rinse the vial and ensure complete transfer of the evaporation residue to the cartridge.

6.2.4 When nearly all the methylene chloride solution has been absorbed onto the SPE cartridge, start eluting the non-polar fraction with 25 cm^3 of hexane. During the elution, maintain a constant solvent flow not exceeding a rate of $5 \text{ cm}^3/\text{min}$.

6.2.5 Stop collecting the purified fraction when all of the 25 cm^3 of *n*-hexane has been added to the SPE cartridge.

6.2.6 Evaporate the eluate to dryness under a stream of nitrogen to prevent oxidation.

6.2.7 Weigh the dry residue to the nearest 0,1 mg and calculate the percentage recovered.

6.2.8 Repeat the extract purification procedure two more times, taking a fresh portion of extract each time.

6.2.9 Calculate the average of the three percentage recovery values. If the individual values obtained are within $\pm 5 \%$ of the average, proceed to 6.3. Otherwise, repeat the sample extraction and extract purification procedure until three values within $\pm 5 \%$ of the average are obtained.

6.3 NMR analysis

6.3.1 General

The aromatic character of the oil present in the dry residue obtained in 6.2.7 is determined by means of ^1H NMR spectroscopy.


6.3.2 Principle

The molecular structure of non-linear PAHs with three or more fused rings contains a characteristic three-sided concave area, located at the periphery of the molecule. The hydrogen atoms in this area are called bay region hydrogens (see Figure 1).

^1H NMR spectroscopy can identify and quantify selectively the hydrogen atoms in the bay region, which are characteristic of aromatic oils.

This method describes a procedure for determining the percentage of bay region hydrogens ($\% \text{H}_{\text{Bay}}$) in a sample solution by ^1H NMR, thus giving an indication of the aromatic character of the oil.

The higher the percentage of bay region hydrogens, the higher the aromaticity.

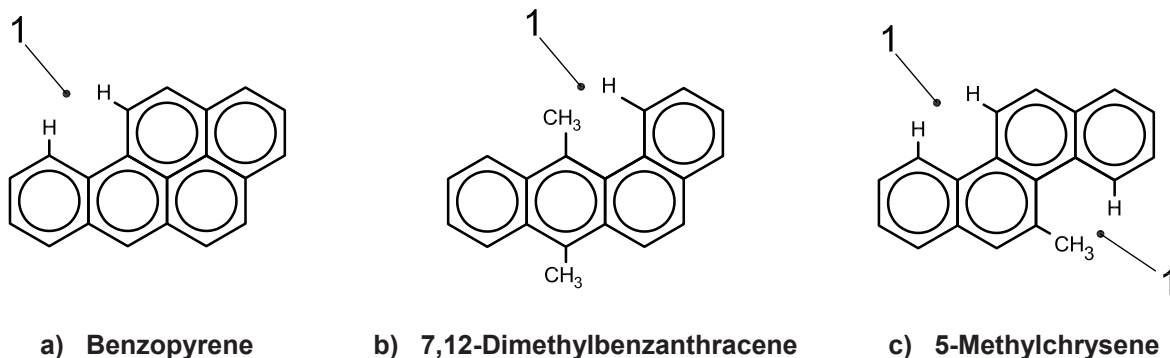

Key

1 bay region

Figure 1

6.3.3 NMR measurement

6.3.3.1 Dissolve one of the dry residues obtained in 6.2.7 and 6.2.8 in a glass vial in about 1 cm³ of CDCl₃ (4.2.4). If necessary, enhance dissolution by using a small magnetic stirrer or mechanical shaker. If this is not enough, add more CDCl₃.

6.3.3.2 Prepare the NMR tube by adding the sample solution prepared in 6.3.3.1 and a few drops of reference solvent, HMDS or TMS (4.2.5).

6.3.3.3 Acquire the free induction decay (FID) signal and apply a Fourier transform, multiplying by an exponential function (LB = 0,3 Hz) to obtain the spectrum. Adjust the resonance of the reference (HMDS or TMS) peak to 0,0 ppm.

6.3.3.4 Integrate the spectrum and record the following areas:

- I_0 the aromatic area, from 6,0 ppm to 9,5 ppm, including the CHCl₃ signal (impurity contained in CDCl₃);
- I_{CHCl_3} the CHCl₃ signal (located around 7,2 ppm);
- I_1 the pure aromatic area (= $I_0 - I_{\text{CHCl}_3}$);
- I_2 the area of the bay region from 8,3 ppm to 9,5 ppm;
- I_3 the area of the aliphatic and ethylenic regions from 0,2 ppm to 5,8 ppm.

6.3.3.5 Perform NMR measurements on each of the three purified extracts obtained in 6.2.7 and 6.2.8.

7 Calculation

For each of the three purified extracts, calculate the percentage of bay region hydrogens (% H_{Bay}) to two decimal places using the following equation:

$$\% \text{H}_{\text{Bay}} = \frac{I_2}{I_1 + I_3} \times 100$$

where the symbols are as defined in 6.3.3.4.

8 Test report

The test report shall include the following information:

- a) a reference to this Technical Report (ISO/TR 16314);
- b) all details necessary for the identification of the rubber sample(s) tested;
- c) details of the silica gel used in the solid-phase extraction cartridge (5.4.2);
- d) the three percentage recovery values calculated in 6.2.7 and 6.2.8;
- e) the average values of I_0 , I_{CHCl_3} , I_1 , I_2 , I_3 and % H_{Bay};
- f) any unusual features noted during the determination;
- g) details of any operation not included in this Technical Report, as well as details of any aspect regarded as optional, such as the NMR parameters in 5.5 if different from those specified;
- h) the date of the test.

Annex A
(informative)

¹H NMR analysis results for typical reclaimed rubbers

Rubber	Type of oil	Bay region hydrogens %
Ecorr RNR30 B01 Rubber Resources (Netherlands)	Non-aromatic	0,15 ± 0,07
Green rubber (Malaysia)	Aromatic	0,57 ± 0,17
Jeng Yuan Tyrec M1 (Malaysia)	Aromatic	0,62 ± 0,18
Union Commercial UCD-103 (Thailand)	Aromatic	0,59 ± 0,18
RBR NE Rubber Resources (Netherlands)	Non-aromatic	0,13 ± 0,07

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™