
**Glass in building — Determination of
the bending strength of glass —**

Part 1:
Fundamentals of testing glass

*Verre dans la construction — Détermination de la résistance du verre
à la flexion —*

Partie 1: Principes fondamentaux des essais sur le verre



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols	2
5 Factors to be taken into account when testing glass	3
5.1 Glass as a material.....	3
5.1.1 General.....	3
5.1.2 Effect of surface condition.....	4
5.1.3 Effect of rate of loading.....	4
5.1.4 Effect of test surface area.....	4
5.1.5 Effect of ambient medium.....	5
5.1.6 Effect of aging.....	5
5.1.7 Effect of temperature.....	5
5.2 Bending stress and bending strength.....	5
5.2.1 General.....	5
5.2.2 Effective stress.....	5
5.2.3 Equivalent bending strength.....	6
5.2.4 Profile bending strength.....	6
5.3 Types of glass.....	6
5.3.1 General.....	6
5.3.2 Patterned glass.....	6
5.3.3 Laminated glass.....	6
5.4 Orientation of the specimens.....	7
5.5 Number of specimens in a sample.....	7
6 Explanations of the test methods	7
6.1 Coaxial double ring test for large test surface areas.....	7
6.1.1 Elimination of edge effects.....	7
6.1.2 Analysis of the stress development.....	7
6.1.3 Testing of patterned glass.....	11
6.2 Test with specimen supported at two points (four point bending).....	11
6.1.4 Limitations.....	11
6.1.5 Inclusion of edge effects.....	11
6.1.6 Analysis of the stress development.....	11
6.3 Coaxial double ring test for small test surface areas.....	13
6.1.7 Elimination of edge effects.....	13
6.1.8 Analysis of the stress development.....	13
7 Range of application of the test methods	14
7.1 General limitations.....	14
7.2 Limitations to ISO 1288-2.....	14
7.3 Limitations to ISO 1288-3.....	14
7.4 Limitations to ISO 1288-4.....	15
7.5 Limitations to ISO 1288-5.....	15
8 Calibration of the testing machines	15
9 Recommendations for safe use of test equipment	15
Bibliography	17

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 160, *Glass in building*, Subcommittee SC 2, *Use considerations*.

ISO 1288 consists of the following parts, under the general title *Glass in building — Determination of the bending strength of glass*:

- *Part 1: Fundamentals of testing glass*
- *Part 2: Coaxial double ring test on flat specimens with large test surface areas*
- *Part 3: Test with specimen supported at two points (four point bending)*
- *Part 4: Testing of channel shaped glass*
- *Part 5: Coaxial double ring test on flat specimens with small test surface areas*

Glass in building — Determination of the bending strength of glass —

Part 1: Fundamentals of testing glass

1 Scope

This part of ISO 1288 specifies the determination of the bending strength of monolithic glass for use in buildings. The testing of insulating units or laminated glass is excluded from this part of ISO 1288.

This part of ISO 1288 describes

- considerations to be taken into account when testing glass,
- explanations of the reasons for designing different test methods,
- limitations of the test methods, and
- gives pointers to safety requirements for the personnel operating the test equipment.

ISO 1288-2, ISO 1288-3, ISO 1288-4 and ISO 1288-5 specify test methods in detail.

The test methods specified in this part of ISO 1288 are intended to provide large numbers of bending strength values that can be used as the basis for statistical evaluation of glass strength.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1288-2, *Glass in building — Determination of the bending strength of glass — Part 2: Coaxial double ring test on flat specimens with large test surface areas*

ISO 1288-3, *Glass in building — Determination of the bending strength of glass — Part 3: Test with specimen supported at two points (four point bending)*

ISO 1288-4, *Glass in building — Determination of the bending strength of glass — Part 4: Testing of channel shaped glass*

ISO 1288-5, *Glass in building — Determination of the bending strength of glass — Part 5: Coaxial double ring test on flat specimens with small test surface areas*

ISO 16293-1, *Glass in building — Basic soda lime silicate glass products — Part 1: Definitions and general physical and mechanical properties*

NOTE ISO TC 160/SC 1 is commencing work on standards for “thermally tempered soda lime silicate safety glass”, “heat strengthened soda lime silicate glass” and “chemically strengthened glass.”

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

- 3.1 flat glass**
any glass product conforming to ISO 16293-2, ISO 16293-3, ISO 16293-4 and ISO 16293-5, or any transformed glass made from these products without deliberately inducing profile or curvature
- 3.2 bending stress**
tensile bending stress induced in the surface of a specimen
- Note 1 to entry: For testing purposes, the bending stress should be uniform over a specified part of the surface.
- 3.3 effective bending stress**
weighted average of the tensile bending stresses, calculated by applying a factor to take into account non-uniformity of the stress field
- 3.4 bending strength**
bending stress (3.2) or *effective bending stress* (3.3) which leads to breakage of the specimen
- 3.5 equivalent bending strength**
apparent *bending strength* (3.4) of patterned glass, for which the irregularities in the thickness do not allow precise calculation of the *bending stress* (3.2)
- 3.6 profile bending strength**
quotient of the maximum bending moment and the section modulus of a channel shaped glass
- 3.7 stress intensity factor**
measure of the stress at a crack tip
- 3.8 prestressed glass**
any glass product that has a surface prestress, i.e. thermally tempered soda lime silicate safety glass, heat strengthened soda lime silicate glass and chemically strengthened glass

4 Symbols

F	applied load	N
h	specimen thickness	M
L	length of side of square test sample	M
k	constant for calculation of bending stress in ISO 1288-3	M
K_1, K_2	constants for calculation of bending stress in ISO 1288-5	
M_{bB}	maximum bending moment	Nm
p	gas pressure applied within loading ring in ISO 1288-2	Pa
P_{bB}	profile bending strength (of channel shaped glass) = M_{bB}/Z	Pa
r_1	radius of loading ring	M
r_2	radius of supporting ring	M

r_3	radius of circular specimen	M
r_{3m}	average specimen radius (for evaluation)	M
y_0	central deflection of specimen	M
Z	section modulus (of channel shaped glass)	m ³
μ	poisson number of specimen	
NOTE	For soda lime silicate glass (see ISO 16293-1), a value of 0,23 is used.	
σ_b	bending stress	Pa
σ_{beff}	effective bending stress	Pa
σ_{bB}	bending strength	Pa
σ_{beqB}	equivalent bending strength	Pa
σ_{rad}	radial stress	Pa
σ_T	tangential stress	Pa
σ_L	stress in a direction along the length of the specimen	Pa

5 Factors to be taken into account when testing glass

5.1 Glass as a material

5.1.1 General

Glass is a homogeneous isotropic material having almost perfect linear-elastic behaviour over its tensile strength range.

Glass has a very high compressive strength and theoretically, a very high tensile strength, but the surface of the glass has many irregularities which act as weaknesses when glass is subjected to tensile stress. These irregularities are caused by attack from moisture and by contact with hard materials (e.g. grit) and are continually modified by moisture which is always present in the air.

Tensile strengths of around 10 000 MPa can be predicted from the molecular structure, but bulk glass normally fails at stresses considerably below 100 MPa.

The presence of the irregularities and their modification by moisture contributes to the properties of glass which need consideration when performing tests of strength.

Because of the very high compressive strength, glass always fails under tensile stress. Since glass in buildings is very rarely used in direct tension, the most important property for load resistance is the tensile bending strength. All the tests described in this part of ISO 1288 are intended to evaluate the tensile bending strength of glass.

The bending strength is influenced by the following factors:

- a) surface condition (see [5.1.2](#));
- b) rate and duration of loading (see [5.1.3](#));
- c) area of surface stressed in tension (see [5.1.4](#));
- d) ambient medium, through stress corrosion cracking, as well as healing of surface damage in the glass (see [5.1.5](#) and Reference [1]);

ISO 1288-1:2016(E)

- e) age, i.e. time elapsing since the last mechanical surface treatment or modification to simulate damage (see [5.1.6](#));
- f) temperature (see [5.1.7](#)).

The influence exerted by factors b) to f) on bending strength has been taken into account in this part of ISO 1288.

5.1.2 Effect of surface condition

For the purpose of bending strength tests according to this part of ISO 1288, glass behaves as an almost ideally linear-elastic material that fails in a brittle manner. This brittleness means that contact with any hard object can lead to surface damage in the form of ultra-fine, partly submicroscopic cracks and chips. Surface damage of this kind, which is practically unavoidable during normal handling of glass, exerts a notch action which is a major factor in reducing mechanical strength, whereas the chemical composition of the glass has only a minor, and in some cases, entirely negligible, significance.

Hence, it follows that the bending strength determined by the methods referred to in this part of ISO 1288 is related largely to the surface condition of the specimen to be tested.

This surface condition is characterized by the following main features:

- a) the surface condition imparted by a particular method of treatment, which produces a specific damage spectrum and thus, results in a strength which is specific to the finished surface condition;
- b) residual stress, e.g. in the form of thermal or chemical prestress intentionally imparted, as well as unintended residual stresses.

5.1.3 Effect of rate of loading

For the interpretation of the bending strength values determined as described in this part of ISO 1288, the rate of loading is of special importance.

Cracks propagate in glass over a wide range of values of tensile stress (see Reference [\[2\]](#)). There is a lower limit to the stress intensity factor below which cracks do not propagate (see Reference [\[1\]](#)). There is then some subcritical crack propagation at higher levels of stress intensity factor, which is influenced by humidity, temperature and chemical agents. Above a critical stress intensity factor, crack propagation is very rapid and leads to (almost) instantaneous failure. The consequence of the subcritical crack propagation is, for example, that the rate of load increase and/or the duration of static loading influences the bending strength.

For prestressed glass, this time dependence does not manifest itself until the tensile stress induced in the surface exceeds the compressive stress permanently present there (see Reference [\[3\]](#)).

5.1.4 Effect of test surface area

The decrease in bending strength of glass with increasing size of the test area exposed to high stress is also of importance (see Reference [\[4\]](#)). This area effect is accounted for by the statistical distribution of surface defects varying in effectiveness; the larger the test area, the greater is the probability of its containing a large surface defect. Consequently, the influence of the area effect increases with decreasing incidence of defects in the surface, so that this influence is more pronounced in the case of undamaged, e.g. fire-finished glass surfaces (see Reference [\[5\]](#)).

Differences are likely between the mean values of the bending strength as measured in accordance with ISO 1288-2 (maximally stressed area: 240 000 mm²), or by using devices R105, R60, R45 and R30 in accordance with ISO 1288-5 (maximally stressed areas: 3 850 mm², 1 260 mm², 254 mm² and 113 mm²), due to the size of the stressed area. Depending on surface damage, the results obtained from testing smaller surface areas may be significantly higher than those obtained from testing larger surface areas, as shown in [Table 1](#).

Table 1 — Approximate effects of test surface area on the mean measured bending strength

Test method	Device	Relative bending strength
ISO 1288-2	—	100 %
ISO 1288-5	R105	120 % to 180 %
ISO 1288-5	R65	125 % to 210 %
ISO 1288-5	R45	140 % to 270 %
ISO 1288-5	R30	145 % to 300 %

Since glass for use in buildings is often in large sizes, the test methods specified in ISO 1288-2 and ISO 1288-3 give values which are more appropriate as the basis for designing flat glass for use in buildings. The test method specified in ISO 1288-5 can be useful as a method of evaluating the comparative bending strength of flat glass.

5.1.5 Effect of ambient medium

The surrounding medium in which the glass is tested has an influence on the strength of the glass, particularly if the moisture level is very low. When glass is used in buildings, the relative humidity typically ranges from 30 % to 100 %. Within this range, the effect on the bending strength, as tested according to this part of ISO 1288, is not great. However, tests on glass for use in buildings shall be undertaken in test conditions with relative humidity levels in the range of 40 % to 70 %, in order to eliminate this effect when comparing bending strength results.

5.1.6 Effect of aging

If the glass surface is modified (by abrasion, etching, edge working, etc.) before the testing, it is necessary to allow the fresh damage to heal before the test is undertaken. The continual surface modification by moisture affects the damage in a way that can reduce any weakening effect (see Reference [1]). In practice, glass is highly unlikely to be stressed directly after it has been treated, so it shall be conditioned for at least 24 h before testing.

5.1.7 Effect of temperature

The bending strength of glass is affected by changes in temperature. Within the normal range of temperatures experienced by glass in buildings, this effect is not very significant, but to avoid possible complications in the comparison of bending strength values, testing shall be undertaken in a restricted range of temperatures.

5.2 Bending stress and bending strength

5.2.1 General

The test methods described in ISO 1288-2, ISO 1288-3, ISO 1288-4 and ISO 1288-5 are designed to induce a uniform bending stress over an area (the test area) of the specimen. However, the stresses induced by the applied loads depend on the nature of the material tested as well as the load distribution.

5.2.2 Effective stress

Where the stress varies significantly over the test area, as is the case in ISO 1288-3 (see 6.1.6), it can be represented by a weighted average stress called the effective bending stress, σ_{eff} . The weighting is obtained by statistically evaluating the probability of fracture at any point in the stressed area.

5.2.3 Equivalent bending strength

Variations in homogeneity or thickness of the specimen affect the stress distribution. Hence, the bending strength, σ_{bB} , is never entirely an accurate value and, in some instances, it is better termed the equivalent bending strength, σ_{beqB} .

For some of the glass types tested (for example, float glass), such variations are very small and the bending strength determined by the tests is sufficiently close to the actual bending strength for the difference to be unimportant.

In the case of patterned glass, however, only the equivalent bending strength can be determined.

5.2.4 Profile bending strength

When channel shaped glass is tested according to ISO 1288-4, most of the specimens fail from fractures originating at the corner of the profile, where the web and flange meet, and not at the extreme of the flange or surface of the web. This is due to secondary stresses generated by the spreading of the flanges when the channel section is bent. In this test, the bending strength is better expressed as the profile bending strength, P_{bB} .

5.3 Types of glass

5.3.1 General

The tests specified in ISO 1288-2, ISO 1288-3 and ISO 1288-5 are for testing flat glass. This includes float glass, drawn sheet glass, patterned glass, patterned wired glass, polished wired glass and prestressed glass, provided there has been no deliberately induced curvature or profile (other than the patterned surface of patterned glass).

5.3.2 Patterned glass

The coaxial double ring test for large test surface areas (see ISO 1288-2) can be used to determine the equivalent bending strength of patterned glass, provided the maximum and minimum thicknesses do not deviate by more than 30 % or 2 mm, whichever is the lower, from the average thickness. This is because of difficulties in sealing the pressure ring to a patterned surface.

There is no limitation on the depth of pattern if the four point bending test (ISO 1288-3) is used.

5.3.3 Laminated glass

The testing of the bending strength of laminated glass (see ISO 12543-1) is excluded from this part of ISO 1288.

In a bending test, additional shear deformation arises in the elastic or plastic interlayers (sliding of the hard glass plies on the interlayer). This effect means that measuring the bending strength of laminated glass is likely to give a strength value less than the actual bending strength of a monolithic glass of the same thickness. This shear deformation is particularly sensitive to the effects of temperature and loading rate.

Laminated glass is manufactured from monolithic glass products that can be tested individually by the test methods described in ISO 1288-2, ISO 1288-3 and ISO 1288-5.

The process of manufacture is unlikely to cause significant changes in the bending strength of the component glasses, so it is unnecessary to test laminated glass which can be assumed to have bending strengths appropriate to their individual components.

The load resistance of laminated glass depends on the interactions between the component parts of the composite structure, which is beyond the scope of this part of ISO 1288.

5.4 Orientation of the specimens

Many glass products lack symmetry in their production. This may be immediately obvious, such as a patterned glass, which is likely to have one surface much more deeply patterned than the other and possibly in which the pattern is directional, or it may be less obvious, such as the side on which the wheel cut was made (see ISO 1288-3:—, Figure 1).

Where such asymmetry is present, it may be necessary to test the glass in several different orientations in order to determine the bending strength. Samples of glass to be tested shall have all the specimens nominally identical.

5.5 Number of specimens in a sample

The bending strength of glass displays a large variation between nominally identical specimens. Very little information can be obtained by testing only a few specimens, since there is considerable uncertainty about whether the results are representative.

In statistical terms, this uncertainty can be expressed as confidence limits, values between which there is a given probability that the target being sought will lie.

Where the target being sought is in the central part of the bending strength distribution (for instance, the mean value), then the confidence limits can be fairly narrow even with just a few specimens.

An accurate determination of the tensile stress which leads to a low crack probability can require large numbers of specimens when, for example, a characteristic stress, a permissible stress or a design value of bending strength is to be determined.

6 Explanations of the test methods

6.1 Coaxial double ring test for large test surface areas


NOTE This test is specified in ISO 1288-2.

6.1.1 Elimination of edge effects


The special feature of the coaxial double ring bending test in accordance with ISO 1288-2 lies in the fact that only a circular shaped limited area of the surface of the specimen (not, however, its edges) is subjected to maximum stressing. In contrast to other bending tests (for example, see ISO 1288-3), in which the edge of the specimen is subjected to the maximum stress, the procedure in accordance with ISO 1288-2 is suitable for exclusively subjecting surfaces (or different surface conditions) to bending stress. The effect of the specimen edge condition is, for the most part, suppressed.

6.1.2 Analysis of the stress development

When the deflections are relatively small, the central surface area is subjected to uniform tensile stressing [see [Figure 1 a](#)], where the radial and tangential stresses are of equal size.

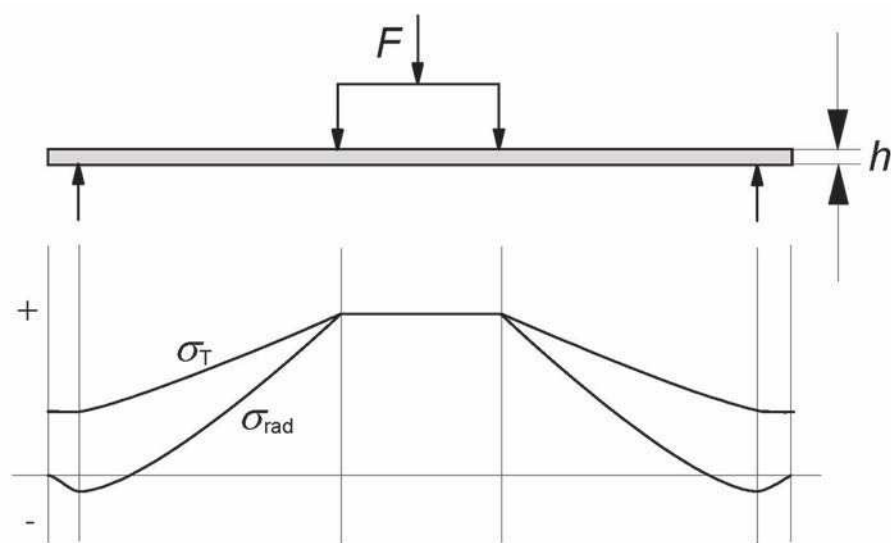

a) In the small deflection range

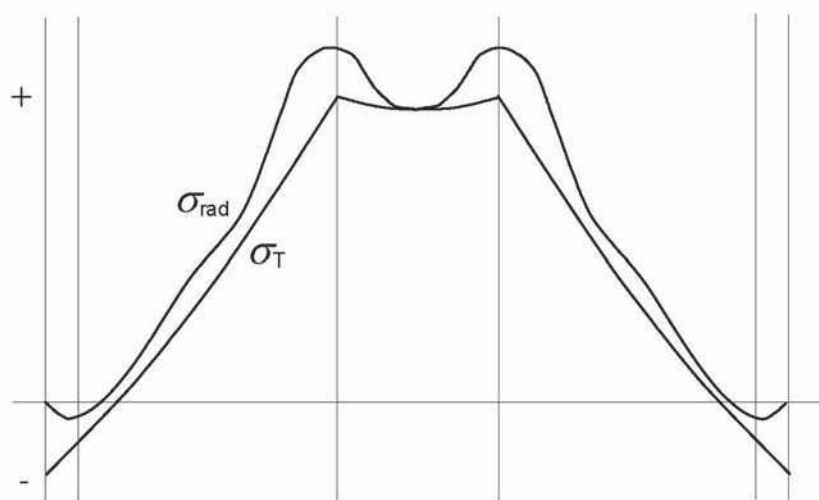


b) In the large deflection range

Figure 1 — Schematic dependence of radial and tangential stresses upon the radius of the specimen, when loaded by a double ring device

If the deflections become larger, i.e. if they exceed approximately half the thickness of the sheet (the precise limit is dependent on the ring ratio, r_2/r_1), this leads to localized increases in stress below the edge of the loading ring, the extent of which increases as the load rises [see [Figure 1 b](#)]. At this stage of the loading, the tangential and radial stresses change differently and a simple calculation of the stresses is no longer possible. The stresses calculated from linear bending theory would be too high.

It has been demonstrated that, by means of a combined ring and surface load (see References [6] to [8]), this increase in stress below the edge of the loading ring can be avoided. With a constant piston force, F , the gas pressure, p , can be optimized in such a way that either the radial or tangential tensile stress develops almost uniformly within the loading ring (see [Figures 2](#) and [3](#)). It is, however, not possible to optimize the gas pressure, p , with regard both to the radial and tangential stress development at the same time.

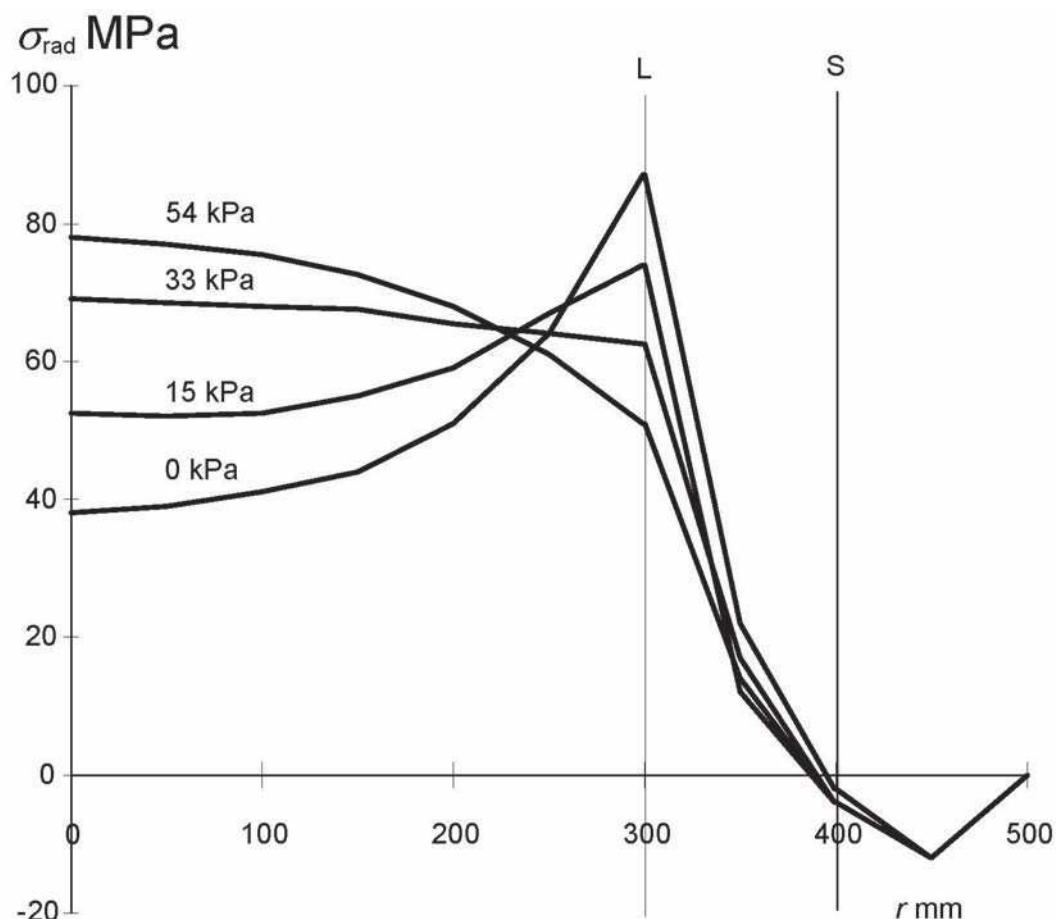**Key**

- L position of loading ring
- S position of supporting ring


This graph has been measured using the following parameters:

Square specimen: 1 000 mm × 1 000 mm × 6 mm; $r_1 = 300$ mm; $r_2 = 400$ mm; $F: 22\,220$ N;

Parameter: gas pressure, p . This determines that the optimized gas pressure, p , is 33 kPa.

Figure 2 — Radial stress development along the median of the convexly bent specimen surface

If the gas pressure, p , is optimized with regard to the radial stress distribution (as given in [Figure 2](#), curve $P = 33$ kPa), then the tangential stress falls towards the loading ring (as given in [Figure 3](#), curve $P = 33$ kPa). If the gas pressure, p , is optimized with regard to the tangential stress distribution (as given in [Figure 3](#), curve $P = 15$ kPa), then the radial stress rises towards the loading ring (as given in [Figure 2](#), curve $P = 15$ kPa). Since, in the case of brittle materials, it is always the normal stresses which cause fractures to be triggered-off, the non-homogenous distribution of the radial stress is the decisive factor in the triggering of the fracture. For this reason the gas pressure, p , is always optimized with regard to the radial stress development for practical test purposes.

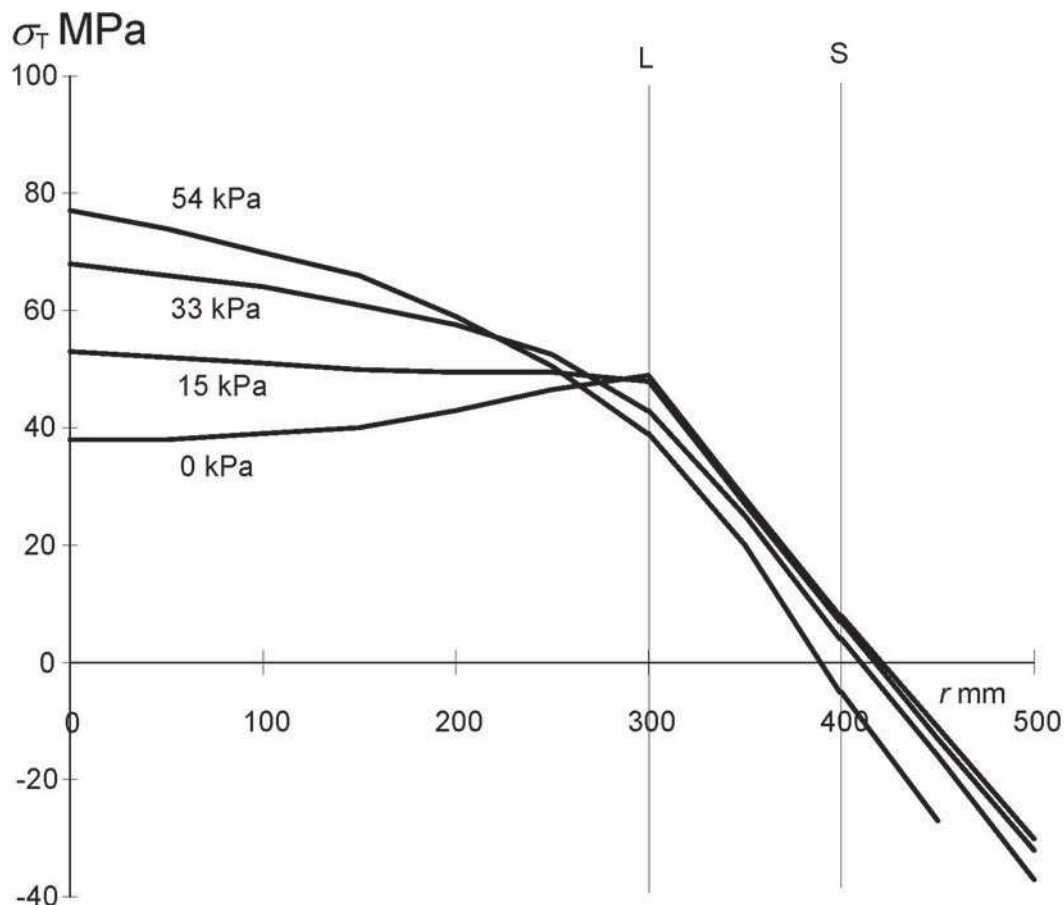

Key

- L position of loading ring
- S position of supporting ring

This graph has been measured using the following parameters:

Square specimen: 1 000 mm × 1 000 mm × 6 mm; $r_1 = 300$ mm; $r_2 = 400$ mm; $F: 22\,220$ N;

Parameter: gas pressure, p . This determines that the optimized gas pressure, p , is 15 kPa.

Figure 3 — Tangential stress development along the median of the convexly bent specimen surface

However, the advantage of the biaxial stress condition, the two principal stresses of which are of equal size, as is apparent during the double ring bending process in the case of small deflections (see 6.3), is lost. This disadvantage is, however, more than offset by the large test surface area, unless the surface damage has a clear preferential direction (e.g. one or more parallel scratches).

In the case of square specimens, the stress distribution is slightly directional; the stresses along the medians and the diagonals differ slightly, within a range of about 5 %.

The curves in ISO 1288-2:—, Figure 3 and the values in ISO 1288-2:—, Table 3 have been determined from measurements. Deviations of individual measured values from the curves or table values are, at most, 5 %.

6.1.3 Testing of patterned glass

Specimens with one or two patterned surfaces cannot be tested by means of a small test area using the coaxial double ring bending test (see [6.3](#) and ISO 1288-5), since the surface spread of the decorations are approximately the same size as the test surface area.

However, with a double ring bending test with a large test area in accordance with ISO 1288-2, it is possible to test glass with patterned surfaces. The permissible structural depth given in [5.3.2](#) (local deviations from the average thickness a maximum of 30 % or 2 mm, whichever is the lower) is based upon experimental results.

Where there are one or two patterned surfaces, the condition of the line-shaped introduction of force by the edge of the loading ring is violated by the necessity to introduce a thicker intermediate layer on the loading ring side. The only effect, however, is to reduce somewhat in size the surface area of the virtually homogeneous radial stress distribution. Otherwise, the stress values remain almost unaffected.

6.2 Test with specimen supported at two points (four point bending)

NOTE This test is specified in ISO 1288-3.

6.1.4 Limitations


This test is not appropriate for products which are expected to have deflections greater than 25 times their thickness.

6.1.5 Inclusion of edge effects

This test is performed as a beam bending test using a wide beam. The edges of the specimen, over the central span of nominally uniform, unidirectional stress, are subjected to the maximum stress as well as the surface. If it is required to determine the bending strength of glass where the effects of the edge are important, this test should be used.

6.1.6 Analysis of the stress development

Simple theory assumes that there are no stresses developed across the width of a beam when it is subjected to bending along its length. However, while this may be a good approximation for narrow beams, the Poisson effect generates significant stresses across the width of wide beams. These stresses induce a contraflexion across the width of the beam, so that the longitudinal stress cannot be regarded as uniform across the width (see Reference [\[9\]](#)). The effect is to increase the tensile bending stress developed at the edges of the beam and decrease the tensile bending stresses at the mid-line of the beam (as shown in [Figure 4](#)).

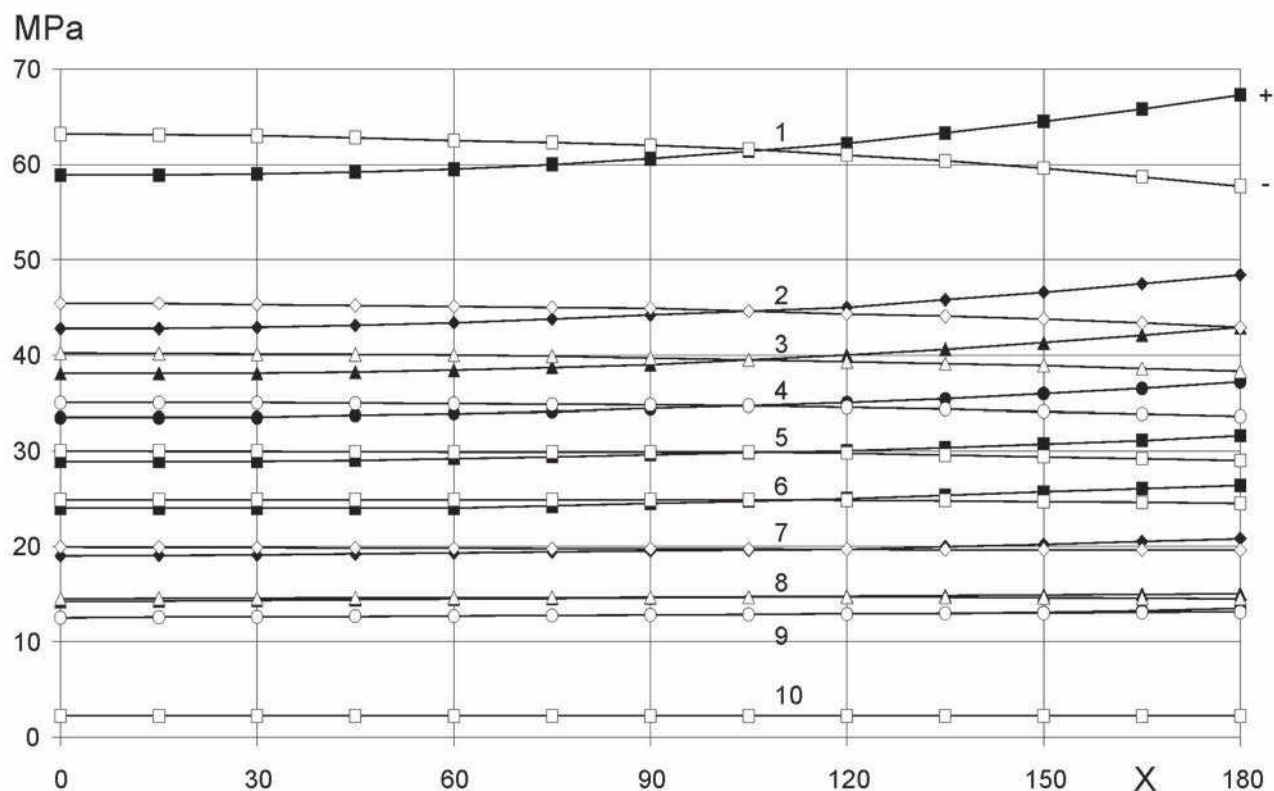

- Key**
- + tensile stress
 - compressive stress
 - X distance from the middle axis of the specimen along the width (mm)
 - 1 stress predicted from simple theory is 60,3 MPa tension or compression
 - 2 stress predicted from simple theory is 43,5 MPa tension or compression
 - 3 stress predicted from simple theory is 38,6 MPa tension or compression
 - 4 stress predicted from simple theory is 33,7 MPa tension or compression
 - 5 stress predicted from simple theory is 28,9 MPa tension or compression
 - 6 stress predicted from simple theory is 24,0 MPa tension or compression
 - 7 stress predicted from simple theory is 19,1 MPa tension or compression
 - 8 stress predicted from simple theory is 14,2 MPa tension or compression
 - 9 stress predicted from simple theory is 12,5 MPa tension or compression
 - 10 stress predicted from simple theory is 2,2 MPa tension or compression

Figure 4 — Variation in stress across the width of an 8,2 mm thick specimen of float glass at the middle of the span

If the exact origin of fracture is known, it is possible to obtain, by complex calculation, the precise local bending stress that has caused fracture of the specimen. If, however, the probability of flaws and the flaw distribution is considered, there is another approach which can be taken, depending upon whether the required bending strength is derived from all the bending test results (overall strength), or whether only those results from edge breaks are to be included (edge strength). It can be shown that the application of a factor, k , to the calculated bending stress can be used to modify the calculated bending stress to a “weighted average” of the bending stresses, called the effective bending strength, σ_{beff} . The factors are the following:

$k = k_s = 1,00$ when all the fractures are to be included;

$k = k_e$ when only edge fractures are to be included.

The value of k_e depends on the deflection of the specimen at its centre, and values for this parameter are given in ISO 1288-3.

6.3 Coaxial double ring test for small test surface areas

NOTE This test is specified in ISO 1288-5.

6.1.7 Elimination of edge effects

The special feature of the coaxial double ring bending test in accordance with ISO 1288-5 lies in the fact that only a circular shaped limited area of the surface of the specimen (not, however, its edges) is subjected to maximum stressing. In contrast to other bending tests (for example, ISO 1288-3) in which the edge of the specimen is subjected to the maximum stress, the procedure in accordance with ISO 1288-5 is suitable for exclusively subjecting surfaces (or different surface conditions) to bending stress. The effect of the specimen edge created by mechanical cold working is for, the most part, suppressed.

6.1.8 Analysis of the stress development

The advantages outlined in 6.1.1 and Reference [10] prompted the choice of the coaxial double ring bending test as a test method for determining the bending strength of glass. One of these advantages is the uniform, and directionally independent loading of the specimen with the loading ring, which means that the direction of possible surface defects has no influence on the result. However, this only applies up to limited deflections, y_0 , at the centre of the specimen.

Above this limit, excessive local stress may occur under the bearing edges of the loading ring, the magnitude of which increases as the load becomes greater. At the same time, tangential and radial stresses undergo variable modification, which is too complex for simple calculation. In this case, the stresses calculated from the linear bending theory are found to be excessively high (see 6.1).

For the ring size ratio, $r_2/r_1 = 5$, chosen here, the permissible deflection range is given approximately by $y_0/h < 1,0$. The minimum values for the thickness of specimens specified in ISO 1288-5 have been selected for bending stresses up to 600 MPa in such a way that, for elastic moduli of not less than 50 GPa, the relative deflections, y_0/h , in the centre of the specimen do not exceed 0,75. The stress differences in the loading ring region are then less than 2 %, according to Reference [11] and [12]. For the purposes of ISO 1288-5, the bending strength can be calculated from the test load using the formulae given in ISO 1288-5, provided that the ring and specimen dimensions and the values of minimum thickness of specimens are adhered to.

For this quasi-linear range of specimen loading, the following expression applies for the stresses in the surface of circular specimens bounded by the loading ring (see Reference [5]).

$$\sigma_{\text{rad}} = \sigma_{\text{T}} = \frac{3(1 + \mu)}{2\pi} \left[\frac{(1 - \mu) r_2^2 - r_1^2}{(1 + \mu) 2r_3^2} + \ln \frac{r_2}{r_1} \right] \frac{F}{h^2} \quad (1)$$

Assuming a constant ratio between the values of r_1 , r_2 and r_3 and a Poisson number, μ , for the specimen of 0,23, the formula used in ISO 1288-5, for a circular specimen, may be derived from the Formula (2):

$$\sigma_{\text{rad}} = \sigma_{\text{T}} = K_1 \frac{F}{h^2} \quad (2)$$

Table 2 shows the effect of Poisson number on K_1 .

Table 2 — Constant, K_1 , as a function of Poisson number, μ

Poisson number, μ	Constant, K_1 , for R30 and R45 rings	Error, %, on assuming $\mu = 0,23$	Constant, K_1 , for R60 and R105 rings	Error, %, on assuming $\mu = 0,23$
0,18	1,059	2,7	0,662	3,4
0,19	1,065	2,1	0,667	2,7
0,20	1,071	1,6	0,672	2,1
0,21	1,076	1,1	0,677	1,4
0,22	1,082	0,5	0,681	0,7
0,23	1,088	0,0	0,686	0,0
0,24	1,094	0,5	0,691	0,7
0,25	1,100	1,1	0,695	1,4
0,26	1,106	1,6	0,700	2,1

The Poisson number for soda lime silicate glass (ISO 16293-1) is given as 0,23. For square specimens, Formula (1) applies using the mean specimen radius, as follows:

$$r_{3m} = \frac{(1 + \sqrt{2}) L}{2} = 0,6L \quad (3)$$

Here, r_{3m} corresponds to the mean of the radii of the circles circumscribing and inscribing the square. This leads to constants, in ISO 1288-5, of $K_2 = 1,04$ for the R30 and R45 rings and $K_2 = 0,674$ for the R60 and R105 rings, for square specimens of soda lime silicate glass.

When testing using loading devices, R45 and R30, as specified in ISO 1288-5, the tangential tensile stress at the edge of the glass is about 30 % of the maximum tangential stress (= radial stress) within the loading ring. If this results in edge breaks, it is recommended to increase the specimen radius, r_3 , or side length, L , and hence, the projection of the specimen beyond the supporting ring. With a ratio $r_3/r_2 = 2$ or $L/2r_2 = 2$, the tangential stress at the edge of the sheet is definitely below 10 % of the maximum value (see Reference [10]), so that the possibility of edge breaks can be virtually excluded. In this case, however, constants K_1 and K_2 need to be calculated again from Formula (1).

In inter-laboratory tests, the calculation principle given here for square and circular specimens has led to satisfactory agreement of the bending strength values determined for both forms of specimen.

7 Range of application of the test methods

7.1 General limitations

The test methods specified in this part of ISO 1288 are not appropriate for the testing of laminated glass or insulating units.

7.2 Limitations to ISO 1288-2

This test method is applicable only to flat glass (see 3.1).

Patterned glass can be tested provided the maximum and minimum thicknesses do not deviate by more than 30 %, but not more than 2 mm, from the mean thickness.

7.3 Limitations to ISO 1288-3

This test method is applicable only to flat glass (see 3.1).

Patterned glass can be tested without limitations.

This test is not appropriate for products which are expected to have deflections greater than 25 times their thickness.

7.4 Limitations to ISO 1288-4

This test method is applicable only to channel shaped glass.

7.5 Limitations to ISO 1288-5

This test method is applicable only to flat glass (see 3.1).

Patterned glass shall not be tested by this method.

8 Calibration of the testing machines

The testing machines used according to ISO 1288-2, ISO 1288-3, ISO 1288-4 and ISO 1288-5 shall have been calibrated by the user within three months before a test.

For the purposes of calibration of a testing machine, the glass specimen can be replaced by a metal (e.g. steel) plate of appropriate thickness.

To perform the calibration of the force measuring instrument, an officially calibrated force gauge with independent instrument reading, accuracy ± 1 %, shall be placed in series with the force measuring instrument of the testing machine.

To perform the calibration of the gas pressure measuring instrument, an officially calibrated pressure gauge with independent instrument reading, accuracy ± 1 %, shall be placed in parallel to the pressure measuring instrument of the testing machine.

The force or pressure shall be increased in at least five approximately equidistant steps covering the ranges of measurement. At every step, the instrument readings from the testing machine and that from the officially calibrated gauge shall be recorded. Both readings shall coincide within ± 1 % over the whole measuring range. If the differences between the two readings exceed ± 1 %, the measuring instrument of the testing machine shall be adjusted accordingly.

Only officially calibrated gauges shall be used for calibration. They shall be officially recalibrated every three years.

9 Recommendations for safe use of test equipment

Where material testing machines are in use, both the user and others may be exposed to hazards arising from the design of the machine and the behaviour of the specimen.

Material testing machines should be so designed that the user and others are protected, as far as possible, against hazards of all kinds, when the machine is used in the proper manner.

The tests methods specified in this part of ISO 1288 are designed to break glass under high stresses, so there is an obvious hazard from the broken glass. Appropriate precautions shall be taken during the testing of glass specimens to avoid the particular hazards to both operators and observers from broken glass. These could include the following:

- providing appropriate protective clothing, e.g. safety spectacles and gloves, especially for the handling of glass specimens and broken glass fragments;
- applying an adhesive film to the surface of the glass, which is not being subjected to bending tension, to ensure that all the broken pieces are held together after breakage;
- using transparent safety screens between observers and/or operators and specimen.

If it is not possible, because of

- the particular nature of the test process, or
- different and unpredictable behaviour of the specimen during the test process,

to achieve safe handling of the testing machine by design measures or by additional safety features, the testing machine should be restricted to use by a limited group of persons who are able to assess the possible risks.

Bibliography

- [1] WIEDERHORN S.M. Environmental Stress Corrosion Cracking of Glass. National Bureau of Standards, Washington D.C. Corros. Fatigue: Chem. Mech. Microstruct, 1971, pp. 731–42.
- [2] KERKHOF F. *Bruchvorgänge in Gläsern (Fracture Processes in Glass)*. Deutsche Glastechnische Gesellschaft, Frankfurt/Main 1970, p. 209 ff
- [3] SHAND E.B. Glass Engineering Hand Book. McGraw-Hill Book Comp, New York, 1958
- [4] SCHEIDLER H. *Verletzlichkeit und technische Festigkeit von Glas (Vulnerability and technological strength of glass)*. Glastechn. Ber. 50 (1977), No. 9, pp.214-222.
- [5] WOELK H., & ELSENHEIMER K. *Biegebruchspannung von Floatglas und thermisch vorgespanntem Floatglas (Ultimate bending stress of float glass and thermally prestressed float glass)*. Glastechn. Ber. 52 (1979), No. 1, pp.14-24.
- [6] SCHMITT R.W. *Die Doppelringmethode mit überlagertem Gasdruck als Prüfverfahren zur Bestimmung der Bruchspannungen von grossformatigen ebenen Glasplatten kleiner Dicke (The double ring method with super-imposed gas pressure as a testing procedure for determining the stress at break of large-sized flat sheets of glass of a small thickness)*. Diplomarbeit am Institut für Maschinenelemente und Maschinengestaltung (Thesis at the Institute for Machinery Components and Machine Design), Leiter: Professor Dr. H. Peecken, RWTH Aachen, 1982
- [7] SCHMITT R. W. *Entwicklung eines Prüfverfahrens zur Ermittlung der Biegefestigkeit von Glas und Aspekte der statistischen Behandlung der gewonnenen Messwerte (Development of a testing procedure for the determination of the bending strength of glass and some aspects of the statistical evaluation of test results)*. Diss. RWTH Aachen, 1987
- [8] BLANK K., & SCHMITT R.W. Troeder, Chr., *Ein modifiziertes Doppelringverfahren zur Bestimmung der Biegezugfestigkeit grossformatiger Glasplatten (A modified coaxial-ring-bending method for testing the bending strength of large glass plates)*. Glastechn. Ber. 56K (1983), volume 1, pp.414-419 (Vortrag auf dem 13 Internationalen Glas-Kongress, Hamburg 1983)
- [9] BLANK K., DURKOP D., DURCHHOLZ M., GRUTERS H., HELMICH G, SENGER W. *Strength tests of flat glass by means of four point bending*. Glastechnische Berichte 67 (1994) No. 1, pp.9-15
- [10] SCHMITT R. W., BLANK K., SCHONBRUNN G. *Experimentelle Spannungsanalyse zum Doppelringverfahren (Experimental stress analysis for the double ring method)*. Sprechsaal 116 (1983), No. 5, pp.397-405 and printing error correction in Sprechsaal 116 (1983), No. 8, p669.
- [11] KAO R., PERRONE N., CAPPS W. *Large-Deflection Solution of the Coaxial-Ring-Circular-Glass-Plate Flexure Problem*. J. Am. Ceram. Soc 54 (1971), No. 11, pp.566-571.
- [12] FAYET A. *Détermination de la résistance mécanique des plaques circulaires des verres minces à l'aide d'un test de flexion par anneaux concentriques*. Revue Francaise de Mécanique (1971) No.37, pp.53-75
- [13] ISO 16293-2,¹⁾ *Glass in building — Basic soda lime silicate glass products — Part 2: Float glass*
- [14] ISO 16293-3,²⁾ *Glass in building — Basic soda lime silicate glass products — Part 3: Polished wired glass*
- [15] ISO 16293-4,³⁾ *Glass in building — Basic soda lime silicate glass products — Part 4: Wired patterned glass*

1) To be published.

2) To be published.

3) To be published.

[16] ISO 16293-5,⁴⁾*Glass in building — Basic soda lime silicate glass products — Part 5: Patterned glass*

4) To be published.

