

# International Standard 4385

K-05-01

---

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

---

## Plain bearings — Compression testing of metallic bearing materials

*Paliers lisses — Essai de compression des matériaux antifriction*

First edition — 1981-12-15

UDC 669.018.24 : 620.173

Ref. No. ISO 4385-1981 (E)

Descriptors : bearings, plain bearings, bearing alloys, tests, mechanical tests, compression tests, definitions, test results.

Price based on 4 pages

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 4385 was developed by Technical Committee ISO/TC 123, *Plain bearings*, and was circulated to the member bodies in January 1979.

It has been approved by the member bodies of the following countries :

Australia	India	Romania
Bulgaria	Italy	South Africa, Rep. of
Chile	Korea, Rep. of	Spain
Czechoslovakia	Libyan Arab Jamahiriya	Sweden
Egypt, Arab Rep. of	Netherlands	United Kingdom
France	New Zealand	USA
Germany, F.R.	Poland	USSR

No member body expressed disapproval of the document.

# Plain bearings — Compression testing of metallic bearing materials

## 1 Scope and field of application

This International Standard specifies a method for the compression testing of metallic bearing materials.

Compression testing within the meaning of this International Standard serves for the determination of the behaviour of metallic materials under uniaxial compression loading which is uniformly distributed over the cross-section. For this purpose, a cylindrical specimen with an original cross-section  $S_0$  is subjected to compression which is slowly and continuously increased, and the compressive force used is measured.

## 2 Definitions

### 2.1 compressive stress (nominal compressive stress)

$\sigma_d$ : At any moment of the compression test, the quotient of the compressive force  $F$  and the original cross-section  $S_0$ :

$$\sigma_d = \frac{F}{S_0} \quad \dots (1)$$

**2.2 compressive strength  $\sigma_{dB}$** : Quotient of the compressive force  $F_B$  (which is measured when the first crack or fracture occurs) and the original cross-section  $S_0$ :

$$\sigma_{dB} = \frac{F_B}{S_0} \quad \dots (2)$$

If no crack occurs, the test is continued until a given total compression  $\epsilon_{dt}$ . Then the compressive strength  $\sigma_{d50}$  is the quotient of the compressive force  $F$  corresponding to this total compression and the original cross-section  $S_0$ ; for example, at a given total compression of 50 %:

$$\sigma_{d50} = \frac{F_{50}}{S_0} \quad \dots (3)$$

NOTE — The given total compression shall not be exceeded: 50 %.

**2.3 compressive limits**: Quotients of the compressive forces  $F$  corresponding to a small ( $\leq 2$  %) non-proportional compression  $\epsilon_{d0}$  or to a permanent compression  $\epsilon_{dt}$ , and the original cross-section  $S_0$ .

Specially stipulated compression limits are:

**2.3.1 compression limit 0,2 %,  $\sigma_{d0,2}$** : Limit corresponding to a non-proportional or permanent compression of 0,2 %:

$$\sigma_{d0,2} = \frac{F_{0,2}}{S_0} \quad \dots (4)$$

In the case of metallic materials with a continuous compressive stress-compressive curve, the 0,2 % compression limit is determined instead of the compressive yield point (see 2.4).

**2.3.2 compression limit 2 %,  $\sigma_{d2}$** : Limit corresponding to a non-proportional or permanent compression of 2 %.

$$\sigma_{d2} = \frac{F_2}{S_0} \quad \dots (5)$$

**2.4 natural compressive yield point  $\sigma_{dF}$** : Quotient of the compressive force  $F_F$  (at which the compressive stress-compression curve begins to increase unsteadily simultaneously with the appearance of a noticeable permanent compression) and the original cross-section  $S_0$ .

$$\sigma_{dF} = \frac{F_F}{S_0} \quad \dots (6)$$

**2.5 differential length  $\Delta L_d$** : At any moment of the test, the difference between the original gauge length  $L_0$  and the actual gauge length  $L$ .


$$\Delta L_d = L_0 - L \quad \dots (7)$$

If  $\Delta L_d$  is divided by the original gauge length  $L_0$ , the result is the compression  $\epsilon_d$  which is expressed as a percentage.

$$\epsilon_d = \frac{\Delta L_d}{L_0} \times 100 \quad \dots (8)$$


Depending on whether it is a question of elastic, non-proportional, permanent or total compression, the symbols  $\epsilon_{de}$ ,  $\epsilon_{dpr}$ ,  $\epsilon_{dt}$  or  $\epsilon_{dt}$  respectively are used.

This document is a  
**POUR**

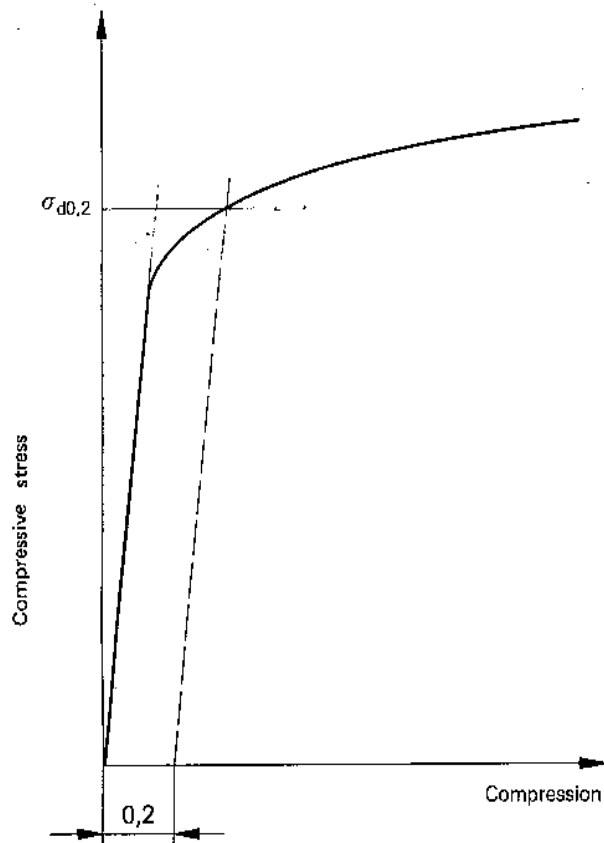

NOTE — Graph not according to scale.

Figure 1 — Determination of the 0,2 % compressive limit  $\sigma_{d0,2}$  with the help of a line parallel to Hooke's straight line at a distance of 0,2 % compression

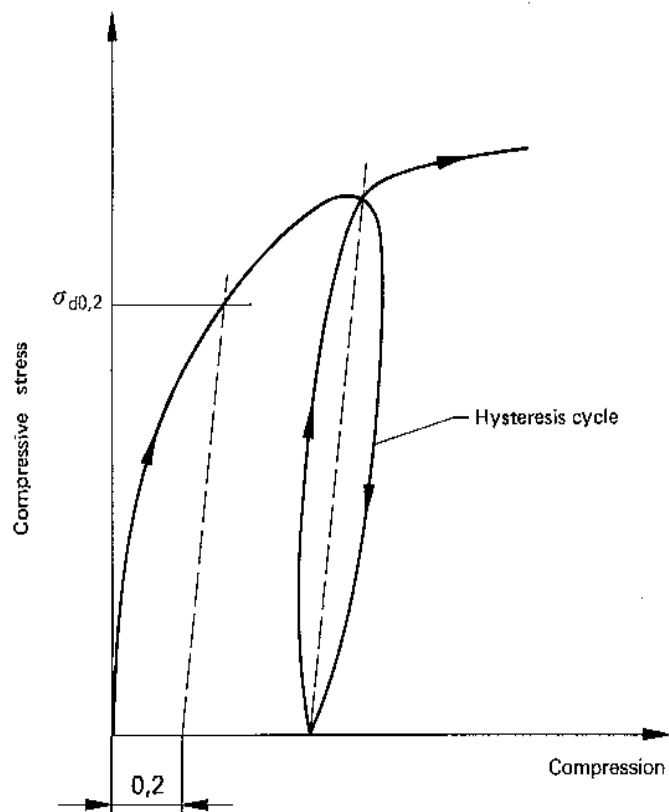

NOTE — Graph not according to scale.

Figure 2 — Determination of the 0,2 % compressive limit  $\sigma_{d0,2}$  with the help of a line parallel to the centre line of the hysteresis cycle at a distance of 0,2 % compression

This document is now  
**POOBLIC**

### 5.3 Determination of the compressive limit by gradually increased force

Load the specimen with a gradually increased force for 30 s. After removal of the force or after reduction of the force to a preforce, measure the permanent differential length. Draw the compressive stress-compression curve on the basis of these measured values. The respective compressive limits are taken from this curve.

The permanent differential length can be measured :

- a) as the change in height of the specimen after removal of the force and removal of the specimen from the compression testing machine;
- b) by a differential length measuring device fixed to the specimen after reduction of the force to preforce.

The differential length measuring device shall be accurate to within 0,01 mm.

NOTE — As concerns 5.3 a) above, the specimen must be centered according to clause 5 when it is reinstalled in the compression testing machine.

## 6 Test report

The test report shall include the following information :

- a) reference to this International Standard;
- b) method of sampling and manufacturing of the specimen (for example chill casting ; chill and casting temperature);
- c) dimensions of the specimen;
- d) method of measuring the differential length and, if necessary, the method of determination of the compressive limit in accordance with the note to 5.2;
- e) lubricant used for greasing the pressure plates;
- f) test temperature to an accuracy of 1 °C;
- g) strength values  $\sigma_{dB}$ ,  $\sigma_{d50}$ ,  $\sigma_{d0,2}$ ,  $\sigma_{d2}$ ,  $\sigma_{dF}$ , in newtons per square millimetre, rounded off to the nearest whole;
- h) deformation characteristic values  $\epsilon_{dB}$ ,  $\psi_{dB}$  expressed as a percentage, rounded off to the nearest whole number.

This document is now  
**POOBLIC**

This document is now  
**POOBLIC**