
**Iron ores for blast furnace feedstocks —
Determination of the reducibility by the
rate of reduction index**

*Minerais de fer pour charges de hauts fourneaux — Détermination de la
réductibilité à partir de la vitesse de réduction*



Reference number
ISO 4695:2007(E)

© ISO 2007

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Sampling, sample preparation and preparation of test portions	2
6 Apparatus	2
7 Test conditions	3
8 Procedure	4
9 Expression of results	5
10 Test report	6
11 Verification	7
Annex A (normative) Flowsheet of the procedure for the acceptance of test results	10
Annex B (informative) Derivation of equation for reducibility	11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 4695 was prepared by Technical Committee ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 3, *Physical testing*.

This third edition cancels and replaces the second edition (ISO 4695:1995), which has been revised to homogenise with other physical test standards.

Introduction

This International Standard concerns one of a number of physical test methods that have been developed to measure various physical parameters and to evaluate the behaviour of iron ores, including reducibility, disintegration, crushing strength, apparent density, etc. This method was developed to provide a uniform procedure, validated by collaborative testing, to facilitate comparisons of tests made in different laboratories.

The results of this test should be considered in conjunction with other tests used to evaluate the quality of iron ores as feedstocks for blast furnace processes.

This International Standard may be used to provide test results as part of a production quality control system, as a basis of a contract, or as part of a research project.

Iron ores for blast furnace feedstocks — Determination of the reducibility by the rate of reduction index

CAUTION — This International Standard may involve hazardous materials, operations and equipment. This standard does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

1 Scope

This International Standard specifies a method to provide a relative measure for evaluating the extent to and ease with which oxygen can be removed from iron ores, when reduced under conditions resembling those prevailing in the reduction zone of a blast furnace.

This International Standard is applicable to lump ores, sinters and hot-bonded pellets.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2597-1:2006, *Iron ores — Determination of total iron content — Part 1: Titrimetric method after tin(II) chloride reduction*

ISO 3082:2000¹⁾, *Iron ores — Sampling and sample preparation procedures*

ISO 9035:1989, *Iron ores — Determination of acid-soluble iron(II) content — Titrimetric method*

ISO 9507:1990, *Iron ores — Determination of total iron content — Titanium(III) chloride reduction methods*

ISO 11323:2002, *Iron ore and direct reduced iron — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

4 Principle

The test portion is isothermally reduced in a fixed bed, at 950 °C, using a reducing gas consisting of CO and N₂, and is weighed at specified time intervals until its degree of reduction reaches 65 %. The rate of reduction is calculated at the oxygen/iron ratio of 0,9.

1) Under revision, to incorporate ISO 10836, *Iron ores — Method of sampling and sample preparation for physical testing*.

5 Sampling, sample preparation and preparation of test portions

5.1 Sampling and sample preparation

Sampling of a lot and preparation of a test sample shall be in accordance with ISO 3082.

The size range for pellets, sinters and lump ores shall be – 12,5 mm + 10,0 mm.

A test sample of at least 2,5 kg, on a dry basis, of the sized material shall be obtained.

Oven-dry the test sample to constant mass at $105\text{ °C} \pm 5\text{ °C}$ and cool it to room temperature before preparation of the test portions.

NOTE Constant mass is achieved when the difference in mass between two subsequent measurements becomes less than 0,05 % of the initial mass of the test sample.

5.2 Preparation of test portions

Collect each test portion by taking ore particles at random.

NOTE Manual methods of division recommended in ISO 3082, such as riffing, can be applied to obtain the test portions.

At least 5 test portions, each of approximately 500 g (\pm the mass of 1 particle) shall be prepared from the test sample: 4 test portions for testing and 1 for chemical analysis.

Weigh the test portions to the nearest 1 g and register the mass of each test portion on its recipient label.

6 Apparatus

6.1 General

The test apparatus shall comprise:

- a) ordinary laboratory equipment, such as an oven, hand tools, time-control device and safety equipment;
- b) a reduction-tube assembly;
- c) a furnace, equipped with a balance for permitting the mass loss of the test portion to be read at any time during the test;
- d) a system to supply the gases and regulate the flow rates;
- e) a weighing device.

Figure 1 shows an example of the test apparatus.

6.2 Reduction tube, made of non-scaling, heat-resistant metal to withstand temperatures higher than 950 °C and resistant to deformation. The internal diameter shall be $75\text{ mm} \pm 1\text{ mm}$. A removable perforated plate, made of non-scaling, heat-resistant metal to withstand temperatures higher than 950 °C , shall be mounted in the reduction tube to support the test portion and to ensure uniform gas flow through it. The perforated plate shall be 4 mm thick, with its diameter 1 mm less than the tube internal diameter. The holes in the plate shall be 2 mm to 3 mm in diameter, at a pitch center distance of 4 mm to 5 mm.

Figure 2 shows an example of a reduction tube.

6.3 Furnace, having a heating capacity and temperature control able to maintain the entire test portion, as well as the gas entering the bed, at $950\text{ °C} \pm 10\text{ °C}$.

6.4 Balance, capable of weighing the reduction-tube assembly, including the test portion, to an accuracy of 1 g. The balance shall have an appropriate device to suspend or support the reduction-tube assembly.

6.5 Gas-supply system, capable of supplying the gases and regulating gas flow rates. It shall be ensured that a frictionless connection between the gas-supply system and the reduction tube does not affect the weight-loss determination during reduction.

6.6 Weighing device, capable of weighing the test sample and test portions to an accuracy of 1 g.

7 Test conditions

7.1 General

Volumes and flow rates of gases are as measured at a reference temperature of 0 °C and at a reference atmospheric pressure of 101,325 kPa (1,013 25 bar).

7.2 Reducing gas

7.2.1 Composition

The reducing gas shall consist of:

CO	40,0 % ± 0,5 % (volume fraction)
N ₂	60,0 % ± 0,5 % (volume fraction)

7.2.2 Purity

Impurities in the reducing gas shall not exceed:

H ₂	0,2 % (volume fraction)
CO ₂	0,2 % (volume fraction)
O ₂	0,1 % (volume fraction)
H ₂ O	0,2 % (volume fraction)

7.2.3 Flow rate

The flow rate of the reducing gas, during the entire reducing period, shall be maintained at 50 L/min ± 0,5 L/min.

7.3 Heating and cooling gas

Nitrogen (N₂) shall be used as the heating and cooling gas. Impurities shall not exceed 0,1 % (volume fraction).

The flow rate of N₂ shall be maintained at 25 L/min until the test portion reaches 950 °C, and at 50 L/min during the temperature-equilibration period.

7.4 Temperature of the test portion

The temperature of the entire test portion shall be maintained at 950 °C ± 10 °C during the entire reducing period and, as such, the reducing gas shall be preheated before entering the test portion.

8 Procedure

8.1 Number of determinations for the test

Carry out the test as many times as required by the procedure in Annex A.

8.2 Chemical analysis

Take, at random, one of the test portions prepared in 5.2 and use it for the determination of the iron(II) oxide content (w_1) in accordance with ISO 9035 and the total iron content (w_2) in accordance with ISO 2597-1 or ISO 9507.

8.3 Reduction

Take, at random, one test portion prepared in 5.2 and record its mass (m_0). Place it in the reduction tube (6.2) and level its surface.

NOTE In order to achieve a more uniform gas flow, a double-layer bed of porcelain balls sized between 10,0 mm and 12,5 mm can be placed between the perforated plate and the test portion.

Close the top of the reduction tube. Connect the thermocouple, ensuring that its tip is in the centre of the test portion.

Insert the reduction tube into the furnace (6.3) and suspend or support it centrally from the balance (6.4) ensuring that there is no contact with the furnace wall or heating elements.

Connect the gas-supply system (6.5).

Pass a flow of N_2 through the test portion at a rate of 25 L/min and commence the heating. When the temperature of the test portion approaches 950 °C, increase the flow rate to 50 L/min. Continue heating while maintaining the flow of N_2 , until the mass of the test portion is constant and the temperature is constant at 950 °C ± 10 °C for 15 min.

DANGER — Carbon monoxide and the reducing gas, which contains carbon monoxide, are toxic and therefore hazardous. Testing shall be carried out in a well ventilated area or under a hood. Precautions should be taken for the safety of the operator according to the safety codes of each country.

Record the mass of the test portion (m_1) and immediately introduce the reducing gas at a flow rate of 50 L/min ± 0,5 L/min to replace the N_2 . Record the mass of the test portion (m_t) at least every 3 min for the first 15 min and thereafter at 10 min intervals.

Calculate the degree of reduction, R_t , relative to the iron(III) state, after t min, as follows:

$$R_t = \left(\frac{0,111 w_1}{0,430 w_2} + \frac{m_1 - m_t}{m_0 \times 0,430 w_2} \times 100 \right) \times 100$$

where

m_0 is the mass, in grams, of the test portion;

m_1 is the mass, in grams, of the test portion immediately before starting the reduction;

m_t is the mass, in grams, of the test portion, after reduction time t ;

w_1 is the iron(II) oxide content, as a percentage by mass, of the test sample prior to the test, determined in accordance with ISO 9035; it is calculated from the iron(II) content by multiplying it by the oxide conversion factor $\text{FeO/Fe(II)} = 1,286$;

w_2 is the total iron content, as a percentage by mass, of the test portion prior to the test, determined in accordance with ISO 2597-1 or ISO 9507.

When the degree of reduction reaches 65 %, turn off the power and stop the flow of the reducing gas. If, after 4 h, 65 % of oxygen loss has not been achieved, the reduction may be stopped. Introduce N_2 at a flow rate of 5 L/min for 5 min or more, to purge the reducing gas from the tube.

9 Expression of results

9.1 Calculation of the reducibility index $\left(\frac{dR}{dt}\right)_{(\text{O/Fe} = 0,9)}$

Prepare the reduction curve by plotting the degree of reduction R_t against time t .

Read off, from the reduction curve, the time, in minutes, to attain degrees of reduction of 30 % and 60 %.

The reducibility index, expressed as the rate of reduction at the atomic ratio of O/Fe of 0,9²⁾ in %/min, is calculated from the following equation³⁾:

$$\frac{dR}{dt} (\text{O/Fe} = 0,9) = \frac{33,6}{t_{60} - t_{30}}$$

where

t_{30} is the time, in minutes, to attain a degree of reduction of 30 %;

t_{60} is the time, in minutes, to attain a degree of reduction of 60 %;

33,6 is a constant.

Record the result to 2 decimal places.

NOTE If a degree of reduction of 60 % is not attained in the test, lower values may be accommodated by the following equation:

$$\frac{dR}{dt} (\text{O/Fe} = 0,9) = \frac{k}{t_y - t_{30}}$$

where

t_y is the time, in minutes, to attain a degree of reduction of y %;

k is a constant depending on y .

If $y = 50$ % then the value of $k = 20,2$; if $y = 55$ % then the value of $k = 26,5$.

2) The atomic ratio O/Fe = 0,9 means a 40 % degree of reduction.

3) The derivation of the equation is given in Annex B.

9.2 Repeatability and acceptance of test results

Follow the procedure in Annex A by using the repeatability value given in Table 1. The results shall be reported to two decimal places.

Table 1 — Repeatability (*r*)

Type of iron ore	<i>r</i> %/min
Pellets	$0,07 \times \overline{dR/dt}$
Sinter	0,17
Lump ore	0,10
NOTE $\overline{dR/dt}$ is the mean value of dR/dt results.	

10 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 4695:2007;
- b) all details necessary for the identification of the sample;
- c) the name and address of the test laboratory;
- d) the date of the test;
- e) the date of the test report;
- f) the signature of the person responsible for the test;
- g) details of any operation and any test conditions not specified in this International Standard or regarded as optional, as well as any incident which may have had an influence on the results;
- h) the reducibility index, dR/dt (O/Fe = 0,9);
- i) the total iron and iron(II) contents of the test portion before reduction;
- j) the reduction curve, if specified at the time of ordering.

11 Verification


Regular checking of the apparatus is essential to ensure test result reliability. The frequency of checking is a matter for each laboratory to determine.

The conditions of the following items shall be checked:

- weighing device;
- reduction tube;
- temperature control and measurement devices;
- balance;
- gas flow meters;
- purity of gases;
- recording system;
- time-control device.

It is recommended that internal reference material be prepared and used periodically to check test repeatability.

Appropriate records of verification activities shall be maintained.

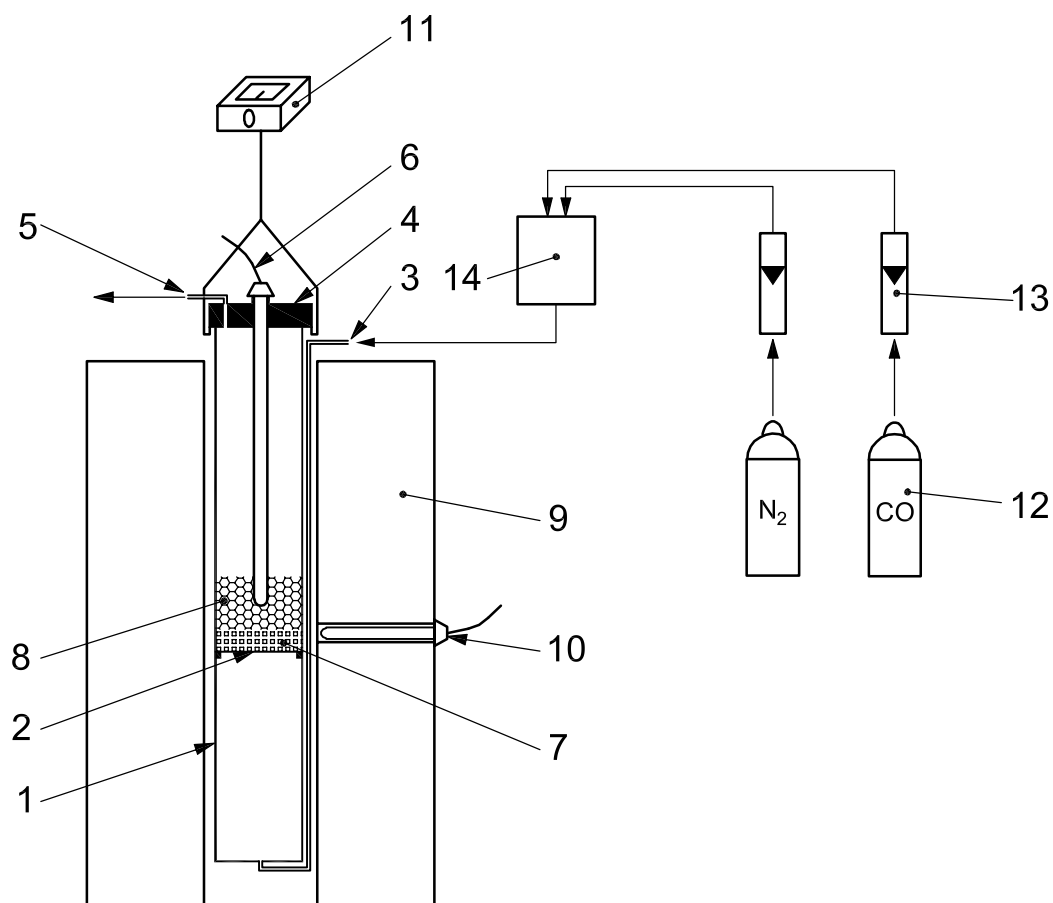

Key

Reduction tube

- 1 reduction tube
- 2 perforated plate
- 3 gas inlet
- 4 lid
- 5 gas outlet
- 6 thermocouple for measuring the reduction temperature
- 7 porcelain-ball layer
- 8 test portion

Furnace


- 9 electrically heated furnace
- 10 thermocouple for temperature regulation of furnace
- 11 balance

Gas-supply system

- 12 gas cylinder
- 13 gas flow meter
- 14 mixing vessel

Figure 1 — Example of test apparatus (schematic diagram)

Dimensions in millimetres

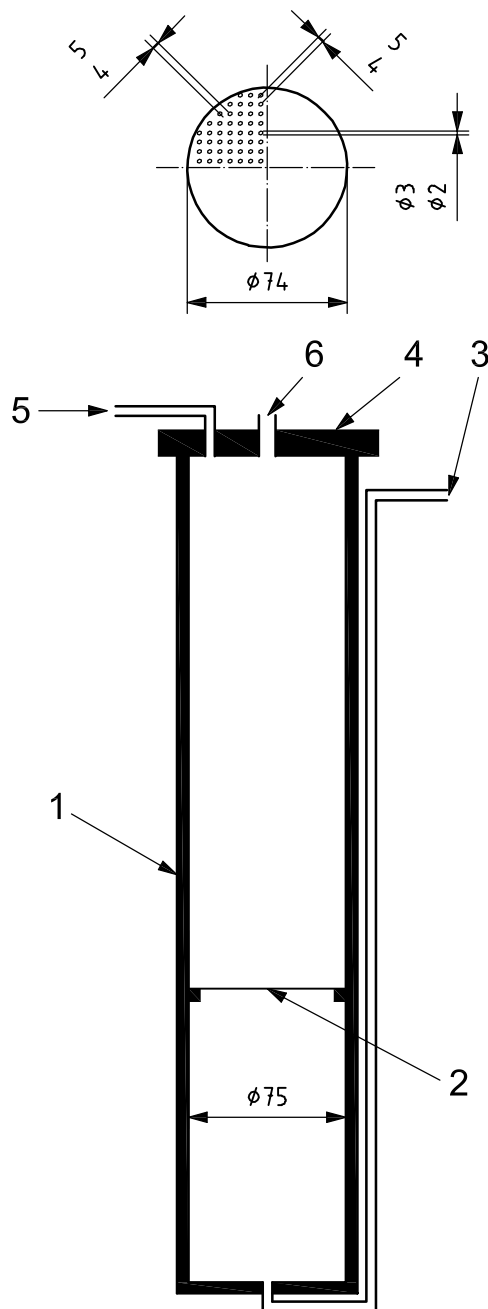

Key


- 1 reduction tube
- 2 perforated plate
- 3 opening for gas inlet
- 4 lid
- 5 opening for gas outlet
- 6 opening for thermocouple insertion

NOTE Dimensions not specified in the apparatus clause are shown for information only.

Figure 2 — Example of reduction tube (schematic diagram)

Annex A (normative)

Flowsheet of the procedure for the acceptance of test results

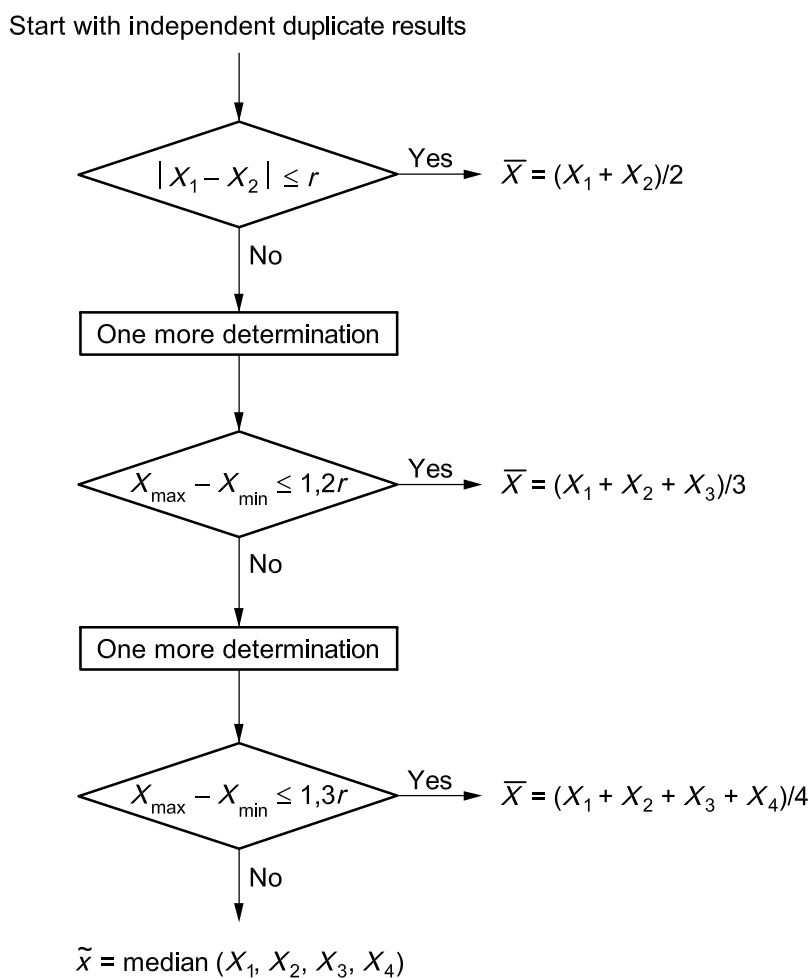

r: see Table 1

Annex B (informative)

Derivation of equation for reducibility

The “degree of reduction” describes the extent to which oxygen has been removed from iron oxides, and is defined generally as shown below:

$$\text{Degree of reduction} = \frac{\text{Oxygen removed from iron oxide}}{\text{Original oxygen combined with iron}} \quad (\text{B.1})$$

The equation in 9.1 is derived on the assumption that all oxygen combined with iron is present in the form of hematite (Fe_2O_3) whereas, for most iron ore materials, some magnetite (Fe_3O_4), wustite (FeO), and metallic iron is also present. Therefore, the degree of reduction is estimated from the loss in mass of the test portion during reduction plus the difference between the theoretical oxygen content of the original sample, based on all iron being associated as Fe_2O_3 , and the true oxygen content based on actual amounts of Fe_2O_3 , Fe_3O_4 and FeO in the sample.

$$R_t = \frac{m_0 w_1 \times \frac{8}{71,85}}{m_0 w_2 \times \frac{48}{111,7}} \times 100 + \frac{m_1 - m_t}{m_0 \times \frac{w_2}{100} \times \frac{48}{111,7}} \times 100 \quad (\text{B.2})$$

The equation in 9.1 is derived on the assumption that the rate of oxygen removed from iron ore is a first-order reaction with respect to the prevailing oxygen concentration.

$$-\frac{dO}{dt} = k \times O_v \quad (\text{B.3})$$

$$dO = -dR \times \frac{O_{\text{total}}}{100} \quad (\text{B.4})$$

$$\frac{O_v}{O_{\text{total}}} = 1 - \frac{R}{100} \quad (\text{B.5})$$

where

O_v is the prevailing oxygen content;

O_{total} is the total oxygen combined with iron (as Fe_2O_3);

R is the degree of reduction.

From Equations (B.3), (B.4) and (B.5), the rate of reduction is derived:

$$\frac{dR}{dt} = k \times \left(1 - \frac{R}{100}\right) \times 100 \quad (\text{B.6})$$

Integration of Equation (B.6) gives

$$\log_{10}\left(1 - \frac{R}{100}\right) = -0,434 kt + C$$

where C is a constant.

For R between 30 % and 60 %:

$$k = \frac{-\log_{10}(1 - 60/100) + \log_{10}(1 - 30/100)}{0,434 (t_{60} - t_{30})} = \frac{0,56}{t_{60} - t_{30}} \quad (\text{B.7})$$

In the case of hematite, the oxygen/iron ratio of 0,9 has the same meaning as $R = 40$ %. By substituting $R = 40$ % and Equation (B.7) into Equation (B.6), the value of dR/dt (at $O/Fe = 0,9$) is obtained:

$$\frac{dR}{dt}(O/Fe = 0,9) = \frac{33,6}{t_{60} - t_{30}}$$

www.iso.org

© ISO 2007. All rights reserved.

ICS 73.060.10

Price based on 12 pages