

---

---

**Rubber- or plastics-coated fabrics —  
Determination of abrasion resistance —**

**Part 2:  
Martindale abrader**

*Supports textiles revêtus de caoutchouc ou de plastique —  
Détermination de la résistance à l'usure —*

*Partie 2: Appareil d'essai d'abrasion Martindale*



Reference number  
ISO 5470-2:2003(E)

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

Foreword .....	iv
1 Scope .....	1
2 Normative references .....	1
3 Principle .....	1
4 Apparatus and materials .....	2
5 Test specimens .....	4
6 Conditioning of specimens and wetting of abrasant .....	4
7 Procedure .....	5
8 Assessment of damage — Methods 1 and 2 .....	6
9 Test report .....	7

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 5470-2 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 4, *Products (other than hoses)*.

ISO 5470 consists of the following parts, under the general title *Rubber- or plastics-coated fabrics — Determination of abrasion resistance*:

- *Part 1: Taber abrader*
- *Part 2: Martindale abrader*

# Rubber- or plastics-coated fabrics — Determination of abrasion resistance —

## Part 2: Martindale abrader

**WARNING** — Persons using this part of ISO 5470 should be familiar with normal laboratory practice. This part of ISO 5470 does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory conditions.

### 1 Scope

This part of ISO 5470 details two separate methods for determining the resistance of a material to wet and dry abrasion. It is applicable to the coated surface or surfaces of coated fabrics. If the abrasion behaviour of the uncoated surface of a coated fabric is to be determined, use the methods for uncoated textiles described in the various parts of ISO 12947.

### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2231:1989, *Rubber- or plastics-coated fabrics — Standard atmospheres for conditioning and testing*

ISO 2286-1:1998, *Rubber- or plastics-coated fabrics — Determination of roll characteristics — Part 1: Methods for determination of length, width and net mass*

ISO 12947-2:1998, *Textiles — Determination of the abrasion resistance of fabrics by the Martindale method — Part 2: Determination of specimen breakdown*

ISO 12947-3:1998, *Textiles — Determination of the abrasion resistance of fabrics by the Martindale method — Part 3: Determination of mass loss*

ISO 12947-4:1998, *Textiles — Determination of the abrasion resistance of fabrics by the Martindale method — Part 4: Assessment of appearance change*

### 3 Principle

This part of ISO 5470 details two different methods. In method 1, test specimens are clamped in a specimen holder and abraded using pieces of a selected abradant under constant pressure. A variant of this method consists of carrying out the method with a wet abradant. Method 2 reverses the position of the abradant and the specimen. In both cases, the relative movement between the abradant and the specimens forms a complex cyclic pattern (a Lissajous figure) which produces rubbing in all directions. The test is stopped either after a predetermined number of cycles (in which case the damage to each specimen is assessed) or when the specimen has reached a predetermined degree of abrasion (in which case the number of cycles is noted).

## 4 Apparatus and materials

**4.1 Abrasion machine**, with one or more test stations, each fitted with the items of equipment specified in 4.1.1 to 4.1.6.

**4.1.1 Circular specimen holder**, with a clamping ring which grips the specimen around its edge, leaving an exposed raised flat circular portion of area  $(645 \pm 5) \text{ mm}^2$ .

**4.1.2 Horizontal abradant table**, of sufficient size to incorporate a square central test area of side 88 mm. Typically, abradant tables are circular and have a diameter of at least 125 mm.

**4.1.3 Means of holding the exposed flat portion of the specimen holder (4.1.1) in contact with the abradant table (4.1.2)** whilst allowing the specimen holder to rotate freely in the plane of the abradant table.

**4.1.4 Means of producing relative movement between the specimen holder (4.1.1) and the abradant table (4.1.2)** which forms a Lissajous figure occupying an area of  $(60 \pm 1) \text{ mm} \times (60 \pm 1) \text{ mm}$  (see Figure 1). Each Lissajous figure requires 16 elliptical motions (revolutions) of the specimen holder, and the speed of operation of the tester shall be  $(48 \pm 4) \text{ revs/min}$ .

The parallelism of the abradant table (4.1.2) and the specimen holder (4.1.1) shall be maintained to within  $\pm 0,05 \text{ mm}$  throughout each Lissajous figure. A dial gauge fitted in place of the specimen holder can be used to verify the parallelism of the abradant table.

The circumferential parallelism of the holder (4.1.1) in contact with the abradant table shall be better than  $\pm 0,05 \text{ mm}$ . This can be verified by attempting to insert slip gauges of thickness less than 0,05 mm under the edges of the flat face of the specimen holder.

**4.1.5 Means of maintaining a constant pressure of  $(12 \pm 0,2) \text{ kPa}$  between the specimen holder (4.1.1) and the abradant table (4.1.2)**. This will be the case if the mass of the specimen holder and its associated fittings is  $(795 \pm 5) \text{ g}$ .

**4.1.6 Means of counting the number of abrasion cycles completed** in terms of revolutions (16 revs per cycle).

## 4.2 Reference abradant

### 4.2.1 General

Unless otherwise stated by mutual agreement between the interested parties, this shall be either a wool abradant fabric or a silicon carbide cloth. Results from tests carried out with different abradants are not considered to be comparable. When tests are carried out, by mutual agreement of all parties, using a non-standard abradant, a description of this abradant shall be included in the test report.

### 4.2.2 Wool abradant fabric

The properties of wool abradant fabric shall be as given in Table 1.

Table 1 — Properties of wool abrasant fabric

	Warp	Weft
Linear density of yarn, tex	R63 ± 4/2	R74 ± 4/2
Threads per millimetre	1,7 ± 0,1	1,3 ± 0,1
Singles "Z" twist, turns per metre	540 ± 20	500 ± 20
Two-fold "S" twist, turns per metre	450 ± 20	350 ± 20
Fibre diameter, µm	27,5 ± 2	29 ± 2
Minimum mass per unit area, g·m <sup>-2</sup>	195 ± 5	

The two faces of the wool abrasant fabric will not necessarily have the same abrasive characteristics, and when purchased from a supplier it shall be noted which face the supplier recommends for use. This is normally the slightly smoother face of the fabric. Stocks of the fabric shall be controlled to ensure that only this face is used in testing.

#### 4.2.3 Silicon carbide cloth

The properties of silicon carbide cloth shall be as given in Table 2.

Table 2 — Properties of silicon carbide cloth

Abrasive	Fused silicon carbide free from extraneous material
Backing	Cotton cloth of minimum breaking strength 961 N/50 mm width in the warp direction and 392 N/50 mm in the weft direction
Grade	P 180

**4.3 Flat weightpiece**, of suitable dimensions to place over the entire surface of the abrasant table to ensure that the abrasant fabric is held flat whilst it is clamped in position. The weightpiece shall apply a pressure of (2 ± 0,2) kPa.

**4.4 Cutting device**, such as a die cutter, of sufficient size to produce specimens that will be held firmly in the specimen holders (4.1.1). The exact size of the device will depend on the design of the clamping system of the specimen holder.

**4.5 Four pieces of wool felt**, mass per unit area 575 g·m<sup>-2</sup> to 800 g·m<sup>-2</sup>, and thickness 2,0 mm to 3,5 mm. Both sides of the felt may be used. The felt used in dry tests may be re-used either until both sides are discoloured or until the thickness has been reduced to less than 2,0 mm, but felt used in wet tests shall not be re-used.

**4.6 Polyurethane foam**, of thickness (3 ± 1) mm, density (30 ± 2) kg·m<sup>-3</sup> and indentation hardness (5,8 ± 0,8) kPa.

**4.7 Water-jet**: a rubber tube with one end restricted and the other attached to a cold-water tap at mains pressure is suitable.

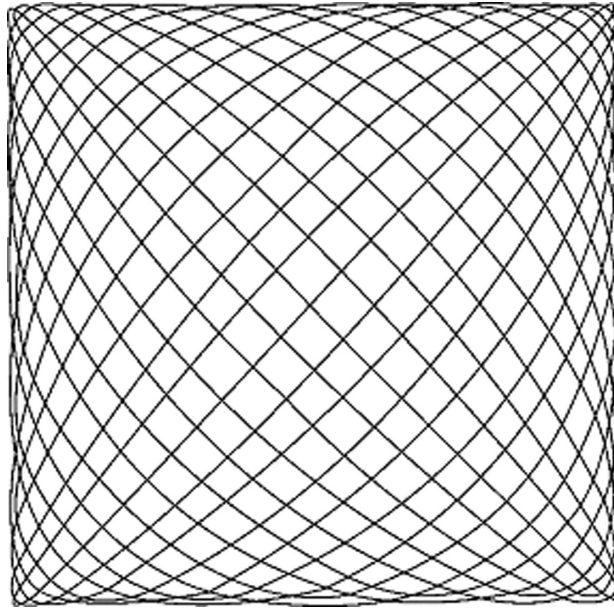


Figure 1 — Lissajous figure

## 5 Test specimens

### 5.1 Method 1 — Test specimens clamped in holders

**5.1.1** Using the cutting device (4.4), take at least four specimens, of sufficient size for them to be firmly held in the specimen holders (4.1.1), from non-adjacent areas within the usable width of the roll (as defined in ISO 2286-1). With double-coated fabrics, if both surfaces are to be tested, select another set of at least four specimens.

**5.1.2** If the material under test has an irregular embossing pattern or irregular printing pattern (patches), take specimens from positions selected so that each part of the pattern is tested. This may mean that more than four specimens are required.

**5.1.3** If the result of the test required by the relevant product specification is expressed in terms of mass loss, determine the mass of each specimen.

### 5.2 Method 2 — Test specimens on the table

**5.2.1** Cut at least four specimens, each measuring 125 mm × 125 mm, from non-adjacent areas within the usable width of the roll (as defined in ISO 2286-1).

**5.2.2** If the material under test has an irregular embossing pattern or irregular printing pattern (patches), take specimens from positions selected so that each part of the pattern is tested. This may mean that more than four specimens are required.

**5.2.3** If the result of the test required by the relevant product specification is expressed in terms of mass loss, determine the mass of each specimen.

## 6 Conditioning of specimens and wetting of abradant

**6.1** For dry tests, place the specimens in a conditioning atmosphere as specified in ISO 2231 for at least 16 h prior to testing and carry out the test in this atmosphere. Specimens for wet tests need not be conditioned prior to test.



**6.2** For wet tests, fully saturate the abrasant cloth (4.2) and wool felt (4.5) (method 1) or the specimen mounted on the abrasant table (method 2) by directing the water-jet (4.7) to and fro over their surfaces until complete saturation can be seen by a uniform darkening in colour.

## 7 Procedure

### 7.1 Method 1

**7.1.1** Place each specimen in a specimen holder (4.1.1) so that the specimen surface to be abraded is facing outwards. This surface shall not be that of the base fabric.

**7.1.2** If testing materials with a mass per unit area of less than  $500 \text{ g}\cdot\text{m}^{-2}$ , place a similar-size piece of polyurethane foam (4.6) in each of the specimen holders as backing for the specimen.

**7.1.3** Check that the specimen in its holder is not baggy, creased or distorted in any way.

**7.1.4** Place a piece of dry or wet felt (4.5) on the abrading table, depending on whether dry or wet test conditions are being used.

**7.1.5** Place a corresponding dry or wet piece of the abrasant fabric (4.2) over each piece of table felt with the test face uppermost.

**7.1.6** Place the weightpiece (4.3) on top of the abrasant fabric and clamp the abrasant in position so that it is free of wrinkles. When this has been achieved, remove the weightpiece.

**7.1.7** Repeat the procedure in 7.1.1 to 7.1.6 for any other test stations.

**7.1.8** Fit each filled specimen holder into the abrasion machine so that the specimen is resting on the abrasant.

**7.1.9** Apply a vertical downwards force to each specimen holder to provide the required pressure between the specimen and the abrasant (normally  $12 \text{ kPa} \pm 0,2 \text{ kPa}$ )

**7.1.10** Start the abrasion machine (4.1).

**7.1.11** At the numbers of revolutions indicated in Table 3, remove the specimens from their holders and inspect the specimens under bright indirect lighting for signs of damage. If possible, compare each specimen with a piece of the same material which has not been abraded and rate the observed alterations in accordance with Clause 8.

If the damage is rated to be “complete”, stop the test. If the predetermined number of revolutions is reached, note the rating of the damage and stop the test. If the damage has reached a predetermined limit, note the number of revolutions performed and stop the test. Otherwise, note the number of revolutions and the rating of the damage observed.

**7.1.12** Return each specimen to the same holder/abrasant table and restart the machine.

**7.1.13** Stop the machine at each inspection point and repeat the procedure given in 7.1.11.

**7.1.14** If appropriate, re-wet the abrasant fabric and wool felt or specimen at each wet test station at the points shown in Table 3, as follows. With the fabric and felt still clamped over the abrasant table, gradually pour up to 30 g of water on to the surface while lightly rubbing in the water with the finger tips. Stop pouring the water when it stops being absorbed and excess water is seen to accumulate on the surface. Place the weightpiece (4.3) on top of each abrasant for  $(10 \pm 2) \text{ s}$  and then remove.

**7.2 Method 2**

**7.2.1** Apply double-sided adhesive tape to the back of a specimen. Ensuring that no creases or wrinkles are introduced in the specimen, fix the specimen to the abradant table (4.1.2). Continue the same procedure for the remaining specimens.

**7.2.2** Into each specimen holder place a piece of abradant fabric (4.2) of sufficient size to allow it to be fixed firmly within the specimen clamps.

**7.2.3** Back the abradant cloth with a similar-size piece of polyurethane foam (4.6).

**7.2.4** Ensuring that the abradant and foam are not baggy, creased or distorted in any way, firmly clamp the assembly in place.

**7.2.5** Follow the same procedure as detailed in 7.1.10 to 7.1.14 for assessing the damage to the specimen on the abradant table.

**Table 3 — Recommended inspection and abradant re-wetting stages**

Number of revolutions	Inspect specimen	Re-wet abradant or specimen
1 600	Yes	No
3 200	Yes	No
6 400	Yes	Yes
12 800	Yes	Yes
25 600	Yes	Yes
38 400	No	Yes
51 200	Yes	No

**8 Assessment of damage — Methods 1 and 2**

To assess the amount of damage suffered by each specimen, rate them using the scale given in Table 4.

**Table 4 — Specimen damage rating scale**

<b>0</b>	None	No change.
<b>1</b>	Very slight	Modification of brightness. Printing (if any) shows no wear. No attack of top coat.
<b>2</b>	Slight	Change in brightness. Printing (if any) is partially or totally worn. Top coat not attacked, or only very superficially.
<b>3</b>	Moderate	Top coat attacked.
<b>4</b>	Severe	Top coat worn through and intermediate or foam layer attacked.
<b>5</b>	Complete	Base fabric appears.

If the test requires an assessment of the loss in mass of the specimens after a predetermined number of cycles, before the test condition the specimens and record the mass of each. After completing the required number of cycles, recondition the specimens for the same time as before the test and then re-weigh.

## 9 Test report

The test report shall include the following information:

- a) a reference to this part of ISO 5470 and the method used (i.e. method 1 or method 2, wet or dry);
- b) a description of the material under test;
- c) in the case of double-coated fabrics, the surface which was tested;
- d) details of the abrasant employed;
- e) details of any changes in the characteristics of the coated fabric, as required by the product specification;
- f) details of any deviations from the method specified;
- g) the pressure applied;
- h) the rating of the damage observed, in accordance with Clause 8, and the corresponding number of revolutions for each individual test specimen;
- i) if the test was stopped due to early complete wear, or because the specified number of revolutions or the specified abrasion damage was attained, indicate this.

---

---

**ICS 59.080.40**

Price based on 7 pages