

# INTERNATIONAL STANDARD

**ISO  
6441-1**

First edition  
1999-12-15

---

---

## **Paints and varnishes — Determination of micro-indentation hardness —**

### **Part 1: Knoop hardness by measurement of indentation length**

*Peintures et vernis — Détermination de la dureté par micro-indentation —  
Partie 1: Dureté Knoop par mesurage de la longueur d'indentation*

This material is reproduced from ISO documents under International Organization for Standardization (ISO) Copyright License Number HIS/CC/1996. Not for resale. No part of these ISO documents may be reproduced in any form, electronic retrieval system or otherwise, except as allowed in the copyright law of the country of use, or with the prior written consent of ISO (Case postale 56, 1211 Geneva 20, Switzerland, Fax +41 22 734 10 79), IHS or the ISO Licensor's members.



Reference number  
ISO 6441-1:1999(E)

© ISO 1999

**ISO 6441-1:1999(E)**

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 1999

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 734 10 79  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

**Contents**

	Page
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Principle .....</b>	<b>2</b>
<b>4 Required supplementary information .....</b>	<b>2</b>
<b>5 Apparatus .....</b>	<b>2</b>
<b>6 Sampling .....</b>	<b>4</b>
<b>7 Test panels .....</b>	<b>4</b>
<b>8 Calibration of the apparatus .....</b>	<b>5</b>
<b>9 Procedure .....</b>	<b>5</b>
<b>10 Expression of results .....</b>	<b>6</b>
<b>11 Precision .....</b>	<b>6</b>
<b>12 Test report .....</b>	<b>7</b>
<b>Annex A (normative) Required supplementary information .....</b>	<b>8</b>
<b>Bibliography .....</b>	<b>9</b>

## ISO 6441-1:1999(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 6441 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 6441-1 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

Together with the other parts (see below), it cancels and replaces ISO 6441:1984, which has been technically revised.

ISO 6441 consists of the following parts, under the general title *Paints and varnishes — Determination of micro-indentation hardness*:

- *Part 1: Knoop hardness by measurement of indentation length*
- *Part 2: Knoop hardness by measurement of indentation depth under load*
- *Part 3: Creep and visco-elastic properties and elastic modulus using the Vickers indenter*

Annex A forms a normative part of this part of ISO 6441.

## Introduction

This part of ISO 6441 is one of three dealing with the determination of the micro-indentation hardness of a dried film of paint, varnish or related product.

Part 1 specifies a method in which the hardness is calculated from the length, measured using a microscope, of a long diagonal of the indentation made by a Knoop indenter.

In this method, the indentation length is measured after the indenter has been removed.

Part 2 specifies a method in which the hardness is calculated from the depth, measured using an electronic technique, of the indentation made by a Knoop indenter.

In this method, the indentation depth is measured while the indenter is still under load.

Part 3 specifies a method in which the hardness, creep, visco-elasticity and modulus of elasticity are determined by measuring the depth of the indentation made by a Vickers indenter as a function of time.

Other methods have been standardized to measure the hardness of a paint film:

- ISO 1518, *Scratch test*.
- ISO 15184, *Determination of film hardness by pencil test*.
- ISO 2815, *Buchholz indentation test*.
- ISO 1522, *Pendulum damping test*.

The method chosen depends on the property which is to be measured. All these tests differ from each other technically, and in their accuracy. They also range from fairly simple to rather sophisticated, with the instruments prescribed in ISO 6441, part 1, part 2 and part 3, being of a sophisticated nature.

# Paints and varnishes — Determination of micro-indentation hardness —

## Part 1: Knoop hardness by measurement of indentation length

### 1 Scope

This part of ISO 6441 is one of a series of standards dealing with the sampling and testing of paints, varnishes and related products.

It specifies a method for determining the hardness of a dried film of a paint, varnish or related product by conducting an indentation test in which the indentation length is measured under zero-load conditions using a microscope.

It is applicable to single-coat and multicoat systems.

The result is expressed as a hardness value, in N/mm<sup>2</sup>, calculated from the indentation produced by a pyramidal indenter of a specified size and shape applied to the coating under specified conditions.

This method is similar to Test Method A of ASTM D 1474-92 (see reference [1] in the Bibliography).

### 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 6441. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 6441 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 1513:1992, *Paints and varnishes — Examination and preparation of samples for testing.*

ISO 1514:1993, *Paints and varnishes — Standard panels for testing.*

ISO 2808:1997, *Paints and varnishes — Determination of film thickness.*

ISO 3270:1984, *Paints and varnishes and their raw materials — Temperatures and humidities for conditioning and testing.*

ISO 15528:—<sup>1)</sup>, *Paints, varnishes and raw materials for paints and varnishes — Sampling.*

---

1) To be published. (Revision of ISO 842:1984 and ISO 1512:1991)

**ISO 6441-1:1999(E)****3 Principle**

The hardness of the surface of a dried paint or varnish film is measured, under specific conditions, with a pyramidal indenter (Knoop indenter) fitted to a micro-hardness tester.

The Knoop hardness is defined as the applied load divided by the projected area of the indentation in the plane of the surface of the paint film (see Figure 3).

During the test, the Knoop indenter is kept under a specified load for  $(18 \pm 0,5)$  s. After removal of the indenter, the length of the indentation is measured.

From this length, the area of the indentation in the plane of the surface of the paint film is calculated, and hence the Knoop hardness.

This method is applicable provided that the indentation depth does not exceed approximately 25 % of the coating thickness.

Exceeding this limit will result in the substrate influencing the penetration depth.

Further, the hardness value of the coating can be influenced (lowered) by a substrate material of much lower hardness than the coating.

**4 Required supplementary information**

For any particular application, the test method specified in this part of ISO 6441 needs to be completed by supplementary information. The items of supplementary information are given in annex A.

**5 Apparatus**

**5.1 Hardness tester**, including a Knoop indenter (5.1.1) and a microscope (5.1.2). This apparatus shall be capable of:

- Bringing the indenter into contact with the test surface at a specified speed, in accordance with the manufacturer's instructions, with negligible impact under a nearly zero load. Any impact by the indenter on the test surface will result in errors in readings and the calculated hardness will be too low.
- Progressively applying a selected load to the indenter and maintaining the load for  $(18 \pm 0,5)$  s.
- Removing the load and withdrawing the indenter from the test surface.
- Measuring the length of the indentation by a microscope.

**NOTE** Several types of (electronic) apparatus are available commercially and may be used, provided that they can be shown to give similar results.

**5.1.1 Knoop indenter:** a pyramidal diamond with a longitudinal included angle at the vertex of  $172^\circ 30'$  and a transverse included angle of  $130^\circ$  (see Figure 1).

The four faces shall be equally inclined to the axis of the indenter (within  $\pm 0,2^\circ$ ) and shall meet at the vertex, any offset between opposite faces not exceeding  $1 \mu\text{m}$  (the usual shape of the point as it would appear under high magnification is shown in Figure 2).

**NOTE 1** The ratio of the long diagonal to the short diagonal of the indentation is approximately 7:1; the ratio of the long diagonal to the depth of penetration is approximately 30:1.

**NOTE 2** The manufacturer normally provides with each indenter a certificate stating the dimensions of the indenter. The certificate also gives the indenter constant, calculated from the dimensions.




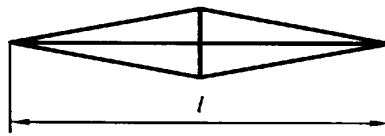


Figure 1 — Knoop indenter

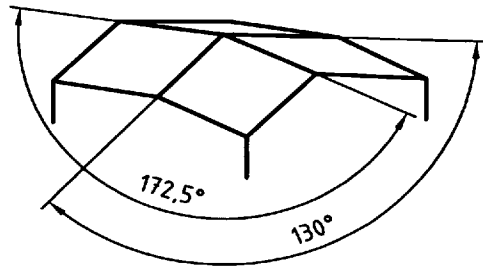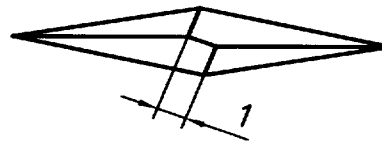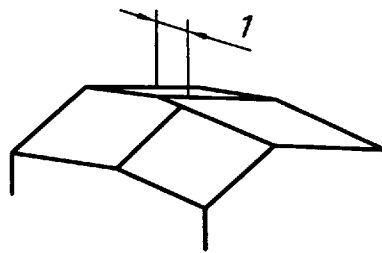

**Key**

1 Offset (1 μm max.)

Figure 2 — Indenter offset



**ISO 6441-1:1999(E)**

**5.1.2 Microscope**, with a filar micrometer eyepiece and sufficiently powerful objective to permit the measurement of the length of the indentation to within  $\pm 1\%$ .

The microscope shall be fitted with a source of illumination to give maximum contrast when viewing an indentation. The specimen shall be firmly supported on a movable micrometer stage attached to the microscope.

**5.2 Weights**, to enable a load of up to 1 N to be applied to the indenter in steps of 20 mN, 50 mN, 100 mN, 250 mN, 500 mN and 1 N.

**5.3 Standard test blocks**, for verifying the accuracy of the measurements.

It is recommended that the measurements be compared with those obtained using standard test blocks chosen so that their hardnesses cover the whole hardness range of interest.

Each test block shall be of compact-grained metal and shall have a known uniform hardness measured at the particular test force specified by the calibration authorities or the test instrument manufacturer. The test force shall be the same as that used in the actual tests.

**NOTE** A suitable source of standard reference materials in this hardness range is available from NIST<sup>2)</sup>. By agreement between the interested parties, a stable specimen (such as an aged coating or a baked enamel with a Knoop hardness  $H_K < 200 \text{ N/mm}^2$ , applied to a flat substrate) could be used to calibrate the hardness tester.

**5.4 Means of fixing the test specimen rigidly to the moving table of the hardness tester.**

**NOTE** Vibration represents a serious source of error, irrespective of the force applied, but the effects are far more evident with small forces. In general, lower hardness values are obtained if vibrations are present. This source of error can be detected by comparative measurements on a specimen of known hardness nearly equal to the hardness of the test surface. The effects of vibration can be reduced by mounting the test specimen on a rigid support.

**5.5 Stopwatch**, or other suitable timing device.

## **6 Sampling**

Take a representative sample of the product to be tested (or of each product in the case of a multicoat system), as described in ISO 15528.

Examine and prepare each sample for testing, as described in ISO 1513.

## **7 Test panels**

### **7.1 Substrate**

Unless otherwise agreed, select the substrate from one of those described in ISO 1514, using, where possible, the same type of material as will be used in practice. The substrate panels shall be plane and free from distortion.

**NOTE** Surface curvature can introduce an error in the determination of the hardness, which increases as the radius diminishes. On convex surfaces, higher hardness readings are obtained than on plane surfaces, while on concave surfaces lower hardness readings are obtained.

---

2) National Institute for Standards and Technology, Standard Reference Material Program, Building 202, Room 204, Gaithersburg, MD 20899, USA.

## 7.2 Shape and dimensions

The shape and dimensions shall be such that the test panels can be fitted correctly in the apparatus.

NOTE Typical dimensions for a test panel are 100 mm × 100 mm. Depending on the type of test instrument, other dimensions are possible.

## 7.3 Preparation and coating

Unless otherwise agreed, prepare each test panel in accordance with ISO 1514 and then coat it by the specified method with the product or system under test.

In order to minimize the effect of coating thickness on the depth of indentation, it is recommended that the conditions of test and the thickness of the coating be specified where possible so that the expected depth of indentation does not exceed approximately 25 % of the coating thickness.

## 7.4 Drying and conditioning

Dry (or stove) and age, if applicable, each coated test panel for the specified time under the specified conditions. Before testing, condition the coated panels at a temperature of  $(23 \pm 2)$  °C and a relative humidity of  $(50 \pm 5)$  % in accordance with ISO 3270, unless otherwise agreed, for a minimum period of 16 h.

## 7.5 Thickness of coating

Determine the thickness, in micrometres, of the dried coating by one of the procedures specified in ISO 2808.

## 8 Calibration of the apparatus

Calibrate the apparatus in accordance with the manufacturer's instructions, paying particular attention to the following points:

Adjust the illumination in the microscope to give maximum contrast when viewing an indentation.

By means of a calibrated scale, determine the factor for each microscope objective that converts the filar scale units of the eyepiece to millimetres.

Determine the Knoop hardness on a standard test block (see 5.3). If the value obtained is within  $\pm 5$  % of the assigned value, the instrument is considered to be calibrated.

## 9 Procedure

### 9.1 Test conditions

Carry out the test at a temperature of  $(23 \pm 2)$  °C and a relative humidity of  $(50 \pm 5)$  %, unless otherwise agreed.

### 9.2 Preparation for the test

Attach the specimen securely to the moving table so that the test surface is normal to the direction of indentation and so that it cannot move in any direction with respect to the mount during the test.

Use the microscope to select an area of the test specimen that is free of surface irregularities and imperfections.

Place this area under the indenter by means of the movable micrometer stage.

NOTE If the test surface is rough, it may be impossible to measure accurately the length of the indentation diagonal. In such cases, the surface may be gently polished, if agreed between the interested parties.

**ISO 6441-1:1999(E)****9.3 Determination**

Adjust the test load on the indenter to the specified value or the value agreed by the interested parties.

Several paint systems of different hardnesses can be compared within one series by measuring all the systems with the same load despite the fact that not all the indentation depths are within 25 % of the coating thickness. If this is done, it shall be reported in the test report.

Perform the test in accordance with the manufacturer's instructions, with the indenter in contact with the specimen for  $(18 \pm 0,5)$  s.

Immediately, or a specified length of time after completion of the 18 s indentation period, adjust the movable stage so that the indentation is in the field of the microscope.

Focus the microscope on the indentation so that both ends of the long diagonal (i.e. where the upper edges of the indentation just converge) are as sharp as possible.

Measure the length of the long diagonal of the indentation with the filar micrometer eyepiece.

Repeat the determination at least two times at widely spaced locations on the specimen. This will result in three determinations.

**10 Expression of results**

**10.1** For each specimen, calculate the mean indentation length for the three determinations and express this in filar units.

**10.2** Convert this mean indentation length in filar units to the Knoop hardness value  $H_K$  by means of the tables supplied with the instrument.

If conversion tables are not available, the Knoop hardness value can be calculated as follows:

$$H_K = \frac{P}{A} = \frac{P}{l^2 \times C}$$

where

$P$  is the load applied to the indenter, in newtons;

$l$  is the mean length of the long diagonal of the indentation, in millimetres;

$C$  is the indenter constant ( $= 7,028 \times 10^{-2}$ ) (see note 2 to 5.1.1 and the note below);

$A$  is the projected area of indentation, in square millimetres.

**NOTE** The indenter constant  $C$  is a factor for calculating the projected area, in  $\text{mm}^2$ , of the impression (see Figure 3). The value will vary slightly, depending on the actual dimensions of the indenter.

**11 Precision****11.1 General**

The data given in this clause have been taken from ASTM D 1474-92 [1].

## 11.2 Repeatability

Two results, each the mean of three determinations on a specimen, obtained by the same operator in one laboratory should be considered suspect if they differ by more than 9 % of their mean value.


## 11.3 Reproducibility

Two results, each the mean of three determinations on a specimen, obtained by operators in different laboratories should be considered suspect if they differ by more than 24 % of their mean value.

## 12 Test report

The test report shall contain at least the following information:

- a) all details necessary to identify the product tested;
- b) a reference to this part of ISO 6441 (ISO 6441-1);
- c) the items of supplementary information referred to in annex A;
- d) a reference to the international or national standard, product specification or other document supplying the information referred to in c);
- e) the mean thickness of the coating on each specimen;
- f) the load used;
- g) the results of the test as indicated in clause 10;
- h) any deviation from the test method specified;
- i) the date of the test.

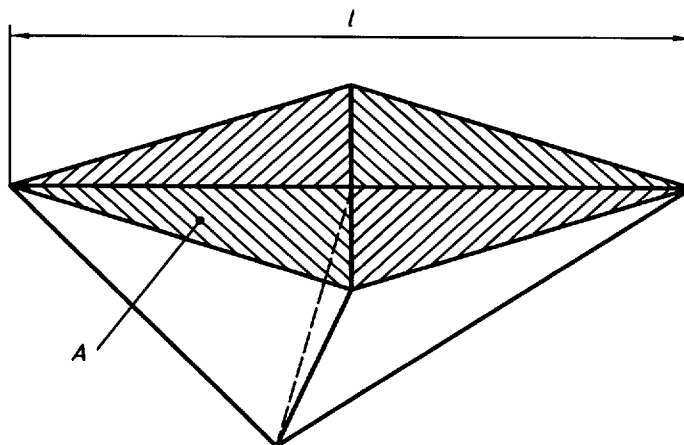

### Key

$l$  = indentation length, in mm

$A$  = projected area, in mm<sup>2</sup>

**Figure 3 — Relationship between indentation length and projected area (see 10.2)**

## **Annex A** **(normative)**

### **Required supplementary information**

The items of supplementary information listed in this annex shall be supplied as appropriate to enable the method to be carried out.

The information required should preferably be agreed between the interested parties and may be derived, in part or totally, from an international or national standard or other document related to the product under test.

- a) Material, dimensions and surface preparation of the substrate.
- b) Method of application of the test coating to the substrate, including duration and conditions of drying between coats in the case of a multi-coat system.
- c) Duration and conditions of drying (or stoving) and ageing (if applicable) of the coated panels before testing.
- d) Thickness, in micrometres, of the dry coating and method of measurement in accordance with ISO 2808, and whether it is a single coat or a multi-coat system.
- e) Temperature and humidity of the test, if different from those specified in 9.1.

## Bibliography

- [1] ASTM D 1474-92, *Standard Test Methods for Indentation Hardness of Organic Coatings*.
- [2] ISO 4516, *Metallic and related coatings — Vickers and Knoop microhardness tests*.

**ISO 6441-1:1999(E)**

---

---

**ICS 87.040**

Price based on 9 pages

© ISO 1999 – All rights reserved