
**Plastics — Determination of puncture
impact behaviour of rigid plastics —**

**Part 1:
Non-instrumented impact testing**

*Plastiques — Détermination du comportement des plastiques rigides
perforés sous l'effet d'un choc —*

Partie 1: Essais de choc non instrumentés



Reference number
ISO 6603-1:2000(E)

© ISO 2000

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 734 10 79
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Contents

Page

Foreword.....	iv
1 Scope	1
2 Normative references	2
3 Terms and definitions	3
4 Principle	5
5 Apparatus	6
6 Test specimens	9
7 Procedure	10
8 Precision	16
9 Test report	16
Annex A (informative) Examples of calculations	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 6603 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 6603-1 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical properties*.

This second edition cancels and replaces the first edition (ISO 6603-1:1985), which has been technically revised.

ISO 6603 consists of the following parts, under the general title *Plastics — Determination of puncture impact behaviour of rigid plastics*:

- *Part 1: Non-instrumented impact testing*
- *Part 2: Instrumented impact testing*

Annex A of this part of ISO 6603 is for information only.

Plastics — Determination of puncture impact behaviour of rigid plastics —

Part 1: Non-instrumented impact testing

1 Scope

This International Standard specifies methods for the determination of puncture-impact properties of rigid plastics in the form of flat test specimens, such as discs or square pieces, under defined conditions. Specimens may be moulded directly, cut from sheets or taken from finished products. Different types of test specimens and test conditions are defined.

These falling-dart methods are used to investigate the behaviour of plastic sheeting or mouldings under the impact of a striker applied perpendicular to the plane of the specimen.

This part of ISO 6603 can be used if it is sufficient to characterize the impact behaviour of plastics by a threshold value of impact-failure energy based on many test specimens. ISO 6603-2 is used if a force-deflection or force-time diagram, recorded at nominally constant striker velocity, is necessary for detailed characterization of the impact behaviour.

These test methods are applicable to specimens with a thickness between 1 mm and 4 mm.

NOTE For thicknesses less than 1 mm, ISO 7765 should preferably be used. Thicknesses greater than 4 mm may be tested if the equipment is suitable, but the test falls outside the scope of ISO 6603-1 and ISO 6603-2.

These methods are suitable for use with the following types of material:

- rigid thermoplastic moulding and extrusion materials, including filled, unfilled and reinforced compounds and sheets;
- rigid thermosetting moulding and extrusion materials, including filled and reinforced compounds, sheets and laminates;
- fibre-reinforced thermoset and thermoplastic composites incorporating unidirectional or non-unidirectional reinforcements such as mats, woven fabrics, woven rovings, chopped strands, combination and hybrid reinforcements, rovings, milled fibres and sheets made from pre-impregnated materials (prepregs).

These methods are also applicable to specimens which are either moulded or machined from finished products, laminates and extruded or cast sheet.

The test results are comparable only if the conditions of preparation of the specimens, their dimensions and surfaces as well as the test conditions are the same. In particular, results determined on specimens of different thickness cannot be compared with one another (see annex E of ISO 6603-2:—). Comprehensive evaluation of the reaction to impact stress requires that determinations be made as a function of impact velocity and temperature for different material variables, such as crystallinity and moisture content.

The impact behaviour of finished products cannot be predicted directly from this test, but specimens may be taken from finished products (see above) for test by these methods.

Test data developed by these methods should not be used for design calculations. However, information on the typical behaviour of the material can be obtained by testing at different temperatures and impact velocities (see annex D of ISO 6603-2:—), by varying the thickness (see annex E of ISO 6603-2:—) and by testing specimens prepared under different conditions.

Two statistical methods of test are described in this part of ISO 6603:

— Method A: staircase method (individual) (preferred)

In this method, a uniform energy increment is employed during testing. The energy is decreased or increased by the uniform increment after testing each specimen, depending upon the observed result (pass or fail) for the preceding test.

— Method B: group method (optional)

In this method, successive groups of at least ten test specimens are tested. The impact failure energy is calculated by statistics.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 6603. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 6603 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 291:1997, *Plastics — Standard atmospheres for conditioning and testing.*

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials.*

ISO 294-3:1996, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 3: Small plates.*

ISO 295:1991, *Plastics — Compression moulding of test specimens of thermosetting materials.*

ISO 1268:1974¹⁾, *Plastics — Preparation of glass fibre reinforced, resin bonded, low-pressure laminated plates or panels for test purposes.*

ISO 2818:1994, *Plastics — Preparation of test specimens by machining.*

ISO 6603-2:—²⁾, *Plastics — Determination of puncture impact behaviour of rigid plastics — Part 2: Instrumented impact testing.*

ISO 7765-1:1988, *Plastics film and sheeting — Determination of impact resistance by the free-falling dart method — Part 1: Staircase methods.*

ISO 7765-2:1994, *Plastics film and sheeting — Determination of impact resistance by the free-falling dart method — Part 2: Instrumented puncture test.*

1) Under revision.

2) To be published (Revision of ISO 6603-2:1989)

3 Terms and definitions

For the purposes of this part of ISO 6603, the following terms and definitions apply:

3.1 General

3.1.1

failure

any break in the surface of the specimen which is visible to the naked eye

3.2 Failure-criteria terms

3.2.1

crack

any fissure that can be observed by the naked eye and that does not penetrate the full thickness of the material (see Figure 1)

3.2.2

break

any fissure through the full thickness of the material (see Figure 2)

3.2.3

penetration

failure in which the striker penetrates through the whole thickness of the test specimen [see Figure 3 b)]

3.2.4

shattering

breaking of the test specimen into two or more pieces [see Figure 3 a)]

3.3 Impact-failure terms

3.3.1

50 % impact-failure energy

E_{50}

the energy that will cause 50 % of the test specimens to fail as defined in 3.1.1

3.3.2

50 % impact-failure mass

M_{50}


the mass that will cause 50 % of the test specimens to fail, as defined in 3.1.1, for a given height of fall

3.3.3


50 % impact-failure height

H_{50}

the height that will cause 50 % of the test specimens to fail, as defined in 3.1.1, using a given falling mass

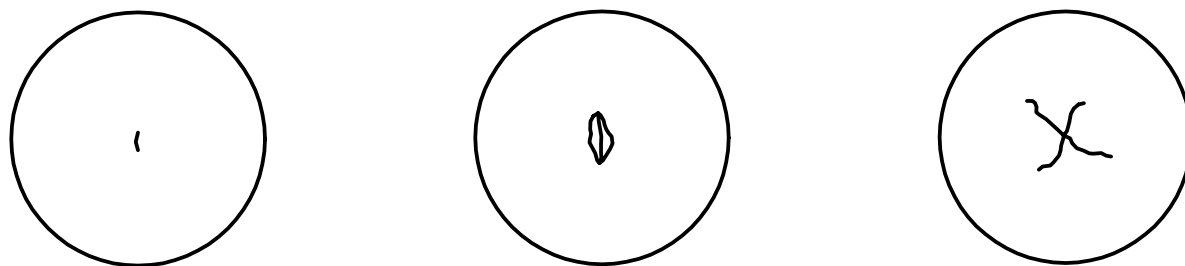


Views of specimen surfaces damaged by a “crack” (examples)

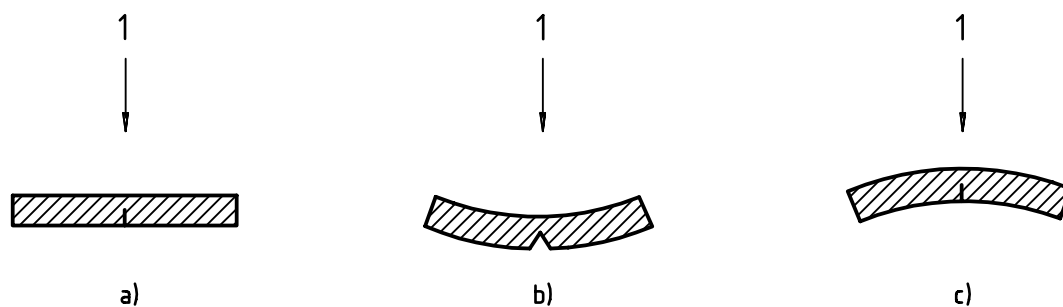

Key

1 Impact direction


Figure 1 — Sections through specimens damaged by a “crack” [b) and c) after bending by hand]

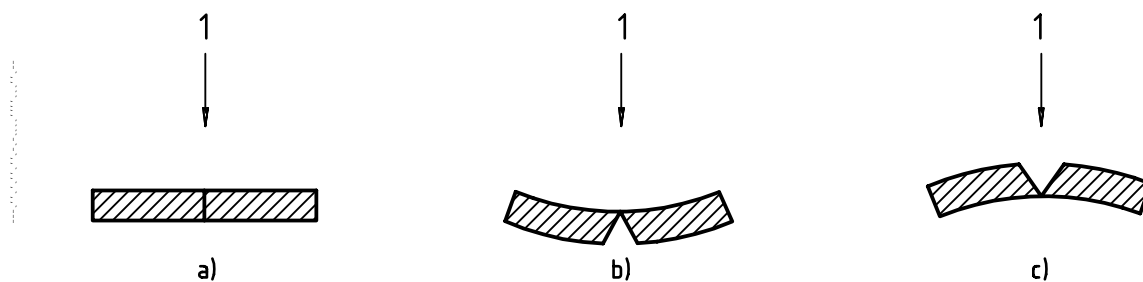

Key

1 Impact direction

Figure 2 — Sections through specimens damaged by a “break” [b) and c) after bending by hand]

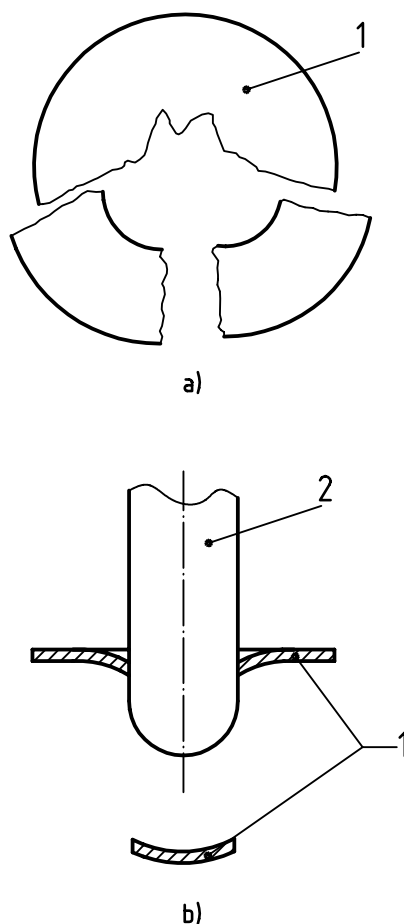

Key

- 1 Specimen
- 2 Dart with hemispherical head

Figure 3 — Example of “shattering” failure [a)] and “penetration” [b)]

4 Principle

The impact strength of suitably sized test specimens is determined by striking them with a lubricated weighted striker dropped vertically from a known height. The test specimen is impacted at its centre by a striker, perpendicular to the surface of the specimen.

Two methods of adjusting the energy at impact are permitted: altering the mass at constant height and altering the height at constant mass.

NOTE The variable-height procedure is velocity-dependent, and differing results may be observed depending upon the material's strain rate.

Two statistical methods of test are given:

- Method A: staircase method (individual) (preferred).
- Method B: group method (optional).

5 Apparatus


5.1 Test device

5.1.1 Essential components

The essential components of the test device (see Figure 4) are:

- an energy carrier (dart system), of the inertial-mass type, which includes:
 - weights,
 - a striker (lubrication is required);
- a specimen support (see Figure 4), optionally with a clamping device (Figure 5).


The test device shall permit the test specimen to be punctured at its centre, perpendicular to the specimen surface.

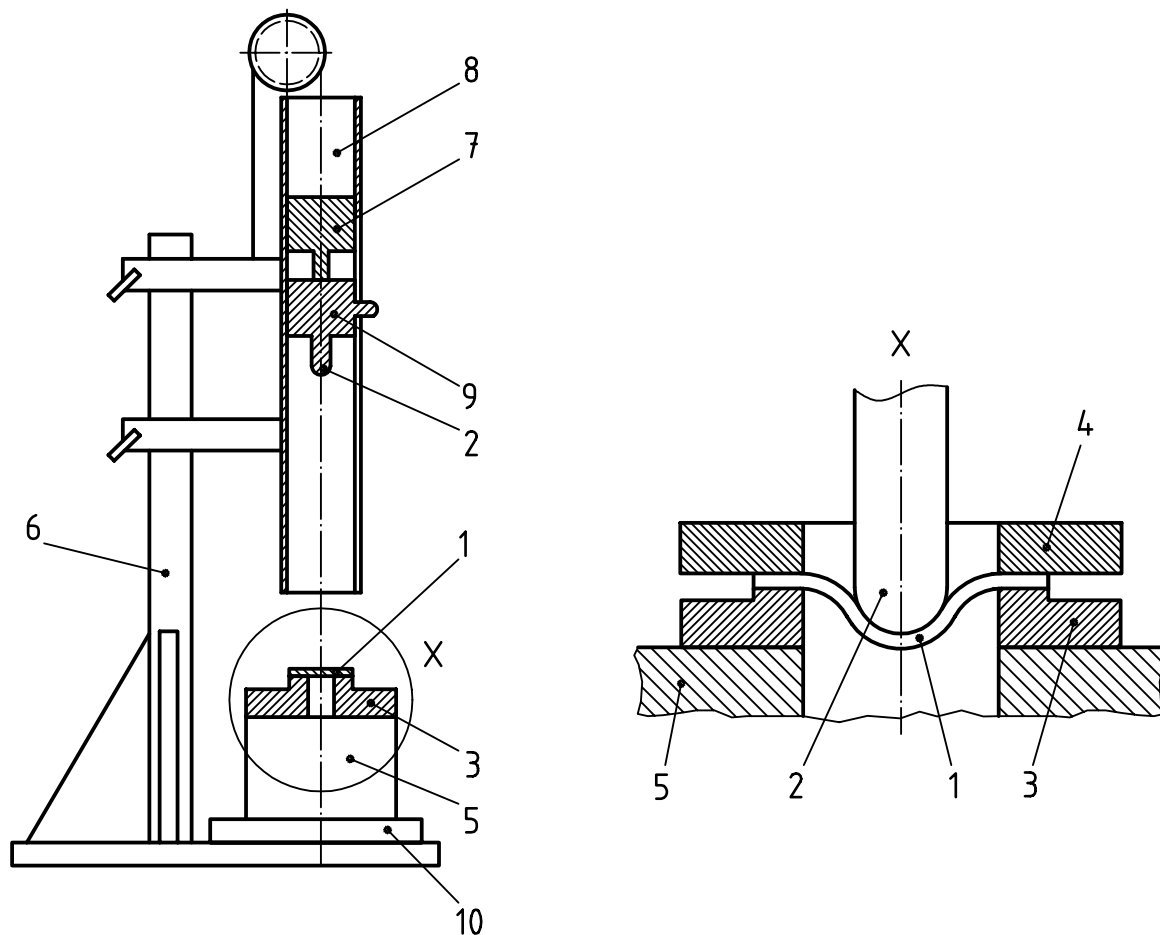

Key

- | | | | |
|---|---------------------------|----|---|
| 1 | Test specimen | 6 | Stand for falling-dart system |
| 2 | Hemispherical striker tip | 7 | Holding and release system for weighted striker |
| 3 | Test specimen support | 8 | Guide shaft for weighted striker |
| 4 | Clamping ring (optional) | 9 | Weighted striker |
| 5 | Base | 10 | Acoustic isolation (optional) |

Figure 4 — Falling-dart system (example)

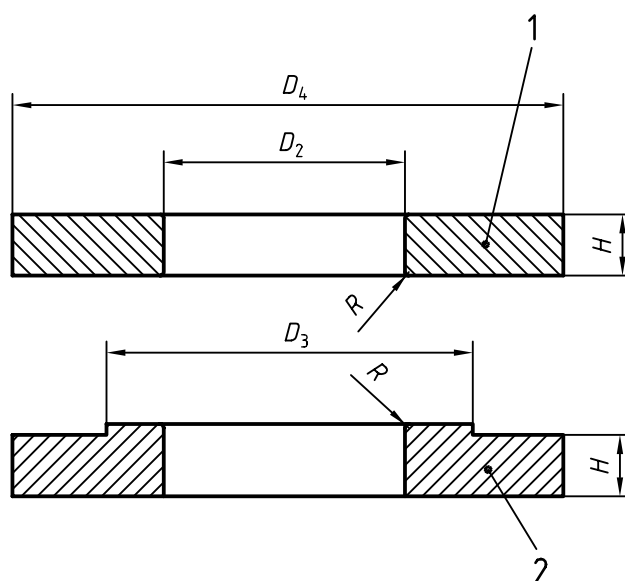**Key**

- 1 Clamping ring (optional)
- 2 Specimen support

Dimensions in millimetres

	Specimen type	
	Square of side 60	Disc of diam. 140
D_2	40 ± 2	100 ± 5
D_3	60	140
D_4	min. 90	min. 200
H	12	12
R	1	1

Figure 5 — Schematic drawing of clamping device (optional)**5.1.2 Falling-dart system**

The falling-dart system shall be capable of holding and releasing a weighted striker such that it will fall constrained by one or more guides. The fall shall be nominally without friction and losses through windage, or the amount of friction has to be taken into account in the calculations.

5.1.3 Weights (masses)

Appropriate weights are required that can be firmly attached to the striker. The combined mass of the attached weights, and the mass of the striker, shall be known to within 1 %.

5.1.4 Striker

The preferred striker has a polished hemispherical striking surface with a diameter $20 \text{ mm} \pm 0,2 \text{ mm}$. Alternatively, a $10 \text{ mm} \pm 0,1 \text{ mm}$ diameter striking surface may be used.

NOTE The size, dimensions and condition of the surface of the striker will affect the results.

The preferred striker is one made of any material with sufficient resistance to wear and of sufficiently high strength to prevent plastic deformation. In practice, hardened tool steel or similar material with a hardness of 54 HRC has been found acceptable. Harder materials or materials with a lower density (for example titanium) with equivalent

hardness are also acceptable. The hemispherical surface of the striker shall be lubricated to reduce any friction between the striker and the test specimen (see annex B of ISO 6603-2:—).

5.1.5 Support ring

The support ring (see Figures 4 and 5) shall be rigidly fixed on a rigid base and shall be designed such that air cannot be trapped under the test specimen, possibly causing a spring effect. Below the support ring, there shall be enough distance for the striker to travel after total penetration of the test specimen. The support ring shall have an inside diameter of either 40 mm ± 2 mm or 100 mm ± 5 mm and a minimum height of 12 mm.

5.1.6 Striker/support combinations

The following striker/support combinations are permissible:

Striker	Support	
20 mm	40 mm	Default combination
10 mm	100 mm	Optional

5.1.7 Base for test device

The test device shall be firmly mounted on a rigid structure of sufficient stiffness to minimize deflection of the specimen support. The mass of the base shall be at least 180 kg.

The test device is generally susceptible to mechanical vibration. The design of the foundation on which the base is mounted shall be such as to minimize the effect of any mechanical vibration in the system. The centre of gravity of the base shall be in line with the trajectory of the impacting striker.

5.1.8 Clamping device (optional)

When it is utilized, a two-piece annular specimen clamp consisting of the support ring and a clamping ring shall be used (see Figure 5).

The clamping device shall have an inside diameter equal to 40 mm ± 2 mm or 100 mm ± 5 mm. The clamp may work by the application of force on the specimen. A clamping force of ≥ 3 kN is recommended.

NOTE Pneumatically and screw operated clamps have been successfully employed. The results obtained for clamped and unclamped specimens are likely to be different because the edges of an unclamped specimen are free to move under test and specimen vibrations with higher amplitudes may occur (see annex C of ISO 6603-2:—).

5.1.9 Device for catching the dart after impact

This device is designed to prevent multiple impacts on the specimen and damage to the striker.

5.2 Thickness gauge

This device shall enable the thickness of the test specimens to be measured to an accuracy of ±0,01 mm.

6 Test specimens

6.1 Shape and dimensions

The preferred test specimen is $60\text{ mm} \pm 2\text{ mm}$ square or $60\text{ mm} \pm 2\text{ mm}$ in diameter, with a thickness of $2,0\text{ mm} \pm 0,1\text{ mm}$, and is used with the 40 mm diameter support ring.

For testing brittle fibre-reinforced plastic composites and low failure strain plastics, a test specimen $140\text{ mm} \pm 2\text{ mm}$ square or $140\text{ mm} \pm 2\text{ mm}$ in diameter with a recommended thickness of $4,0\text{ mm} \pm 0,2\text{ mm}$ may be used with the 100 mm diameter support ring.

6.2 Preparation of test specimens

The test specimens shall be prepared in accordance with the relevant material specification. Where none exists, or when not otherwise specified, test specimens shall be prepared in accordance with ISO 293, ISO 294-3, ISO 295 or ISO 1268 as appropriate or machined from plates in accordance with ISO 2818 (see note). The test specimens may also be prepared with a cutting or punching device, since there are no special requirements for the cut edges.

NOTE The preparation of test specimens 140 mm square or 140 mm in diameter by injection moulding is not yet covered by any International Standard.

Because the larger specimen is used primarily for fibre-reinforced plastic composites, it is recommended that they be made by machining from sheet material.

Test specimens taken from larger sheets or sections of sheet shall be taken from locations that are as uniformly distributed over the surface as possible. Non-homogeneous edge zones shall not be used. The thickness of these test specimens shall be the thickness of the sheet up to a thickness of 4 mm. If the sheet is more than 4 mm thick, the specimens shall be machined to 4 mm.

6.3 Non-homogeneous test specimens

In general, the test is conducted on either side of the specimen, selected at random. However, if there is a reason to believe that the results are dependent on which side of the specimen faces the striker, each side shall be tested separately. This especially holds for test specimens with textured surfaces, specimens lacquered on one side and specimens which are UV-aged. When assessing the influence of a one-sided treatment, the test specimen shall be impacted on the opposite side.

6.4 Checking the specimens

The specimens shall be free of twist and warpage. Both surfaces shall be smooth and free of scratches, pits and sink marks to avoid notching effects.

The specimens shall be checked for conformity with these requirements by visual observation or by measuring with a thickness gauge.

Specimens showing any observable departure from one or more of these requirements shall be rejected.

6.5 Number of test specimens

For tests conducted under constant conditions:

- Method A: staircase method (individual) (preferred)

At least 30 test specimens shall be used (10 for pretesting to determine the starting energy).

— Method B: group method (optional)

At least 40 test specimens shall be used (10 for pretesting and 30 for the main test).

If a large number of test specimens is required, for example to determine the temperature dependence of the parameters measured, the test specimens shall be selected in accordance with statistical principles.

6.6 Conditioning of test specimens

The test specimens shall be conditioned as required by the relevant material specification or as agreed upon by the interested parties. Otherwise, the most appropriate conditions from ISO 291 shall be selected.

7 Procedure

7.1 Test atmosphere

7.1.1 General

Conduct the test in one of the standard atmospheres specified in ISO 291.

7.1.2 Room-temperature testing

If a standard atmosphere from ISO 291 was used for conditioning, conduct the test in the same atmosphere. If not, ensure that the transit time t_T (see note) is short enough (i.e. less than 5 s) to prevent changes in the mechanical behaviour (state of material) of the test specimen caused by changes in the temperature of the specimen. For dry polyamides, for instance, a transit time of up to 30 min has been found not to markedly affect the impact behaviour when testing in an atmosphere of 23 °C and 50 % R.H.

NOTE The transit time t_T is the total time from the removal of the specimen from the conditioning environment until the specimen is impacted.

7.1.3 Low-temperature testing

When test specimens are conditioned at low temperature and the test equipment is at room temperature, a transit time t_T (see note to 7.1.2) short enough to prevent significant changes in the temperature of the test specimen prior to impact is required (i.e. less than 5 s). Differences in humidity between the test specimen conditioning atmosphere and the test atmosphere are critical.

7.2 Measurement of thickness

For each test specimen, measure the thickness to the nearest 0,02 mm at three points which are equidistant to one another on a circle with a radius of 10 mm centred on the centre of the specimen. Record the average value of the measured thickness (see note). If the thickness of any specimen differs by more than 5 % from the average thickness of the specimens from that sample, discard that specimen and replace it with another specimen.

NOTE When using injection-moulded specimens, it is not necessary to measure the dimensions of each specimen. It is sufficient to measure one specimen from each set.

When using multiple-cavity moulds, measure the thickness of the specimens from each cavity. If the difference in specimen thickness between mould cavities is greater than 5 %, the specimens from each cavity shall be treated as different batches.

7.3 Clamping the test specimen (optional)

The default condition for this test is that the specimen is unclamped.

If the specimen is clamped, however, take care to ensure that the clamping force does not induce bending or torsional forces in the specimen.

7.4 Lubrication

Lubricate the tip of the striker with oil or grease before each test. The viscosity η of the lubricant shall be in the range $10 \text{ cP} < \eta < 10^4 \text{ cP}$ ($10^{-2} \text{ Pa}\cdot\text{s} < \eta < 10 \text{ Pa}\cdot\text{s}$) (see annex B of ISO 6603-2:—)

7.5 Puncture test procedure

7.5.1 General

Place the test specimen on the support ring (5.1.5) and clamp in place, if appropriate. When testing machined specimens, impact the specimen on the machined surface.

Firmly secure the necessary weights (5.1.3) to the striker (5.1.4).

Put the dart (5.1.2) into position at the specified height, according to the method used, and release the dart.

If the dart rebounds from the surface of the test specimen, catch the dart after it bounces to prevent

- multiple impacts with the surface of the test specimen;
- any damage to the hemispherical surface of the dart if it impacts with metal parts of the apparatus.

Examine the test specimen to determine whether it has or has not failed in accordance with any of the definitions given in 3.2.

The failure criteria defined in 3.2 describe definite alterations of the test specimen caused by the falling mass, a failure being defined as any break in the surface of the specimen which is visible to the naked eye. These failure criteria shall be either as specified in the relevant material specification or agreed upon by the interested parties. If other failure criteria (e.g. crazing, indentation, stress whitening, etc.) are deemed to be of importance, these criteria shall be defined by agreement between the interested parties and included in the test report.

Each test specimen shall be impacted only once.

7.5.2 Constant height of fall (preferred)

A height of fall of 1 m should preferably be chosen for a variable falling mass. If the specimen cannot be broken by this method, then the alternative constant falling mass approach is recommended.

7.5.3 Constant falling mass (optional)

If a variable height is used, it should be chosen over any range between 0,3 m and 2,0 m, but preferably around 1,0 m.

7.6 Method A: staircase method (preferred)

7.6.1 General

In this method, a uniform energy increment is employed during testing and the energy is adjusted after striking each test specimen. The energy at impact is adjusted either by altering the mass at constant height or altering the height at constant mass (see, however, the note to clause 4).

7.6.2 Pretesting

Use 10 test specimens to estimate the 50 % impact-failure energy E_{50} .

NOTE It is suggested that, during pretesting, the increments used are not uniform. Begin with relatively large increments to find the energies which will cause, with certainty, failure (or no failure). Finish the pretesting with smaller energy increments in order to estimate roughly the energy that causes 50 % of the test specimens to fail.

7.6.3 Test procedure

As a starting point, select an energy near the expected impact-failure energy, based on the pretesting.

Select an energy increment ΔE appropriate to the impact strength of the sample. The value chosen for ΔE should preferably be such that three to six energy steps will be employed in the determination. A ΔE value equal to approximately 5 % of the expected impact-failure energy E , based on the pretesting, is usually appropriate.

After striking the first specimen, examine it to determine whether it has or has not failed and record the results in the form shown in Figure 6 or 7, using an "o" to denote non-failure and an "x" to denote failure.

If the first specimen fails, decrease the energy by ΔE . If the first specimen does not fail, increase the energy by ΔE . Continue testing successive specimens, decreasing or increasing the energy by ΔE between drops, depending upon whether the preceding specimen did or did not fail.

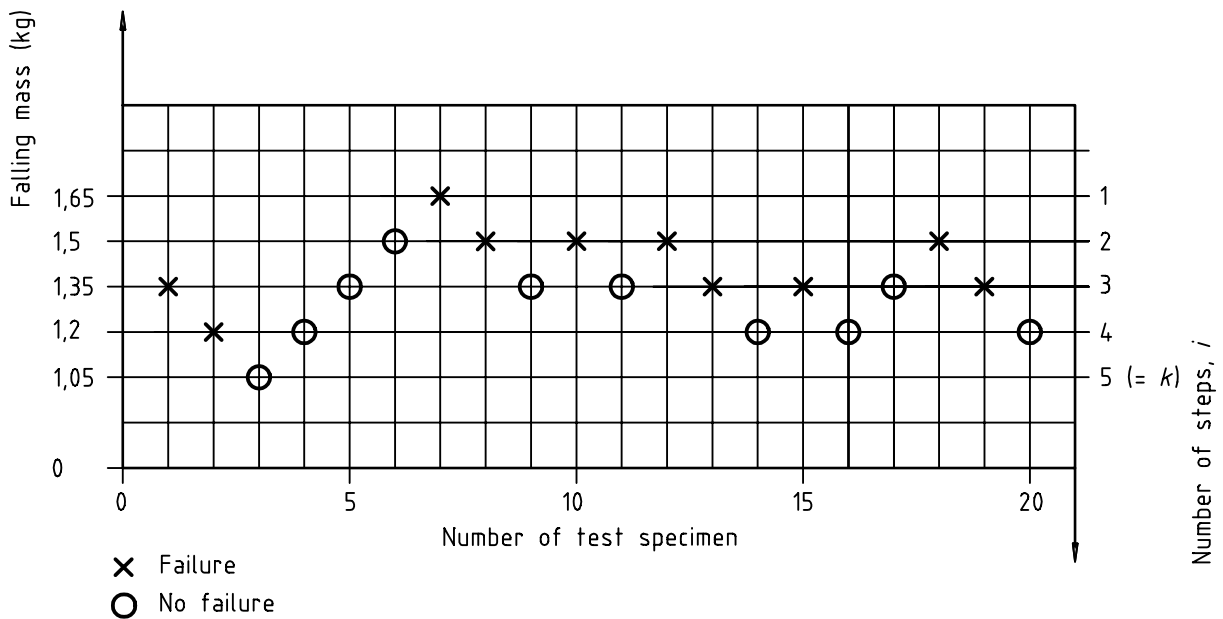


Figure 6 — Example of method A (staircase) test results with constant height of fall (0,66 m)

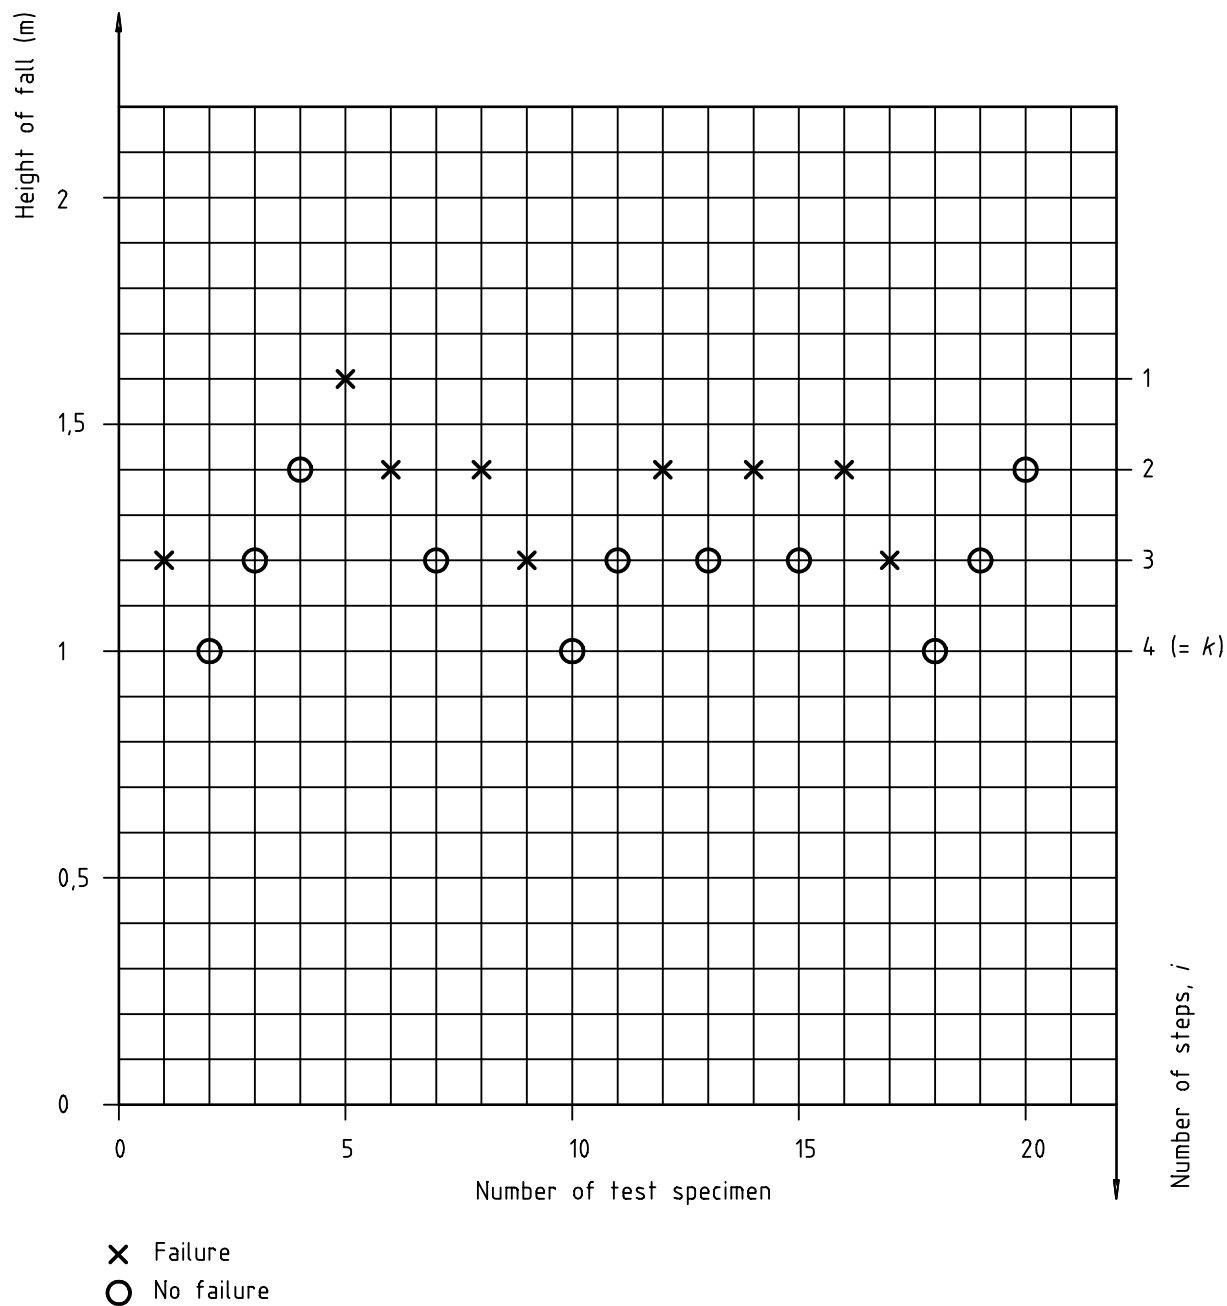


Figure 7 — Example of method A (staircase) test results with constant mass (1 kg)

7.6.4 Expression of results

7.6.4.1 Calculation

Calculate the 50 % impact-failure energy E_{50} , in joules, as follows:

$$E_{50} = H \times g \times m_{50} \quad \text{in the case of constant height}$$

$$E_{50} = m \times g \times H_{50} \quad \text{in the case of constant mass}$$

where

H is the constant height of fall, in metres;

m is the constant falling mass, in kilograms;

g is the acceleration due to gravity (9,81 m/s²);

$$m_{50} = m_a + \Delta m \left(\frac{A}{N} \pm 0,5 \right)$$

$$H_{50} = H_a + \Delta H \left(\frac{A}{N} \pm 0,5 \right)$$

[the plus sign is taken if the no-failure ($N = N_0$) blows are considered and the minus sign if the failure ($N = N_x$) blows are considered]

m_a being the smallest mass among the k mass steps m_i ($i = 1$ to k) from the main test, in kilograms,

Δm being the mass increment, in kilograms,

H_a being the smallest height among the k height steps H_i ($i = 1$ to k) from the main test, in metres,

ΔH being the height increment, in metres;

$$N = \sum_{i=1}^k n_i$$

[total number of failed (N_x) or not failed (N_0) specimens, depending which number is smaller]

n_i being the number of specimens that have failed or not failed, respectively, at each height H_i or mass m_i ;

$$A = \sum_{i=1}^k n_i z_i$$

z_i being the number of mass increments from m_a or the number of height increments from H_a , given by

$$z_i = \frac{m_i - m_a}{\Delta m}$$

or

$$z_i = \frac{H_i - H_a}{\Delta H}$$

7.6.4.2 Standard deviation

Calculate the standard deviation s , in joules, as follows:

$$s = 1,62 \Delta E \left(\frac{NB - A^2}{N^2} + 0,029 \right)$$

where

$$B = \sum_{i=1}^k n_i z_i^2$$

This formula is valid only if $\frac{NB - A^2}{N^2} > 0,3$.

Examples of the calculations are given in annex A.

NOTE If the condition $0,5s \leq \Delta E \leq 2s$ is not fulfilled, it is strongly recommended that the test be repeated with another ΔE .

7.7 Method B: group method

7.7.1 General

In this method, successive groups of at least 10 test specimens each are tested. For each group, one impact energy is employed and from group to group the energy is varied in increments. The energy at impact is adjusted either by altering the mass at constant height or altering the height at constant mass (see, however, the note to clause 4)

Testing is carried to a point where there are at least five percentage-failure results: one 0 % failure result, one 100 % failure result and at least three results between the 0 % and 100 % results. The three results between the 0 % and 100 % limits shall not all be lower or higher than 50 %.

7.7.2 Pretesting

Test a minimum of 10 test specimens to estimate the approximate limits at which 0 % and 100 % failure occurs.

7.7.3 Test procedure

Select the mass (or height) increments such that, between the "0 %" and "100 %" limits, based on the pretesting, a minimum of three points is determined, at each of which at least 10 test specimens are tested.

Record the failure mass (or height) and the percentage of failures for each point.

At this stage, if the minimum five results described in 7.7.1 have been obtained, testing is complete.

7.7.4 Expression of results

7.7.4.1 Calculation

Plot the data on linear probability graph paper (see Figure 8) with mass (or height) along the linear axis and percent failure along the probability axis, omitting the 0 % and 100 % failure points.

Fit the best straight line through the points and read M_{50} (or H_{50}) from the graph at the falling mass (or height of fall) corresponding to the intersection of the straight line with the 50 % probability line.

7.7.4.2 Standard deviation

To determine the standard deviation s , determine in the same way E_{16} and E_{84} as shown in Figure 8 and calculate s as follows:

$$s = \frac{E_{84} - E_{16}}{2}$$

NOTE The best-fitting straight line may be obtained by a suitable technique such as the least-squares method or regression analysis.

An example of the calculation is given in annex A.

7.8 Significant figures

Report all calculated mean values for both methods to two significant figures.

8 Precision

The precision of this test method is not known because inter-laboratory data are not available. When inter-laboratory data are obtained, a precision statement will be added at the following revision.

9 Test report

The test report shall include the following information:

- a) a reference to this part of ISO 6603;
- b) the test parameters, identified as follows:
 - the method used, A or B,
 - the support ring diameter 40 mm (or 100 mm),
 - the striker diameter 20 mm (or 10 mm),
 - whether the specimen was clamped (C) or unclamped (U),
 - the impact velocity 4,4 m/s (or other),e.g. "Non-instrumented puncture test ISO 6603-1/A/40/20/C/4,4";
- c) type, identification mark, origin, date of receipt and other pertinent data concerning the test material, such as coated, textured and orientation of texture;
- d) the shape and dimensions of the specimens tested;
- e) the method of preparation of the specimens;
- f) the average thickness of the specimens, measured in accordance with 7.2;
- g) the test conditions and, if applicable, the conditioning procedure;
- h) if clamping was used, details of the way it was done;
- i) the type of lubricant, if used;

- j) the number of specimens tested;
- k) the appearance of the specimens after the test (optional);
- l) the constant height (or mass) and increment used;
- m) the impact-failure criterion that was agreed upon;
- n) the 50 % impact-failure energy, in joules, to two significant figures and, if required, the standard deviation and the individual test results in graphic form (see examples in Figures 6 to 8);
- o) the date of the test.

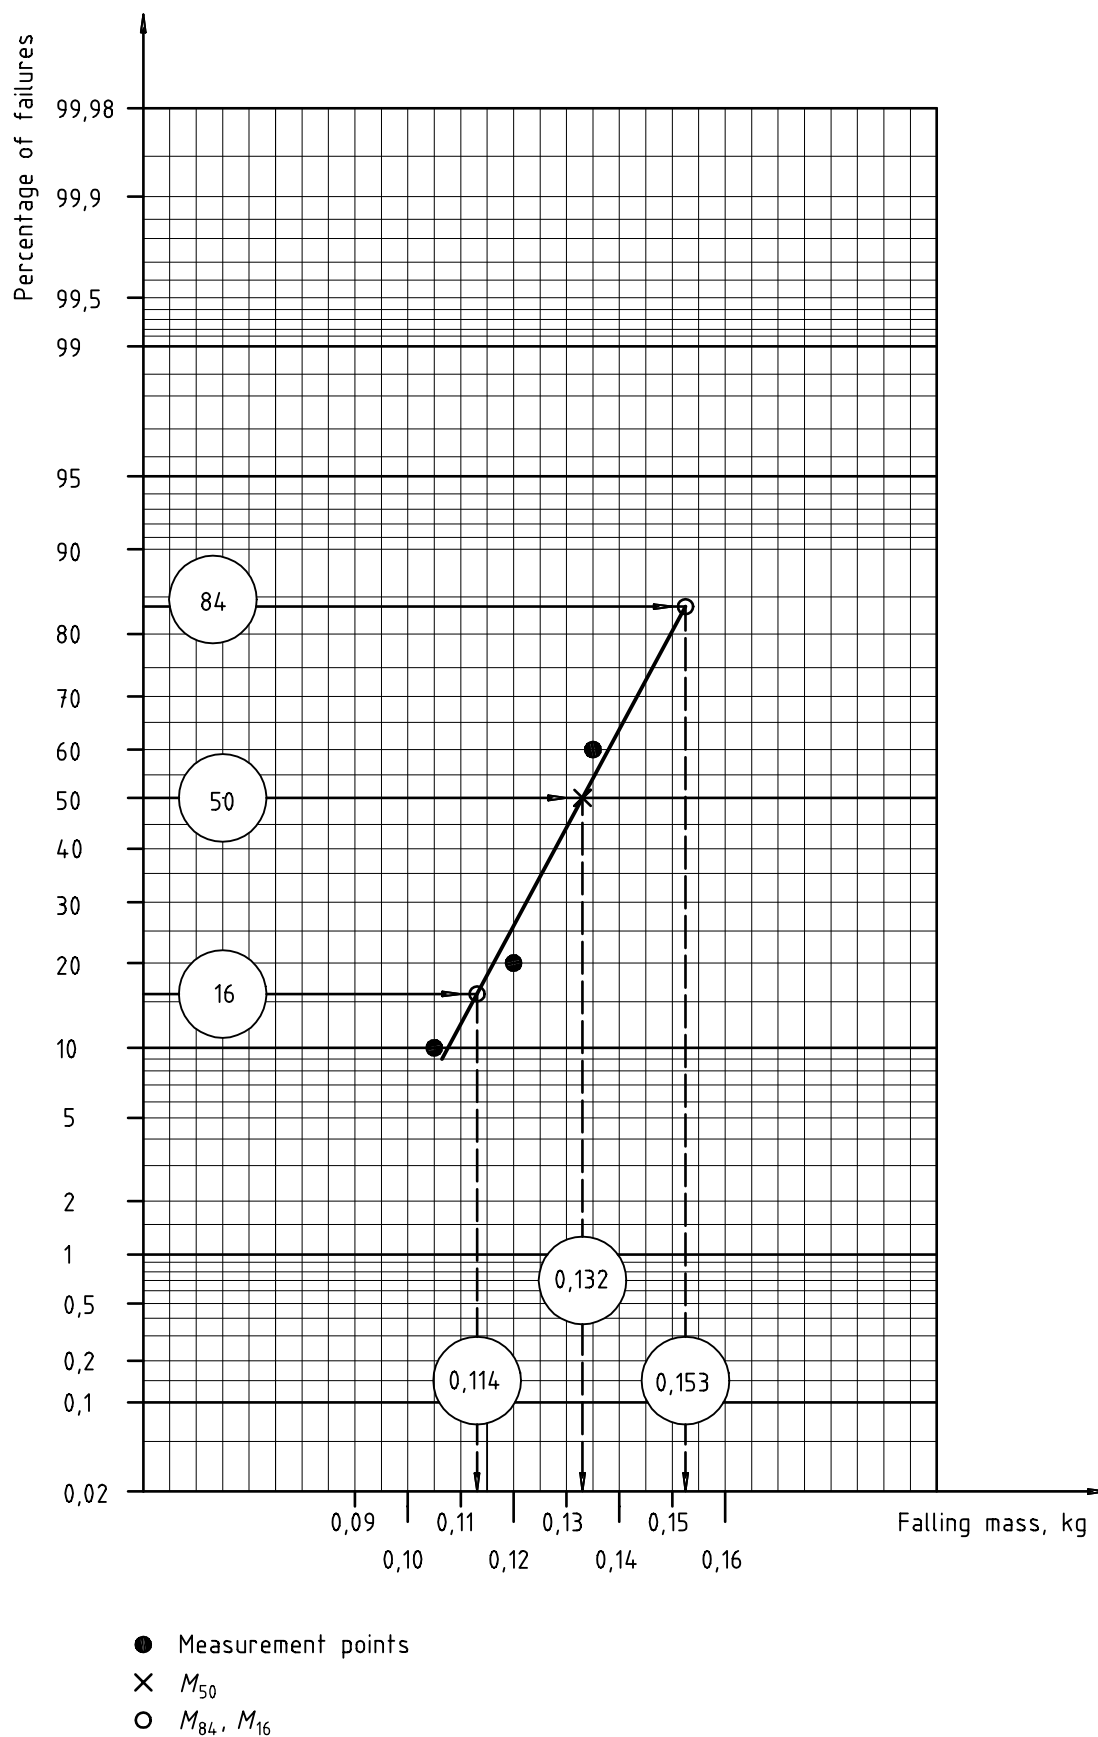


Figure 8 — Example of plot for method B (group) with constant height of fall (1 m)

Annex A (informative)

Examples of calculations

A.1 Method A: staircase method

EXAMPLE 1: Variable falling mass, constant height of fall (see Figure 6 and Table A.1)

Table A.1

i	Falling mass kg	$n_i(0)$	$n_i(X)$	n_i	z_i	$n_i z_i$	$n_i z_i^2$
1	1,65	0	1	1	4	4	16
2	1,50	1	4	4	3	12	36
3	1,35	4	4	4	2	8	16
4	1,20	4	1	1	1	1	1
5 (= k)	1,05	1	0	0	0	0	0
$\sum_{i=1}^k$		10 (N_0)	10 (N_X)	10 ($N = N_X$)		25 (A)	69 (B)

Number of specimens:	20
Height of fall:	0,65 m
Falling mass:	Variable
Mass increment:	0,15 kg
Initial falling mass from pretesting	1,35 kg

The number of failure blows N_X and no-failure blows N_0 are the same, so either can be used in the calculation. Otherwise, the smaller number shall be used. In the example in Table A.1 and the following calculation, the failure blows have been used.

$$M_a = 1,05 \text{ kg}; \quad \Delta M = 0,15 \text{ kg}; \quad N = N_X = 10$$

$$A = \sum_{i=1}^{k=5} n_i z_i = 25$$

$$B = \sum_{i=1}^{k=5} n_i z_i^2 = 69$$

$$E_{50} = HgM_{50} = Hg \left[M_a + \Delta M \left(\frac{A}{N} - \frac{1}{2} \right) \right]$$

$$E_{50} = 0,66 \times 9,81 \left[1,05 + 0,15 \left(\frac{25}{10} - \frac{1}{2} \right) \right] = 8,74 \text{ J}$$

$$s = 1,62 \Delta E \left(\frac{NB - A^2}{N^2} + 0,029 \right) = 1,62 (Hg \Delta M) \left(\frac{NB - A^2}{N^2} + 0,029 \right)$$

$$s = 1,62 (0,66 \times 9,81 \times 0,15) \left(\frac{10 \times 69 - 625}{100} + 0,029 \right) = 1,07 \text{ J}$$

Thus

$$E_{50} = 8,74 \text{ J}$$

$$s = 1,07 \text{ J}$$

EXAMPLE 2: Variable height of fall, constant mass (see Figure 7 and Table A.2):

Table A.2

<i>i</i>	Height of fall m	$n_i(o)$	$n_i(x)$	n_i	z_i	$n_i z_i$	$n_i z_i^2$
1	1,6	0	1	1	3	3	9
2	1,4	2	5	5	2	10	20
3	1,2	6	3	3	1	3	3
4 (= <i>k</i>)	1,0	3	0	0	0	0	0
$\sum_{i=1}^k$		11 (N_o)	9 (N_x)	9 ($N = N_x$)		16 (<i>A</i>)	32 (<i>B</i>)

Number of specimens: 20
 Falling mass: 1 kg
 Height of fall: Variable
 Height of fall increment: 0,2 m
 Initial height of fall from pretesting 1,2 m

Since $N_x < N_o$, the calculation is conducted on the basis of the $N = N_x$

$$E_{50} = MgH_{50} = Mg \left[H_a + \Delta H \left(\frac{A}{N} - \frac{1}{2} \right) \right]$$

$$E_{50} = 1,0 \times 9,81 \left[1,0 + 0,2 \left(\frac{16}{9} - \frac{1}{2} \right) \right] = 12,3 \text{ J}$$

$$s = 1,62 \Delta E \left(\frac{NB - A^2}{N^2} + 0,029 \right) = 1,62 (Mg \Delta H) \left(\frac{NB - A^2}{N^2} + 0,029 \right)$$

$$s = 1,62 (1 \times 9,81 \times 0,2) \left(\frac{9 \times 32 - 256}{81} + 0,029 \right) = 1,35 \text{ J}$$

Thus

$$E_{50} = 12,3 \text{ J}$$

$$s = 1,35 \text{ J}$$

A.2 Method B: group method

EXAMPLE (see Figure 8)

Height of fall: 1 m

Results of pretesting

0 % failure: 0,090 kg

100 % failure: 0,170 kg

Selected steps for main testing and percentage failures:

Mass (kg)	Percent failure
0,105	10
0,120	20
0,135	60

Since $E_{50} = M_{50} \times 9,81 \times H$ (M_{50} in kilograms, H in metres, E_{50} in joules)

Figure 8 gives

$$E_{50} = 0,132 \times 9,81 \times 1 = 1,29 \text{ J}$$

Similarly

$$E_{16} = 0,114 \times 9,81 \times 1 = 1,12 \text{ J}$$

$$E_{84} = 0,153 \times 9,81 \times 1 = 1,50 \text{ J}$$

From which

$$s = \frac{1,50 - 1,12}{2} = 0,19 \text{ J}$$

Thus

$$E_{50} = 1,29 \text{ J}$$

$$s = 0,19 \text{ J}$$

© ISO 2000

ICS 83.080.01

Price based on 21 pages

© ISO 2000 – All rights reserved