

---

---

**Plastics-coated fabrics for upholstery —**  
**Part 1:**  
**Specification for PVC-coated knitted fabrics**

*Supports textiles revêtus de plastique pour ameublement et garniture —*  
*Partie 1: Spécifications des étoffes tricotées revêtues de PVC*



Reference number  
ISO 7617-1:2001(E)

© ISO 2001

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2001

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

**Contents**

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Sampling</b> .....	<b>2</b>
<b>4 Testing and compliance</b> .....	<b>2</b>
<b>5 Technical requirements</b> .....	<b>2</b>
<b>6 Marking</b> .....	<b>6</b>
<b>7 Test report</b> .....	<b>6</b>
<b>Annex A (normative) Method of selecting test specimens</b> .....	<b>7</b>
<b>Annex B (normative) Determination of elongation and elastic recovery</b> .....	<b>10</b>
<b>Annex C (normative) Determination of resistance to print wear</b> .....	<b>12</b>
<b>Annex D (normative) Determination of skin-coat resistance of coated fabrics</b> .....	<b>14</b>
<b>Annex E (normative) Determination of colour fastness to rubbing</b> .....	<b>16</b>
<b>Bibliography</b> .....	<b>17</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 7617 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 7617-1 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 4, *Products (other than hoses)*.

This third edition cancels and replaces the second edition (ISO 7617-1:1994), which has been technically revised.

ISO 7617 consists of the following parts, under the general title *Plastics-coated fabrics for upholstery*:

- *Part 1: Specification for PVC-coated knitted fabrics*
- *Part 2: Specification for PVC-coated woven fabrics*
- *Part 3: Specification for polyurethane-coated woven fabrics*

Annexes A to E form a normative part of this part of ISO 7617.

# Plastics-coated fabrics for upholstery —

## Part 1: Specification for PVC-coated knitted fabrics

### 1 Scope

This part of ISO 7617 specifies technical requirements for coated fabrics for upholstered furniture for interior use, obtained by applying to one side of a weft-knitted base cloth a substantially continuous coating of a suitably plasticized polymer of vinyl chloride, or a copolymer the major constituent of which is vinyl chloride. Such coatings are known as poly(vinyl chloride) (PVC) coatings. The present specification covers fabrics coated with solid PVC and also covers two grades with coatings consisting of a layer of expanded PVC.

### 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 7617. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 7617 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 105-A02:1993, *Textiles — Tests for colour fastness — Part A02: Grey scale for assessing change in colour*

ISO 105-B01:1994, *Textiles — Tests for colour fastness — Part B01: Colour fastness to light: Daylight*

ISO 105-B02:1994, *Textiles — Tests for colour fastness — Part B02: Colour fastness to artificial light: Xenon arc fading lamp test*

ISO 105-X12:2001, *Textiles — Tests for colour fastness — Part X12: Colour fastness to rubbing*

ISO 1419:1995, *Rubber- or plastics-coated fabrics — Accelerated-ageing tests*

ISO 1421:1998, *Rubber- or plastics-coated fabrics — Determination of tensile strength and elongation at break*

ISO 2231:1989, *Rubber- or plastics-coated fabrics — Standard atmospheres for conditioning and testing*

ISO 2286:1998 (all parts), *Rubber- or plastics-coated fabrics — Determination of roll characteristics*

ISO 2411:2000, *Rubber- or plastics-coated fabrics — Determination of coating adhesion*

ISO 3303:1990, *Rubber- or plastics-coated fabrics — Determination of bursting strength*

ISO 5978:1990, *Rubber- or plastics-coated fabrics — Determination of blocking resistance*

ISO 5981:1997, *Rubber- or plastics-coated fabrics — Determination of resistance to combined shear flexing and rubbing*

## ISO 7617-1:2001(E)

ISO 6451:1982, *Plastics coated fabrics — Polyvinyl chloride coatings — Rapid method for checking fusion*

ISO 7854:1995, *Rubber- or plastics-coated fabrics — Determination of resistance to damage by flexing*

### 3 Sampling

If individual rolls can be identified with manufacturing batches, at least one sample shall be taken from each batch in the consignment. Each sample shall be regarded as being representative of its source, and suitable measures shall be taken to preserve the identity between the samples and batch numbers.

If individual rolls cannot be identified in this way, the number of samples to be regarded as being representative of the bulk shall be fixed by agreement between the purchaser and the supplier. Such samples shall be drawn at random.

### 4 Testing and compliance

Samples shall first be subjected to the preliminary examination described in 5.1, which enables grossly defective coated fabrics to be rejected immediately. If the samples satisfy this examination, testing shall be continued as follows:

Tests shall be carried out on a set of test specimens selected from each sample in accordance with annex A. If testing shows that the test specimens comply with the requirements of Tables 1 to 4, the bulk of the coated fabric represented by the sample shall be deemed to comply with the requirements of this part of ISO 7617.

If any of the specimens tested do not comply with any of the appropriate requirements given in Tables 1 to 4, the tests which the specimens have failed shall be repeated twice. For this purpose, two further samples shall be taken from the same source as the original sample, and test specimens shall be taken from each sample so that duplicate tests may be conducted. If all the re-test results comply with the appropriate requirements of Tables 1 to 4, then the bulk represented by the samples from which the specimens for re-testing were taken, together with the original samples, shall be deemed to comply with the requirements of this part of ISO 7617. If any of the results of the re-tests do not comply with the appropriate requirements of Tables 1 to 4, then the bulk represented by those samples shall be deemed not to comply with the requirements of this part of ISO 7617.

### 5 Technical requirements

#### 5.1 Preliminary inspection

##### 5.1.1 General

A preliminary inspection shall be carried out as specified in 5.1.2 and 5.1.3, before conducting a detailed examination and expensive tests, in order to ensure that the samples do not exhibit easily detectable unacceptable faults. If such faults are detected, the inspection shall be stopped and the sample shall be considered as not complying with the requirements of this part of ISO 7617. This shall be stated in the test report.

##### 5.1.2 Visual inspection

The coating shall be uniformly applied and shall be free of visible flaws or cracks. Indicated local flaws are admitted, but no test specimen shall be cut less than 5 cm from the flaw.

When examined under a magnification of  $\times 6$ , the coating shall be substantially free of pinholes. Carry out the inspection by examining 10 areas, each measuring 2 cm  $\times$  2 cm, evenly distributed over the usable width and length of the sample. The mean pinhole density shall not be more than 10 per square decimetre (i.e. 2,5 times the total count shall be  $< 10$ ). This requirement does not apply to products stated to be microperforated.

NOTE 1 Products which are stated to be microperforated will normally be provided with special cleaning instructions.

Unless the coating is intentionally transparent, the knitted base fabric shall not be visible through the coating. Its profile shall also not be visible, either when the coated fabric is slack or when a slight tension is applied by hand. Its presence shall also not be apparent by virtue of any printing or surface lacquer which may be present. If the base fabric is visible in any of these ways, testing may be continued, but the visibility of the base fabric shall be reported in the test report.

NOTE 2 It is possible that the surface is marked with the pattern of the back surface if the roll has been wound too tight. Such marks are reversible and acceptable. They can be easily identified by heating a piece of coated fabric for a few minutes in an oven at a temperature around 100 °C: the marking due to tight winding disappears.

It shall be possible to bend the coated fabric through an angle of 180°, with its coated face outwards, without any noticeable whitening. If whitening appears, testing may be continued, but the appearance of the whitening shall be reported in the test report.

### 5.1.3 Fusion

Verify the state of fusion of the coating to the base fabric in accordance with ISO 6451. Stop testing if the components are not fused together satisfactorily.

## 5.2 Colour, embossing and finish

The quality of the colour, embossing and finish of the coated fabric, whether the material is plain or multicoloured, shall be subject to agreement between the customer and supplier. This agreement shall be based on a reference sample, and on illustrations or other ways of indicating acceptable deviations from the reference sample.

Comparison of colours shall be carried out in accordance with ISO 105-B01.

NOTE 1 Instrumental measurement of the colour difference between a specimen and the agreed reference sample may be performed, if agreed between the interested parties. However, it should be pointed out that such methods are not without problems. The result is influenced by the gloss and the state of the surface of the coated fabric. In addition, the presence of embossing and small differences in gloss induce variations, which can be large, in the results, while the colour itself remains the same. The use of a spectrophotometer equipped with an integrating sphere is mandatory but allows these variations to be only partly eliminated. It is recommended therefore that, before carrying out any instrumental colour measurements on unknown samples, the interested parties conduct comparative trials in order to determine precisely the optimum conditions of measurement and to define tolerances, using samples which have already been adjudged acceptable or not by examination in accordance with ISO 105-B01.

NOTE 2 Gloss can be evaluated by means of a glossmeter or reflectometer, which measures specular reflection. The sensitivity of such an apparatus will vary with the angle of incidence, to an extent depending on the degree of gloss or dullness: 20°, 60° and 85° are the angles of incidence normally selected for glossy, semiglossy and matt coated fabrics. However, sensitivity is poor for highly matt materials. Moreover, reflection can vary noticeably from place to place on the surface depending on the embossing pattern. Bearing these reservations in mind and the fact that response can vary from one apparatus to another, parties which decide to evaluate gloss in this manner should preferably verify, in advance, the reproducibility of the apparatus used for the coated fabrics to be tested.

## 5.3 Dimensions

### 5.3.1 Usable width

The usable width of the coated fabric, measured in accordance with ISO 2286-1, shall be as agreed between purchaser and supplier. For this purpose, the term "usable width" shall refer to the width that has received a coating complying with the requirements of 5.1. (See also the note to 5.3.2.)

### 5.3.2 Length of coated fabric in a roll

The length of material in a roll, measured in accordance with ISO 2286-1, shall be as agreed between purchaser and supplier, including selected lengths and accepted tolerances.

NOTE When, exceptionally, the coated fabric is supplied as pre-cut pieces, the concepts of length and width become meaningless. In this case, the shape and dimensions of the pieces, as well as the tolerances on the dimensions, should preferably be defined by agreement between purchaser and supplier. It is recommended that the agreement include a scale drawing.

**5.3.3 Thickness**

The thickness of the coated fabric, measured in accordance with ISO 2286-3 under a pressure of 2 kPa, shall comply with the requirements of Table 1.

**5.4 Physical requirements**

**5.4.1 Mass of coating per unit area**

The mass of coating per unit area, measured in accordance with ISO 2286-2, shall comply with the requirements of Table 1.

**5.4.2 Mechanical properties**

The coated fabric shall comply with the requirements of Table 2.

**5.4.3 Surface properties**

The coated fabric shall comply with the requirements of Table 3.

**5.4.4 Properties after ageing**

After accelerated ageing for 168 h at 85 °C under the conditions described in ISO 1419:1995, method 1, the coated fabric shall comply with the requirements of Table 4.

**5.4.5 Fire behaviour**

The fire behaviour of the coated fabric shall comply with any existing local or national regulations.

NOTE It is not possible to specify *a priori* performance requirements for fire behaviour: finished items, which are made up of coated fabrics and include various fillings and structures, have to fulfil risk requirements. These risks depend directly on the place and environment of use. However, it is strongly recommended that manufacturers of coated fabrics give the users information regarding fire behaviour so that they may manufacture furnishings responding as well as possible to safety regulation requirements.

**Table 1 — Thickness of coated fabric and mass of coating per unit area**

Property	Unit	Solid coating	Slightly expanded coating	Expanded coating	Test method
Total mass of coating per unit area	g/m <sup>2</sup>	≥ 480	≥ 480	≥ 600	ISO 2286-2
Thickness of coated fabric (nominal)	mm	0,75 to 1,0	0,85 to 1,15	1,10 to 1,40	ISO 2286-3
Tolerance on thickness	mm	± 0,07	± 0,10	± 0,15	



Table 2 — Mechanical-property requirements

Property	Unit	Solid coating	Slightly expanded coating	Expanded coating	Test method
Tensile strength	N				
Longitudinal		≥ 250	≥ 250	≥ 250	ISO 1421:1995, method 1
Transverse		≥ 150	≥ 150	≥ 150	
Elongation at break	%				
Longitudinal		≥ 50	≥ 50	≥ 50	ISO 1421:1995, method 1
Transverse		≥ 100	≥ 100	≥ 100	
Bursting strength	kPa	≥ 700	≥ 400	≥ 700	ISO 3303:1990, method B
Elongation (static)	%				
Longitudinal		≥ 5	≥ 12	≥ 8	Annex B
Transverse		≥ 35	≥ 80	≥ 70	
Elastic recovery	%				
Longitudinal		≥ 80	≥ 80	≥ 80	Annex B
Transverse		≥ 80	≥ 80	≥ 80	
Resistance to flexing	cycles	≥ 400 000	≥ 400 000	≥ 400 000	ISO 7854:1995, method B
or					
shear flexing and rubbing	strokes	≥ 50 000	≥ 50 000	≥ 50 000	ISO 5981:1997, method 2
Abrasion resistance <sup>a</sup>	cycles	≥ 700	≥ 700	≥ 700	Annex D
Coating adhesion	N				
Longitudinal		≥ 30	≥ 30	≥ 30	ISO 2411
Transverse		≥ 20	≥ 20	≥ 20	

<sup>a</sup> Number of cycles without exposure of an intermediate layer under the outer skin.

Table 3 — Surface properties

Property	Test method	Solid coating	Slightly expanded coating	Expanded coating
Print wear	Annex C	≥ 3	≥ 3	≥ 3
Colour fastness to light	ISO 105-B02	≥ 6	≥ 6	≥ 6
Colour fastness to dry rubbing	Annex E	≥ (4 to 5)	≥ (4 to 5)	≥ (4 to 5)
Colour fastness to wet rubbing	Annex E	≥ (4 to 5)	≥ (4 to 5)	≥ (4 to 5)
Colour fastness to rubbing with soapy water <sup>a</sup>	Annex E	≥ (4 to 5)	≥ (4 to 5)	≥ (4 to 5)
Blocking resistance	ISO 5978	Separation without surface damage		

<sup>a</sup> Same conditions as for wet rubbing, but replacing water by a 4 % aqueous solution of soap.

Table 4 — Properties after ageing

Property	Unit	Solid coating	Slightly expanded coating	Expanded coating	Test method
Resistance to flexing	cycles	≥ 400 000	≥ 400 000	≥ 300 000	ISO 7854:1995, method B
Resistance to shear flexing and rubbing	strokes	≥ 50 000	≥ 50 000	≥ 50 000	ISO 5981:1997, method 2

## 6 Marking

Each roll of coated fabric shall be supplied with a label with the following information:

- a) the name and/or trade mark of the manufacturer, and all details necessary for identification of the coated fabric;
- b) the grade of coated fabric: coating solid, slightly expanded or expanded;
- c) the roll number, and the batch number if this is necessary to trace the coated fabric;
- d) the colour;
- e) the length of coated fabric in the roll;
- f) the usable width;
- g) a reference to this part of ISO 7617 (i.e. ISO 7617-1).

## 7 Test report


The test report shall include at least the following:

- a) a reference to this part of ISO 7617 (i.e. ISO 7617-1);
- b) all details necessary for complete identification of the coated fabric tested;
- c) the grade of coated fabric (solid, slightly expanded or expanded coating);
- d) all details necessary for identification of the testing authority;
- e) an indication of compliance or non-compliance with this part of ISO 7617, and in the latter case a clear indication of the property or properties which led to non-compliance;
- f) details of the results obtained for the tests specified in 5.4.1, 5.4.2, 5.4.3 and 5.4.4;
- g) any observations resulting from the examinations specified in 5.1 and 5.2;
- h) the usable width of the coated fabric and the length of coated fabric in the rolls, as determined in 5.3.1 and 5.3.2;
- i) the thickness of the coated fabric as determined in 5.3.3;
- j) details of any deviations from the specified procedures, as well as any additional observations which may have a bearing on the results.

## Annex A (normative)

### Method of selecting test specimens

Test specimens shall be selected from the sample in accordance with the scheme illustrated in Figure A.1, which shows the positions from which the specimens for each type of test shall be taken. Specimens for the preliminary inspection and the assessment of appearance shall be taken from an area outside that reserved for the other specimens, except that the visual inspection using a  $\times 6$  lens for the detection of pinholes (see 5.1.2) shall be made in the diagonal area indicated. Specimens required for colour-fastness testing shall, if possible, include all colours present. If this is impossible, specimens shall be taken in such a way that each colour is included in at least two specimens. The position of such specimens are not critical, and they may be taken at any suitable position across the usable width.

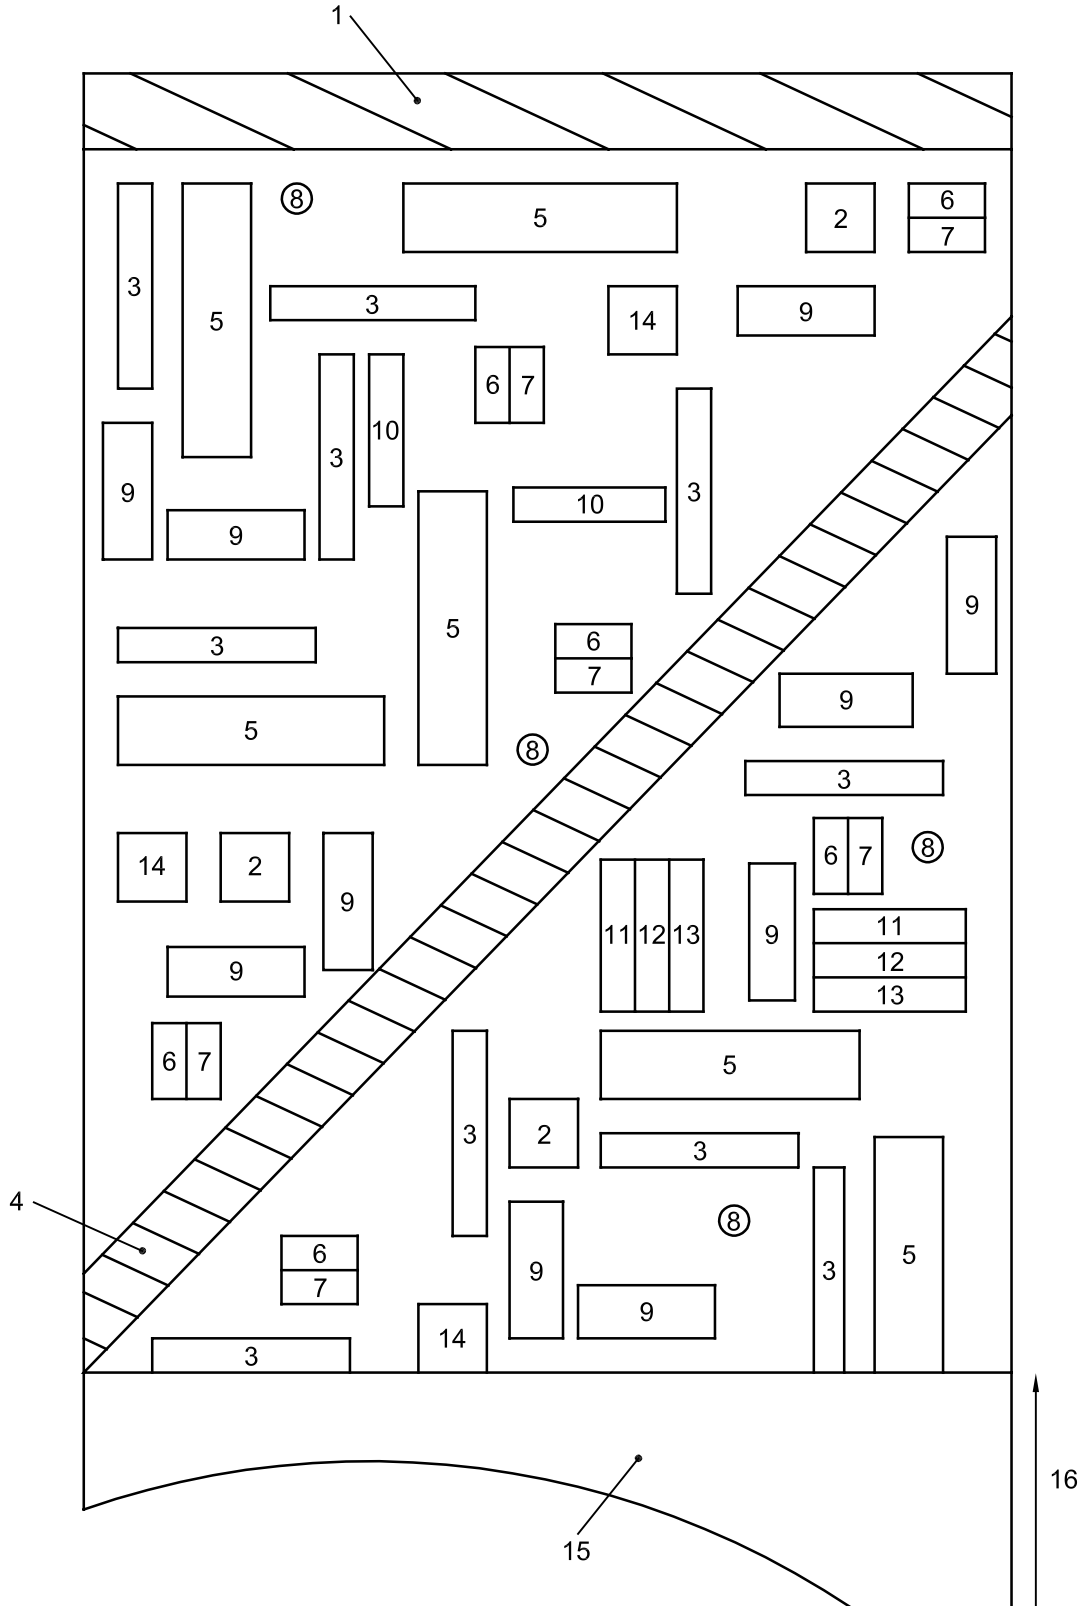

**Key**

- |   |                                                      |    |                                             |
|---|------------------------------------------------------|----|---------------------------------------------|
| 1 | Thickness determination                              | 9  | Coating adhesion                            |
| 2 | Mass of coating per unit area                        | 10 | Print wear                                  |
| 3 | Tensile strength and elongation at break             | 11 | Colour fastness to dry rubbing              |
| 4 | Bursting strength and inspection for pinholes        | 12 | Colour fastness to wet rubbing              |
| 5 | Elongation under constant load and elastic recovery  | 13 | Colour fastness to rubbing with soapy water |
| 6 | Flexing (or shear flexing and rubbing) before ageing | 14 | Blocking resistance                         |
| 7 | Flexing (or shear flexing and rubbing) after ageing  | 15 | Preliminary inspection and appearance       |
| 8 | Abrasion                                             | 16 | Longitudinal (machine) direction            |

**Figure A.1 — Scheme for selection of test specimens**

## Annex B (normative)

### Determination of elongation and elastic recovery

#### B.1 General

When subjected to a constant tensile load for a given length of time, a coated fabric stretches. When the load is removed, the coated fabric tends to come back to its initial length. In practice, the visco-elastic characteristics of plasticized PVC result in a permanent residual elongation, the magnitude of which depends upon many factors such as the size of the applied load, the duration of loading, the width over which the load is applied, the elasticity of the coated fabric, the temperature and humidity during the test, and the time allowed for recovery after removal of the load. A seat covering should have good elasticity, and therefore a small permanent elongation in use.

The permanent elongation, expressed in absolute units, does not give a useful measure of the elasticity of a coated fabric. Expressing the permanent elongation as a percentage of the initial elongation gives a better measure. However, it is preferred to express it as that portion of the initial elongation which is recovered during the relaxation period. This parameter is known as the elastic recovery.

A test length of 200 mm is enough in most cases to give sufficient accuracy. For low-extensibility coated fabrics, it may be necessary to increase the test length. If so, the test length shall be reported in the test report. The calculation shall be modified accordingly.

#### B.2 Apparatus

**B.2.1 Two grips**, capable of clamping 10-cm-wide test specimens. One grip (the upper grip) shall be capable of being attached to a rigid frame in such a way that, when a specimen is centered in the grip and clamped with the jaws of the grip running across the specimen, the specimen hangs in the vertical plane. The other (lower) grip shall be designed so that weightpieces can be added to bring its mass up to a total of 10 kg. The height of the frame shall be such that the loaded specimen can extend freely without touching the floor or lab bench.

**B.2.2 Ruler**, readable to the nearest 0,5 mm, or an equivalent device.

#### B.3 Test specimens

Cut out three test specimens measuring 400 mm × 100 mm with their length in the longitudinal direction and another three specimens with their length in the transverse direction, in accordance with the scheme in annex A. Mark the specimens accordingly.

#### B.4 Procedure

Condition the test specimens in one of the atmospheres defined in ISO 2231. Tests shall be carried out in the same atmosphere.

Draw two fine lines across each test specimen, at right angles to its longest dimension, 100 mm from each end and 200 mm apart. Draw a third line, perpendicular to the two others, to cut them in their mid-point. Make all measurements along this line.

Insert a specimen centered in the upper grip, with the line at the upper end not less than 50 mm from the jaws. Insert the other end in the lower grip in the same way. Attach the upper grip to the frame.

Apply smoothly to the lower grip a weightpiece that will bring the total mass of the lower grip to 10 kg and note the time. After 10 min, measure and note the distance  $L_1$  between the two lines to the nearest 0,5 mm.

Remove the load and withdraw the specimen from the grips. Place it on a flat, horizontal surface. After 10 min, measure and note the distance  $L_2$  between the two lines to the nearest 0,5 mm.

Repeat the procedure with the remaining specimens.

## B.5 Expression of results

**B.5.1** The elongation, expressed as a percentage of the initial distance between the lines, is given by the formula

$$\left( \frac{L_1 - 200}{200} \right) \times 100$$

where  $L_1$  is the distance, in mm, between the lines after extension under constant load.

**B.5.2** The elastic recovery, expressed as a percentage, is given by the formula

$$\left( \frac{L_2 - L_1}{L_1 - 200} \right) \times 100$$

where  $L_2$  is the distance, in mm, between the lines after recovery.

**B.5.3** Calculate the elongation and the elastic recovery for each test specimen and report the mean for the set of three specimens in each direction to the nearest 0,5 %. Report the test conditions if they differ from those in the procedure above (for example in relation to specimen length).

## Annex C (normative)

### Determination of resistance to print wear

#### C.1 Principle

A specimen is subjected to 500 cycles of simple harmonic abrasion using a known abradant under a known pressure. It is then assessed for colour difference with an unabraded portion using the grey scale for assessing change in colour.

#### C.2 Apparatus

The apparatus shall be as described in ISO 105-X12, but with the following modifications:

- a) The force applied to the rubbing finger shall be such that the equivalent of a total mass of 1 500 g is brought to bear on the specimen.
- b) The frequency of operation of the apparatus shall be 0,25 Hz (i.e. 0,5 strokes per second: each cycle comprises one outward stroke and one return stroke).
- c) Use as the abradant a cotton fabric which has been desized, scoured and bleached, is free from fluorescent brightening agents, and has a pH of aqueous extract not greater than 8, a mass per unit area of 93 g/m<sup>2</sup> and a construction of 40 ends/cm, 39 picks/cm, 11,4 tex warp and 9,2 tex weft in plain weave.
- d) Grey scale for assessing change in colour (see ISO 105-A02).

#### C.3 Test specimens

Cut out two specimens of coated fabric, each measuring 230 mm × 50 mm, one with its length parallel to the longitudinal direction of the sample and the other with its length parallel to the transverse direction. Also cut out two circular pieces of the bleached cotton fabric, each 30 mm in diameter, avoiding lumps and neps.

NOTE Initially, four pieces of cotton fabric abradant can be cut out and a double thickness of cotton cloth mounted on the rubbing finger, so that only the outermost layer coming into contact with the test specimen needs to be renewed at each test.

#### C.4 Procedure

Condition the test specimens and cotton fabric in accordance with ISO 2231.

Using the clamps, mount a test specimen securely on the bed of the machine with the coated side uppermost and under sufficient tension to hold the specimen flat. To do this with coated fabrics having a knitted base cloth, it has been found necessary to stretch the specimen approximately 9 %.

Wipe the coated surface of the specimen with a clean, dry cloth to remove dust before testing.

Secure the conditioned cotton fabric to the base of the rubbing finger, making sure that the sateen face is presented to the specimen under test, i.e. with the ribbed side of the cotton fabric in contact with the finger. Lower the finger on to the specimen and run the machine for 500 cycles. Repeat the procedure using the second specimen and second piece of cotton fabric.



Assess the degree of surface print wear on the specimens, using the grey scale as comparator in accordance with ISO 105-A02. If one specimen exhibits greater print wear than the other, the worse result of the two shall be taken as the test result.

### **C.5 Expression of results**

Report the change in colour between the abraded and unabraded portions of the test specimen by reference to the grey scale for assessing change in colour.

.....

## Annex D (normative)

### Determination of skin-coat resistance of coated fabrics

#### D.1 Scope

This test is applicable to plastics-coated fabrics which have an expanded intermediate layer. It is also applicable to fabrics with solid plastics coatings which comprise an intermediate layer which can be visually distinguished from the skin coat. It is meaningless for materials the coating of which is either homogeneous or consists of indistinguishable layers.

#### D.2 Apparatus

**D.2.1 Test machine**, of the Martindale type, largely as described in reference [1] (see the bibliography), and fulfilling the following requirements:

Rotational frequency of each of the outer pegs	(47,5 ± 2,5) r/min
Ratio of speeds (outer pegs:inner pegs)	32:30
Total stroke of outer pegs	60,5 mm
Total stroke of inner pegs	60,5 mm
Working area of specimen holder	645 mm <sup>2</sup>
Pressure on specimen	9,05 kPa

The specimen holders and abrading tables shall be plane and parallel over their entire surface. The drive from the motor to the machine shall be connected to a counter and switch so that the revolutions of the outer pegs are indicated and the machine is stopped after a predetermined number of rubs.

**D.2.2 Abradant**, consisting of grade P180 silicon carbide paper.

**D.2.3 Stiff nylon clothes brush**.

#### D.3 Test specimens

Cut or punch four circular specimens, each 38,0 mm in diameter, from the coated fabric under test. The specimens shall be disposed uniformly throughout the available material excluding selvages.

#### D.4 Procedure

##### D.4.1 Conditioning

Condition the specimens in accordance with ISO 2231.

#### D.4.2 Verification of machine

Verify that the test machine is in good working order as indicated below. In particular, if one of the four heads gives persistently different results from the others, examine it and correct the fault or faults.

The abrasion machine shall be mounted on a firm, level table. The three cups and steel balls shall be cleaned and well lubricated with thin oil.

The stem of each specimen holder shall fit freely but without play in its bracket, and shall be lubricated to avoid unidirectional abrasion.

It is of the greatest importance that the specimen holders be parallel with the flat steel abrading tables. If they are not, most of the wear will take place at the edges of the specimens. Parallelism shall be checked after assembly and at regular intervals. One method of doing this is as follows: without fabric in the specimen holders or table mounts and with each specimen holder in position on the brass plate, it shall not be possible to push a 0,025 mm feeler gauge between the specimen holder and table at any point.

This check shall be carried out for several positions of the specimen holder. If the check shows the machine to be in error, it may be due to one of the following:

- a) a bent specimen holder spindle;
- b) imperfect seating of the specimen holder bracket which is clamped to the brass plate;
- c) non-parallelism of the abrading table with the plane of movement of the brass plate.

If c) is the case, the fault shall be remedied in the following way. After removing the driving pins from the three driving discs, clamp a dial indicator in place of the specimen holder bracket so that the stem moves over the abrading table as the brass plate is moved by hand. Should the gauge readings deviate more than 0,05 mm over the entire surface of the table, loosen the screws fixing the table to the base, pack strips of thin paper or metal shims where required, retighten the screws and check again.

#### D.4.3 Determination

Mount the four circular specimens (see D.3), one in each specimen holder. The specimens shall be mounted under tension by pressing the holder down against the metal plate provided on the base of the machine (D.2.1), and tightening by screwing. Cut out four new pieces of abradant (D.2.2), each measuring 125 mm × 125 mm, and mount one on each of the four tables. The abradant shall be mounted under slight tension by placing a weightpiece on the surface of the square of abradant before tightening up the metal frame. Clamp the circular specimen holders on the moving plate under the specified load and switch on the machine. Replace the squares of abradant by new pieces at the start of each test.

Care shall be taken when mounting or examining the specimens that they do not catch against the metal parts of the machine. If this happens, discard the specimen and prepare a fresh one.

Continue testing for the minimum number of cycles specified in Table 2, but at intervals of 200 cycles clean the abradant by brushing with the brush (D.2.3) and blowing. No abradant shall be used for more than 1 000 cycles.

#### D.5 Expression of results

After the specified number of cycles, assess the state of the abraded area by observing it through a 50 mm disc of card in which a 15-mm-diameter hole has been punched, the mask being put on the test specimen, centered over the test head.

Report any exposure of the cellular (or solid intermediate) layer.

**Annex E**  
(normative)

**Determination of colour fastness to rubbing**

The method of test shall be as specified in ISO 105-X12:1993 but with the following changes:

- a) the frequency of operation of the apparatus shall be 0,25 Hz (i.e. 0,5 strokes per second: each cycle comprises one outward stroke and one return stroke);
- b) the number of strokes shall be 20 (10 outward and 10 return);
- c) the rubbing of the fabric shall be carried out as specified in annex C of this part of ISO 7617.

© ISO 2001 – All rights reserved

## Bibliography

- [1] MARTINDALE, *J. Text. Ins.*, **33** (1942), T 151

© ISO 2004. All rights reserved.

---

---

**ICS 59.080.40; 97.140**

Price based on 17 pages

© ISO 2001 – All rights reserved