

INTERNATIONAL
STANDARD

ISO
9302

Second edition
1994-02-15

**Seamless and welded (except submerged
arc-welded) steel tubes for pressure
purposes — Electromagnetic testing for
verification of hydraulic leak-tightness**

*Tubes en acier sans soudure et soudés (sauf à l'arc immergé) pour service
sous pression — Contrôle électromagnétique pour vérification de
l'étanchéité*



Reference number
ISO 9302:1994(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 9302 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 19, *Technical delivery conditions for steel tubes for pressure purposes*.

Annexes A and B of this International Standard are for information only.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Seamless and welded (except submerged arc-welded) steel tubes for pressure purposes — Electromagnetic testing for verification of hydraulic leak-tightness

1 Scope

This International Standard specifies requirements for electromagnetic testing of seamless and welded tubes (ferromagnetic steels), for pressure purposes, with the exception of submerged arc-welded (SAW) tubes, for verification of hydraulic leak-tightness. It is applicable to the inspection of tubes with an outside diameter greater than or equal to 4 mm.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 235:1980, *Parallel shank jobber and stub series drills and Morse taper shank drills.*

ISO 286-2:1988, *ISO system of limits and fits — Part 2: Tables of standard tolerance grades and limit deviations for holes and shafts.*

ISO 4200:1991, *Plain end steel tubes, welded and seamless — General tables of dimensions and masses per unit length.*

ISO 11484:—¹⁾, *Steel tubes for pressure purposes — Qualification and certification of non-destructive testing (NDT) personnel.*

1) To be published.

3 General requirements

3.1 The electromagnetic inspection covered by this International Standard is usually carried out on tubes after completion of all the primary production process operations.

This inspection shall be carried out by personnel certificated in accordance with ISO 11484, as nominated by the manufacturer. In the case of third-party inspection, this shall be agreed between the purchaser and manufacturer.

3.2 The tubes to be tested shall be sufficiently straight to ensure the validity of the test. The surfaces shall be sufficiently free from foreign matter which would interfere with the validity of the test.


4 Method of test

4.1 The tubes shall be tested for verification of hydraulic leaktightness using a concentric coil or a rotating tube/pancake coil eddy current technique, or a rotating tube/magnetic transducer flux leakage technique. See figures 1 to 3.

NOTES


1 It is recognized that there is a short length at both tube ends which may not be able to be tested.

2 Guidance notes on limitations associated with the eddy current test method and the magnetic transducer/flux leakage technique are given in annexes A and B respectively.

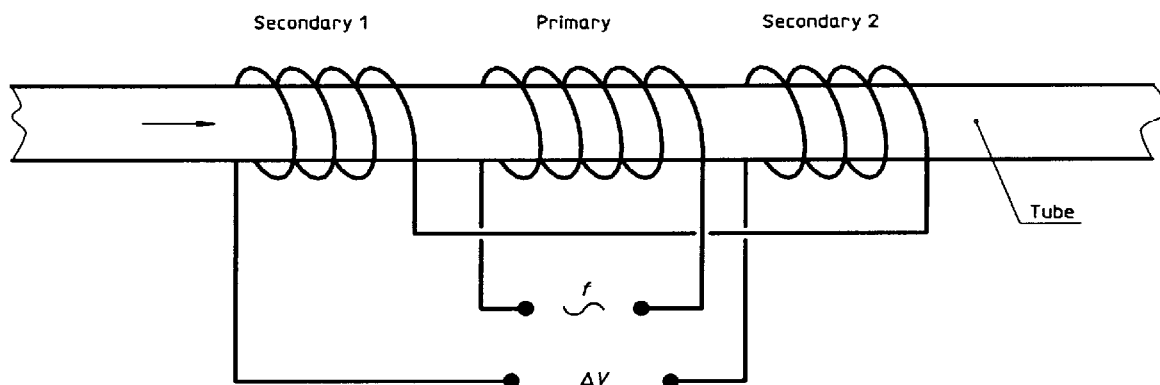

NOTE — The above diagram is a simplified form of a multi-coil arrangement which may contain, for example, split primary coils, twin differential coils, calibrator coil, etc.

Figure 1 — Simplified diagram of concentric coil eddy current technique

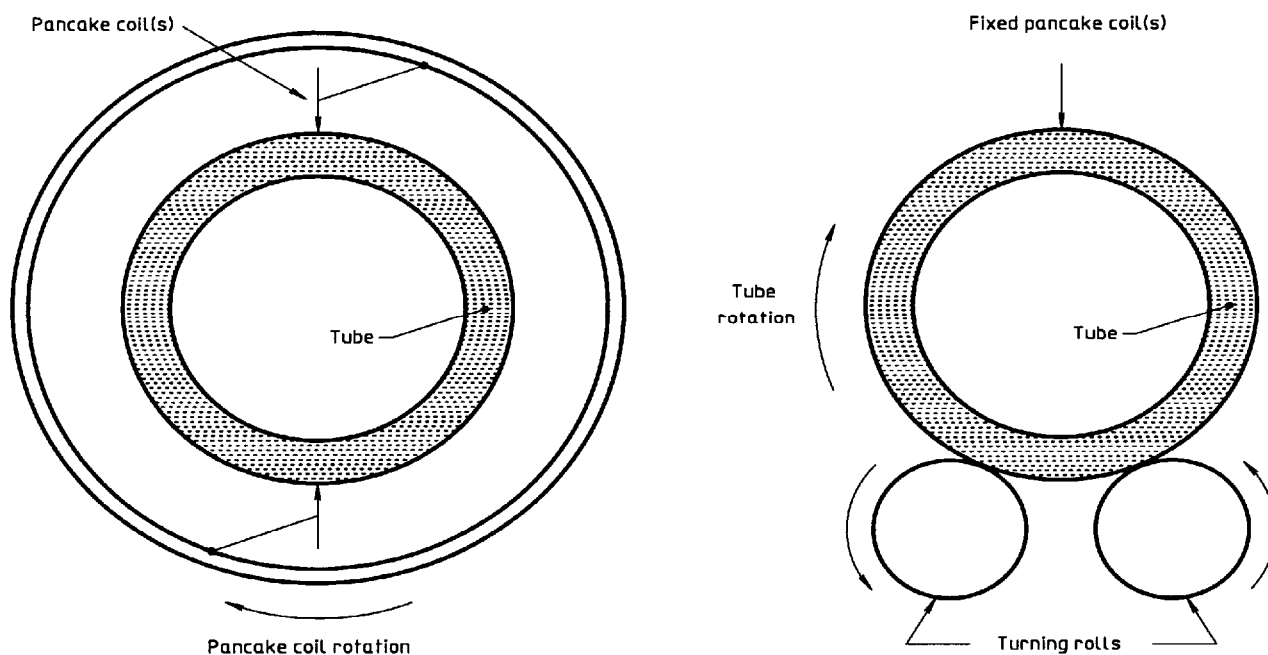


a) Rotating pancake coil technique (linear tube movement through the rotating pancake coil assembly)


b) Rotating tube technique (linear pancake coil traverse along the tube length)

NOTE — The pancake coils used in a) and b) above take many forms, for example, single coil, multi-coil of various configurations, depending on the equipment used and other factors.

Figure 2 — Simplified diagram of rotating tube/pancake coil eddy current technique (helical scan)

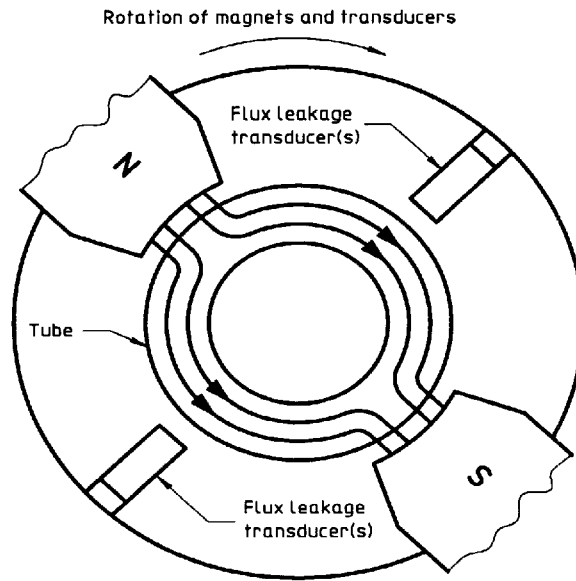

a) Rotating magnetic transducer technique (rotating magnets and transducers)

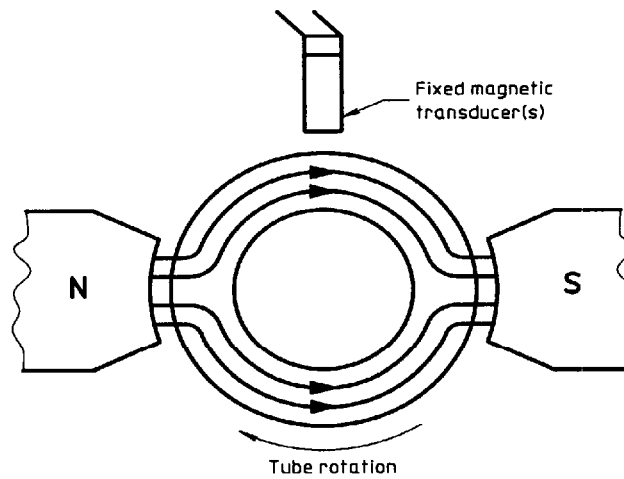

b) Rotating tube technique [(fixed magnets and magnetic transducer(s))]

NOTE — The magnetic transducers used in a) and b) above may take many forms, for example absolute, differential, multidifferential, etc., depending on the equipment used and other factors.

Figure 3 — Simplified diagram of rotating tube/magnetic transducer flux leakage technique

4.1.1 When testing seamless or welded tubes using the eddy current concentric coil technique, the maximum outside diameter of tube to be tested is restricted to 177,8 mm.

4.1.2 When testing seamless or welded tubes using the rotating tube/pancake coil eddy current technique or rotating tube/magnetic transducer flux leakage technique, the tube and/or the pancake coils/magnetic transducers shall be moved relative to each other so that the whole of the tube surface is scanned. There is no restriction on the maximum outside diameter using these techniques.

4.2 The equipment for automatic testing shall be capable of differentiating between acceptable and suspect tubes by means of an automatic trigger/alarm level combined with a marking and/or sorting system.

5.4 When using the eddy current concentric coil technique, the test piece shall contain three circular holes, drilled radially through the full thickness of the test piece. The three holes shall be circumferentially displaced 120° from each other, and shall be sufficiently separated longitudinally and from the extremities of the test pieces so that clearly distinguishable signal indications are obtained.

Alternatively, only one hole shall be drilled radially through the full thickness of the test piece, and during calibration and calibration checking the test piece shall be passed through the equipment with the hole positioned at 0°, 90°, 180° and 270°.

The diameter of the drill required to produce these holes depends on the tube outside diameter as shown in table 1.

The diameter of the reference hole or reference holes shall be verified and shall not exceed the specified drill diameter by more than 0,2 mm.

5 Reference standards

5.1 The reference standards defined in this International Standard are convenient standards for calibration of non-destructive testing equipment. The dimensions of these standards should not be construed as the minimum size of imperfection detectable by such equipment.

5.2 The testing equipment shall be calibrated using reference standards introduced into a tubular test piece. The test piece shall be of the same nominal diameter, thickness and surface finish as the tube to be tested and shall have similar electromagnetic properties.

NOTE 3 In special cases, for example testing hot tubes, a modified testing procedure can be used where it can be demonstrated that the calibration parameters are at least equivalent to the electromagnetic condition of the tubes under test.

5.3 The reference standards for the various testing techniques shall be as follows:

- a) a reference hole or reference holes as defined in 5.4 when using the eddy current concentric coil technique;
- b) a reference notch as defined in 5.5 when using the rotating tube/pancake coil eddy current technique or the rotating tube/magnetic transducer flux leakage technique.

Table 1

| Tube outside diameter <i>D</i> ¹⁾ mm | Drill diameter ²⁾ mm |
|--|------------------------------------|
| $D \leq 26,9$ | 1,20 |
| $26,9 < D \leq 48,3$ | 1,70 |
| $48,3 < D \leq 63,5$ | 2,20 |
| $63,5 < D \leq 114,3$ | 2,70 |
| $114,3 < D \leq 139,7$ | 3,20 |
| $139,7 < D \leq 177,8$ | 3,70 |

1) See ISO 4200.
2) Tolerances according to ISO 235 (jobber series) and ISO 286-2 (h8).

5.5 When using the rotating tube/pancake coil eddy current technique, or rotating tube/magnetic transducer flux leakage technique, the test piece shall contain a longitudinal reference notch on the external surface.

5.5.1 The reference notch shall be sufficiently separated from the extremities of the test piece, so that a clearly distinguishable signal indication is obtained.

5.5.2 The reference notch shall be of the "N" type (see figure 4) and shall lie parallel to the major axis of the tube. The sides shall be nominally parallel and the bottom shall be nominally square to the sides.

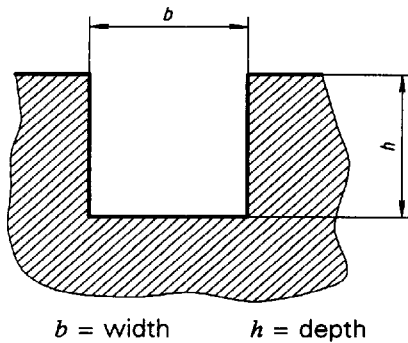


Figure 4 — "N"-type notch

5.5.3 The reference notch shall be formed by machining, spark erosion or other methods.

NOTE 4 It is recognized that the bottom or the bottom corners of the notch may be rounded.

6 Dimensions of reference notch

The dimensions of the reference notch shall be as follows.

6.1 Length

50 mm minimum (at full depth) or a minimum of twice the width of each individual transducer.

6.2 Width, b (see figure 4)

Not greater than the reference notch depth.

6.3 Depth, h (see figure 4)

12,5 % of the specified thickness with the following limitations:

- Minimum depth: 0,5 mm
- Maximum depth: 1,5 mm

6.4 Tolerance on depth, h

$\pm 15\%$ of reference notch depth or $\pm 0,05$ mm, whichever is the larger.

6.5 Verification

The reference notch dimensions and shape shall be verified by a suitable technique.

7 Equipment calibration and checking

7.1 The equipment shall be adjusted to consistently produce, to the satisfaction of the purchaser, clearly identifiable signals from the reference standard(s). These signals shall be used to set the trigger/alarm level of the equipment.

When using multiple reference holes in the test piece (concentric coil eddy current technique), the full amplitude obtained from the reference hole giving the smallest signal shall be used to set the trigger/alarm level of the equipment. When using a single reference hole in the test piece, the test piece shall be passed through the inspection equipment with the reference hole, on successive runs, positioned at 0° , 90° , 180° and 270° and the full amplitude of the smallest signal obtained from the reference hole shall be used to set the trigger/alarm level of the equipment.

When using the reference notch (rotating tube/pancake coil eddy current technique or rotating tube/magnetic transducer flux leakage technique), the full signal amplitude shall be used to set the trigger/alarm level of the equipment.

7.2 During calibration, the relative speed of movement between the test piece and the test coils shall be the same as that to be used during the production test. The same equipment settings, for example frequency, sensitivity, phase discrimination, rate filtering, magnetic saturation, etc., shall be employed.

7.3 The calibration of the equipment shall be checked at regular intervals during the production testing of tubes of the same diameter, thickness and grade, by passing the test piece through the inspection equipment.

The frequency of checking the calibration shall be at least every 4 h; but also whenever there is an equipment operator changeover and at the start and end of the production run.

NOTE 5 In cases where a production testing run is continuous from one shift period to the next, the 4 h maximum period may be extended by agreement between purchaser and manufacturer.

7.4 The equipment shall be recalibrated following any system adjustments or whenever the specified nominal tube diameter, thickness, type or grade of steel is changed.

7.5 If, on checking during production testing, the calibration requirements are not satisfied, even after increasing the test sensitivity by 3 dB to allow for system drift, then all tubes tested since the previous check shall be retested after the equipment has been recalibrated.

Retesting shall not be necessary even after a drop in test sensitivity of more than 3 dB since the previous calibration, provided that suitable recording from individually identifiable tubes are available which permit accurate classification into suspect and acceptable categories.

8 Acceptance

8.1 Any tube producing signals lower than the trigger/alarm level shall be deemed to have passed this test.

8.2 Any tube producing signals equal to or greater than the trigger/alarm level shall be designated suspect or, at the manufacturer's option, may be retested as specified above.

8.3 If, on retesting, no signal is obtained equal to or greater than the trigger/alarm level, the tube shall be deemed to have passed this test.

Tubes giving signals equal to or greater than the trigger/alarm level shall be designated suspect.

8.4 For suspect tubes, one or more of the following actions shall be taken, subject to the requirements of the product standard:

- a) The suspect area shall be explored by dressing using an acceptable method. After checking that the remaining thickness is within tolerance, the tube shall be retested as previously specified. If no signals are obtained equal to or greater than the trigger/alarm level, the tube shall be deemed to have passed this test.

The suspect area may be retested by other non-destructive techniques and test methods, by agreement between purchaser and manufacturer to agreed acceptance levels.

- b) Each suspect tube shall be subjected to a hydraulic leak-tightness test in accordance with the relevant product standard, unless otherwise agreed between the purchaser and manufacturer.
- c) The suspect area shall be cropped off. The manufacturer shall ensure to the satisfaction of the purchaser that all the suspect area has been removed.
- d) The tube shall be deemed not to have passed the test.

9 Test report

When specified, the manufacturer shall submit to the purchaser a test report that includes, at least, the following information:

- a) reference to this International Standard;
- b) date of test report;
- c) statement of conformity;
- d) material designation by grade and size;
- e) type and details of inspection technique;
- f) description of the reference standard.

Annex A

(informative)

Guidance notes on limitations associated with the eddy current test method

A.1 Eddy current testing in general

It should be noted that, during the eddy current testing of tubes, the sensitivity of the test is at a maximum at the tube surface adjacent to the test coil and decreases with increasing distance from the test coil. The signal response from a subsurface or internal surface imperfection is thus smaller than that from an external surface imperfection of the same size. The capacity of the test equipment to detect subsurface or internal surface imperfections is determined by various factors, but predominantly by the thickness of the tube under test and the eddy current excitation frequency.

The excitation frequency applied to the test coil determines the extent to which the induced eddy current intensity penetrates the tube wall. The higher the excitation frequency the lower the penetration, and conversely the lower the excitation frequency the higher the penetration. In particular, the physical parameters of the tube (e.g. conductivity, permeability, etc.) should be taken into account.

A.2 Concentric test coils

This test method is preferred since it can detect short longitudinal imperfections and transverse imperfections both of which break the surface adjacent to the test coil or lie just below it.

The maximum length of the longitudinal imperfection which is detectable is principally determined by the search coil arrangement and by the rate of change of section along the length of the imperfection.

A.3 Pancake coils

This test method uses one or more pancake coils to describe a helical path over the tube surface. For this reason, the method detects longitudinal imperfections with a minimum length dependant on the width of the test coil and the inspection helical pitch. It is recognized that transverse imperfections are not normally detectable.

Since the excitation frequency is significantly higher than that using concentric coils, only those imperfections which break the surface adjacent to the test coil are detectable.

Annex B

(informative)

Guidance notes on limitations of the magnetic transducer/flux leakage technique

It should be noted that, during the magnetic transducer/flux leakage testing of tubes, the sensitivity of the test is at a maximum at the tube surface adjacent to the magnetic transducer and decreases with increasing tube thickness due to effective diminishing flux diversion from imperfections at the tube bore surface in relation to that at the external surface. The signal response from internal surface imperfections may thus be smaller than that from an external imperfection of the same size.

This test method uses one or more magnetic transducers to describe a helical path over the tube surface. For this reason, the method detects longitudinal imperfections with a minimum length dependant on the width of the transducer and the inspection helical pitch. It is recognized that transverse imperfections are not normally detectable.

ICS 23.040.10; 77.040.20; 77.140.30

Descriptors: pipes (tubes), metal tubes, steel tubes, seamless tubes, welded tubes, pressure pipes, tests, non-destructive tests, electromagnetic tests, determination, leaktightness.

Price based on 8 pages
