
Ceramic tiles —

**Part 6:
Determination of resistance to deep
abrasion for unglazed tiles**

Carreaux et dalles céramiques —

*Partie 6: Détermination de la résistance à l'abrasion profonde pour les
carreaux non émaillés*



Reference number
ISO 10545-6:2010(E)

© ISO 2010

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 10545-6 was prepared by Technical Committee ISO/TC 189, *Ceramic tile*.

This second edition cancels and replaces the first edition (ISO 10545-6:1995), of which subclause 4.3 has been technically revised.

ISO 10545 consists of the following parts, under the general title *Ceramic tiles*:

- *Part 1: Sampling and basis for acceptance*
- *Part 2: Determination of dimensions and surface quality*
- *Part 3: Determination of water absorption, apparent porosity, apparent relative density and bulk density*
- *Part 4: Determination of modulus of rupture and breaking strength*
- *Part 5: Determination of impact resistance by measurement of coefficient of restitution*
- *Part 6: Determination of resistance to deep abrasion for unglazed tiles*
- *Part 7: Determination of resistance to surface abrasion for glazed tiles*
- *Part 8: Determination of linear thermal expansion*
- *Part 9: Determination of resistance to thermal shock*
- *Part 10: Determination of moisture expansion*
- *Part 11: Determination of crazing resistance for glazed tiles*
- *Part 12: Determination of frost resistance*
- *Part 13: Determination of chemical resistance*
- *Part 14: Determination of resistance to stains*

ISO 10545-6:2010(E)

- *Part 15: Determination of lead and cadmium given off by glazed tiles*
- *Part 16: Determination of small colour differences*

Ceramic tiles —

Part 6: Determination of resistance to deep abrasion for unglazed tiles

1 Scope

This part of ISO 10545 specifies a test method for determining the resistance to deep abrasion of all unglazed ceramic tiles used for floor coverings.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 630, *Structural steels — Plates, wide flats, bars, sections and profiles*

ISO 8486-1, *Bonded abrasives — Determination and designation of grain size distribution — Part 1: Macrogrits F4 to F220*

3 Principle

Determination of the abrasion resistance of unglazed tiles by measuring the length of the groove produced in the proper surface by means of a rotating steel disc, under given conditions and with the use of abrasive material.

4 Apparatus

4.1 Abrasion apparatus, consisting essentially of a rotating disc, a storage hopper with a dispensing device for the abrasive material, a test specimen support and a counterweight (see Figure 1).

The disc shall be made of E 235 A (Fe 360 A) conforming to ISO 630, with a diameter of $(200 \pm 0,2)$ mm and a thickness at the edge of $(10 \pm 0,1)$ mm, and with a revolution rate of 75 r/min.

The pressure with which the test specimens are held against the steel disc shall be determined by calibrating the apparatus against transparent fused silica. The pressure shall be adjusted such that, after 150 revolutions using F80 abrasive, which shall be in accordance with ISO 8486-1, a chord of $(24 \pm 0,5)$ mm shall be produced. Transparent fused silica shall be used as a primary standard. A secondary standard of float glass or other products may be used.

When the diameter has worn by 0,5 % of the initial diameter, the steel disc shall be replaced.

4.2 Measuring gauge, accurate to 0,1 mm.

4.3 Abrasive material, of white fused aluminium oxide with a grain size of F80, in accordance with ISO 8486-1.

An equivalent abrasive material may be used if it can be shown to lead to the same results.

5 Test specimens

5.1 Types of test specimen

Tests shall be carried out using whole tiles or test specimens of suitable dimensions. Before testing, small specimens shall be fixed with an adhesive on to a larger background, avoiding joints.

5.2 Preparation of test specimens

Clean, dry test specimens shall be used.

5.3 Number of test specimens

A minimum of five test specimens shall be tested.

6 Procedure

Place a test specimen in the apparatus (4.1) so that it is tangential against the rotating disc. Ensure that abrasive material (4.3) is fed uniformly into the grinding zone at a rate of (100 ± 10) g/100 revolutions.

Rotate the steel disc for 150 revolutions. Remove the test specimen from the apparatus and measure the chord length, L , of the groove to the nearest 0,5 mm (see Figure 2). Test each test specimen on its proper surface, in at least two places at right angles to each other.

In the case of relief surfaces interfering with the determination of the abrasion resistance, the projections may be ground off, but the results of the test would not be the same as for similar tiles having plane surfaces.

Do not re-use the abrasive material.

7 Expression of results

The resistance to deep abrasion is expressed as the volume, V , in cubic millimetres, of material removed, and is calculated from the chord length, L , of the groove using the following equation:

$$V = \left(\frac{\pi\alpha}{180} - \sin \alpha \right) \times \left(\frac{h \times d^2}{8} \right)$$

with

$$\sin(0,5\alpha) = \frac{L}{d}$$

where

α is the angle, in degrees, subtended at the centre of the rotating disc by the chord (see Figure 2);

h is the thickness, in millimetres, of the rotating disc;

d is the diameter, in millimetres, of the rotating disc;


L is the maximum length, in millimetres, of the chord.

Some equivalent values of L and V are given in Table 1.

8 Test report

The test report shall include the following information:


- a) reference to this part of ISO 10545, i.e. ISO 10545-6;
- b) a description of the tiles;
- c) the chord length, L , of each groove, to the nearest 0,5 mm;
- d) the volume, V , in cubic millimetres, for each individual groove;
- e) the average volume, V_m , in cubic millimetres.

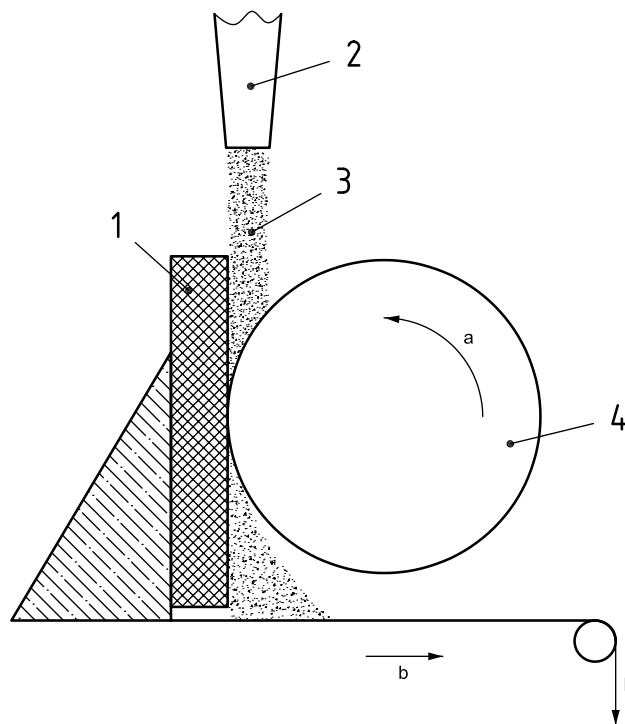

Key

- 1 tile
- 2 dispensing device for the abrasive material
- 3 white fused aluminium oxide of grain size F80
- 4 rotating steel disc
- a Direction of rotation.
- b Collection of material which has been removed.

Figure 1 —Schematic diagram of deep abrasion equipment

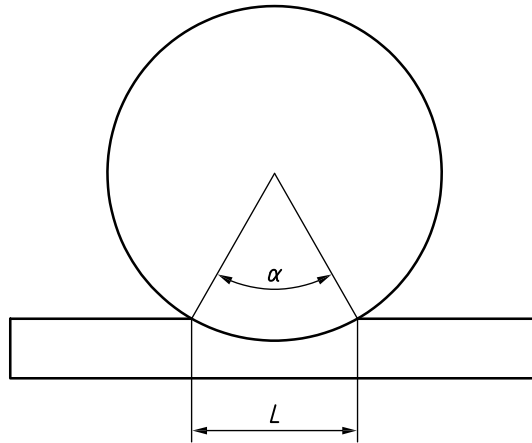

Key

- α angle, in degrees, subtended at the centre of the rotating disc by the chord
- L chord length, in millimetres

Figure 2 — Definition of the chord

Table 1 — Equivalent values

| L mm | V mm ³ | L mm | V mm ³ | L mm | V mm ³ | L mm | V mm ³ | L mm | V mm ³ |
|-----------|------------------------|-----------|------------------------|-----------|------------------------|-----------|------------------------|-----------|------------------------|
| 20 | 67 | 30 | 227 | 40 | 540 | 50 | 1 062 | 60 | 1 851 |
| 20,5 | 72 | 30,5 | 238 | 40,5 | 561 | 50,5 | 1 094 | 60,5 | 1 899 |
| 21 | 77 | 31 | 250 | 41 | 582 | 51 | 1 128 | 61 | 1 947 |
| 21,5 | 83 | 31,5 | 262 | 41,5 | 603 | 51,5 | 1 162 | 61,5 | 1 996 |
| 22 | 89 | 32 | 275 | 42 | 626 | 52 | 1 196 | 62 | 2 046 |
| 22,5 | 95 | 32,5 | 288 | 42,5 | 649 | 52,5 | 1 232 | 62,5 | 2 097 |
| 23 | 102 | 33 | 302 | 43 | 672 | 53 | 1 268 | 63 | 2 149 |
| 23,5 | 109 | 33,5 | 316 | 43,5 | 696 | 53,5 | 1 305 | 63,5 | 2 202 |
| 24 | 116 | 34 | 330 | 44 | 720 | 54 | 1 342 | 64 | 2 256 |
| 24,5 | 123 | 34,5 | 345 | 44,5 | 746 | 54,5 | 1 380 | 64,5 | 2 310 |
| 25 | 131 | 35 | 361 | 45 | 771 | 55 | 1 419 | 65 | 2 365 |
| 25,5 | 139 | 35,5 | 376 | 45,5 | 798 | 55,5 | 1 459 | 65,5 | 2 422 |
| 26 | 147 | 36 | 393 | 46 | 824 | 56 | 1 499 | 66 | 2 479 |
| 26,5 | 156 | 36,5 | 409 | 46,5 | 852 | 56,5 | 1 541 | 66,5 | 2 537 |
| 27 | 165 | 37 | 427 | 47 | 880 | 57 | 1 583 | 67 | 2 596 |
| 27,5 | 174 | 37,5 | 444 | 47,5 | 909 | 57,5 | 1 625 | 67,5 | 2 656 |
| 28 | 184 | 38 | 462 | 48 | 938 | 58 | 1 689 | 68 | 2 717 |
| 28,5 | 194 | 38,5 | 481 | 48,5 | 968 | 58,5 | 1 713 | 68,5 | 2 779 |
| 29 | 205 | 39 | 500 | 49 | 999 | 59 | 1 758 | 69 | 2 842 |
| 29,5 | 215 | 39,5 | 520 | 49,5 | 1 030 | 59,5 | 1 804 | 69,5 | 2 906 |

ICS 91.100.23

Price based on 4 pages