

INTERNATIONAL STANDARD

ISO 12965

First edition
2000-09-15

Butadiene rubber — Determination of microstructure by infra-red spectrometry

*Caoutchouc butadiène — Détermination de la microstructure par
spectrométrie à infrarouge*

This material is reproduced from ISO documents under International Organization for Standardization (ISO) Copyright License Number HIS/CC/1996. Not for resale. No part of these ISO documents may be reproduced in any form, electronic retrieval system or otherwise, except as allowed in the copyright law of the country of use, or with the prior written consent of ISO (Case postale 56, 1211 Geneva 20, Switzerland, Fax +41 22 734 10 79), IHS or the ISO Licensor's members.



Reference number
ISO 12965:2000(E)

© ISO 2000

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Contents

Page

Foreword.....iv

1 Scope 1

2 Normative references 1

3 Principle..... 1

4 Reagent..... 1

5 Apparatus 1

6 Sampling..... 2

7 Procedure 2

8 Precision..... 5

9 Test report 7

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 12965 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analyses*.

Butadiene rubber — Determination of microstructure by infra-red spectrometry

WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

1 Scope

This International Standard specifies a method for the determination of the microstructure of butadiene rubber (BR) by infra-red spectrometry using a cast film.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 1407:1992, *Rubber — Determination of solvent extract*.

ISO 1795:2000, *Rubber, raw natural and raw synthetic — Sampling and further preparative procedures*.

ISO/TR 9272:1986, *Rubber and rubber products — Determination of precision for test method standards*.

3 Principle

3.1 A small quantity of extracted rubber is dissolved in methylene chloride and cast on a salt plate.

3.2 A spectrum is obtained over the range $2\,000\text{ cm}^{-1}$ to 600 cm^{-1} . From the absorbances at fixed wavelengths, the *cis*, *trans* and vinyl contents are calculated.

4 Reagent

4.1 **Methylene chloride.**

5 Apparatus

5.1 **Double-beam infrared spectrophotometer** or **Fourier-transform infra-red (FTIR) spectrophotometer**, with 2 cm^{-1} resolution. The instrument shall be capable of scale expansion along the absorbance or transmittance axis over the spectral region of $2\,000\text{ cm}^{-1}$ to 600 cm^{-1} .

ISO 12965:2000(E)

5.2 Salt plate.

5.3 Balance, weighing to 0,1 mg.

5.4 Vacuum oven, operating at 50 °C to 60 °C.

6 Sampling

Sample the raw rubber in accordance with ISO 1795.

7 Procedure

7.1 Mill the test sample to as thin a sheet as possible. Extract the rubber in accordance with ISO 1407 using ethanol/toluene azeotrope (ETA). Dry the extracted rubber under vacuum in the oven at 50 °C to 60 °C.

7.2 Take approximately 100 mg of extracted sample and dissolve it in around 20 ml of methylene chloride. If gel is present, filter the solution.

7.3 Ensure that the salt plate is levelled horizontally before the film is cast. Place 3 or 4 drops of the solution on the plate and spread evenly over the beam area. Allow the solvent to evaporate, preferably at room temperature.

7.4 Check that the transmittance over the measurement range lies between 50 % and 30 %. If grossly outside these limits, clean the salt plate and repeat step 7.3 with more or less solution.

7.5 When 7.4 is satisfied, scan over the range 2 000 cm⁻¹ to 600 cm⁻¹.

7.6 Draw a baseline from 2 000 cm⁻¹ to 600 cm⁻¹, taking care that no peaks are cut (see Figures 1, 2 and 3 for medium-, low- and high-*cis* polybutadiene).

7.7 Measure the absorbances at 965 cm⁻¹ (A_{965}), 909 cm⁻¹ (A_{909}) and 728 cm⁻¹ (A_{728}). These are an indication of the *trans* (A_{965}), vinyl (A_{909}) and *cis* (A_{728}) contents.

7.8 Normalize the above absorbances using the following equations:

$$\%A_{965} = \frac{A_{965}}{A_{965} + A_{909} + A_{728}} \times 100$$

$$\%A_{909} = \frac{A_{909}}{A_{965} + A_{909} + A_{728}} \times 100$$

$$\%A_{728} = \frac{A_{728}}{A_{965} + A_{909} + A_{728}} \times 100$$

7.9 Calculate the contents of the different isomers, c_{cis} , c_{trans} and c_{vinyl} , in g/dm³, using the following equations:

$$c_{cis} = 1,789\ 6 \times \%A_{728} - 0,025\ 3 \times \%A_{965} - 0,008\ 5 \times \%A_{909}$$

$$c_{trans} = 0,3971 \times \%A_{965} - 0,0502 \times \%A_{728} - 0,014\ 2 \times \%A_{909}$$

$$c_{vinyl} = 0,295\ 4 \times \%A_{909} - 0,007\ 5 \times \%A_{728} - 0,006\ 5 \times \%A_{965}$$

7.10 Determine the microstructure of the rubber, in percent, using the following equations:

$$\% \text{ cis} = \frac{c_{cis} \times 100}{c_{cis} + c_{trans} + c_{vinyl}}$$

$$\% \text{ trans} = \frac{c_{trans} \times 100}{c_{cis} + c_{trans} + c_{vinyl}}$$

$$\% \text{ vinyl} = \frac{c_{vinyl} \times 100}{c_{cis} + c_{trans} + c_{vinyl}}$$

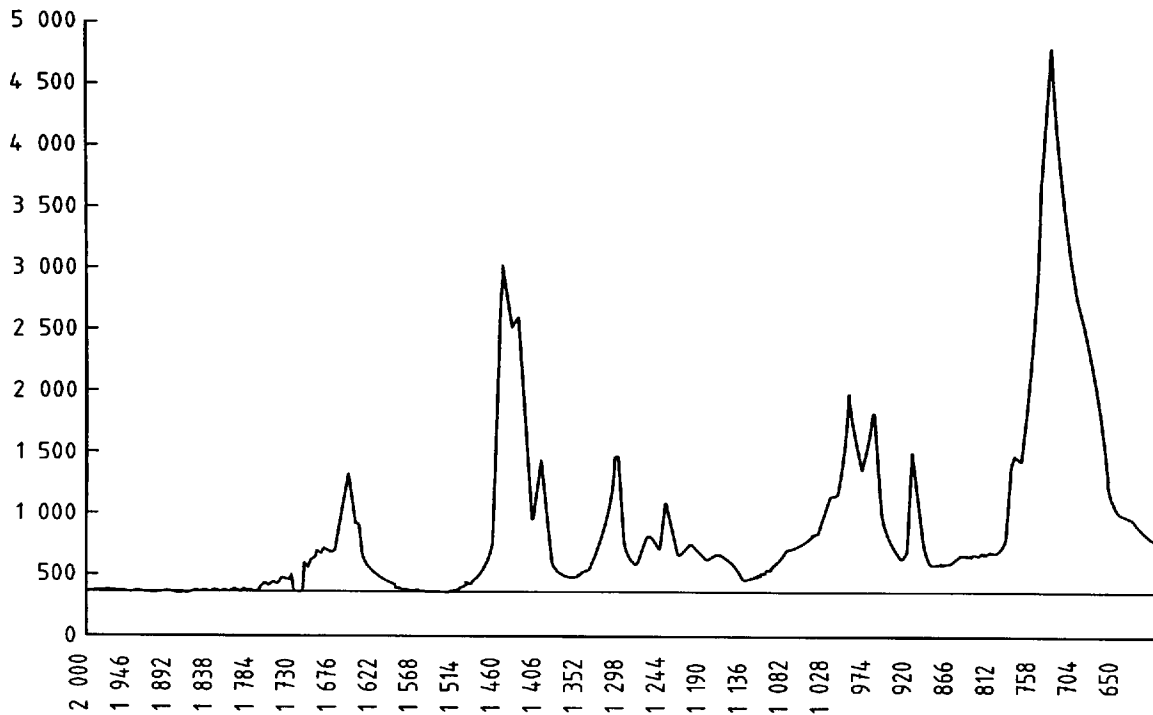


Figure 1 — Sample A (medium-cis polybutadiene)

ISO 12965:2000(E)

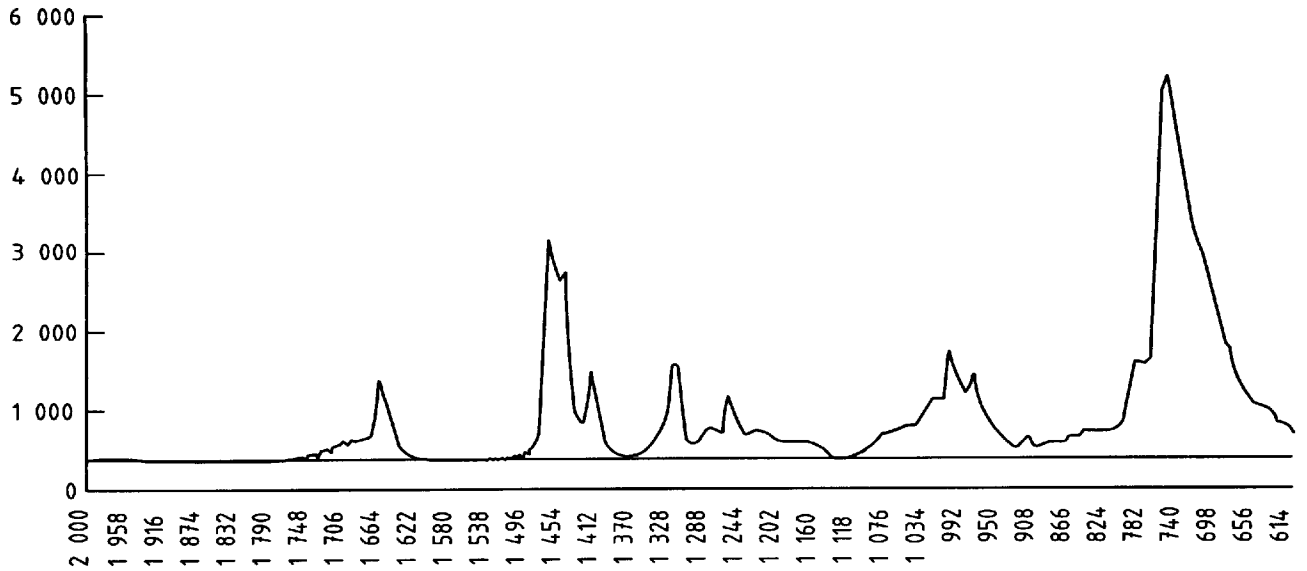


Figure 2 — Sample B (high-*cis* polybutadiene)

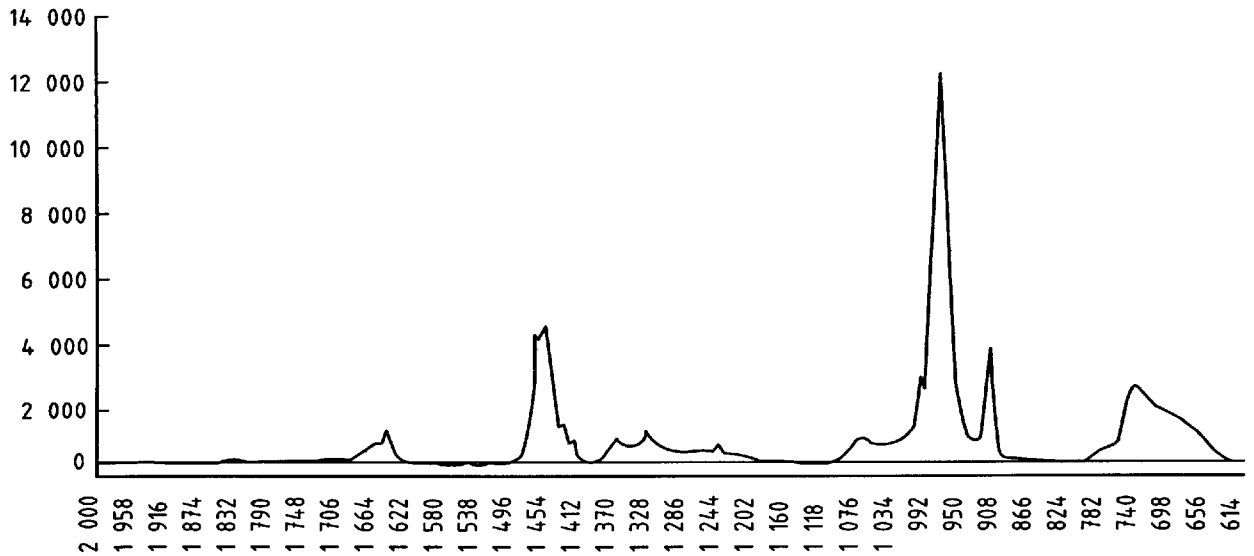


Figure 3 — Sample C (low-*cis* polybutadiene)

8 Precision

8.1 The precision calculations to express repeatability and reproducibility were performed in accordance with ISO/TR 9272. Consult this for precision concepts and nomenclature.

8.2 A type 1 interlaboratory test programme was organized in 1994. Three polybutadiene materials (A, B and C) with different microstructures (see Figures 1, 2 and 3) were sent to the participating laboratories where they were analysed using the test procedure.

8.3 The precision results for the *cis* content are given in Table 1, the precision results for the *trans* content are given in Table 2, while Table 3 shows the precision results for the vinyl content.

For all data, $p = 6$, $q = 3$ and $n = 5$.

8.4 Repeatability for *cis* content: The repeatability r for the *cis* content of polybutadiene has been established as 1,00 percentage points. Two single test results (or determinations) that differ by more than 1,00 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

8.5 Reproducibility for *cis* content: The reproducibility R for the *cis* content of polybutadiene has been established as 1,86 percentage points. Two single test results (or determinations), obtained in separate laboratories, that differ by more than 1,86 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

8.6 Repeatability for *trans* content: The repeatability r for the *trans* content of polybutadiene has been established as 0,72 percentage points. Two single test results (or determinations) that differ by more than 0,72 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

8.7 Reproducibility for *trans* content: The reproducibility R for the *trans* content of polybutadiene has been established as 0,94 percentage points. Two single test results (or determinations), obtained in separate laboratories, that differ by more than 0,94 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

8.8 Repeatability for vinyl content: The repeatability r for the vinyl content of polybutadiene has been established as 0,30 percentage points. Two single test results (or determinations) that differ by more than 0,30 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

8.9 Reproducibility for vinyl content: The reproducibility R for the vinyl content of polybutadiene has been established as 0,64 percentage points. Two single test results (or determinations), obtained in separate laboratories, that differ by more than 0,64 percentage points shall be considered suspect and dictate that some appropriate investigative action be taken.

Table 1 — Precision data for *cis* content

Sample	Mean level %	Within lab			Between labs		
		s_r	r	$r\%$	s_R	R	$R\%$
A	93,48	0,33	0,91	0,97	0,46	1,28	1,37
B	97,52	0,22	0,61	0,63	0,84	2,33	2,39
C	39,94	0,49	1,36	3,41	0,66	1,83	4,58
Pooled or average values	76,98	0,36	1,00	1,30	0,67	1,86	2,42

where

- s_r is the within-lab standard deviation;
- s_R is the between-labs standard deviation;
- r is the repeatability in measurement units;
- $r\%$ is the repeatability in percent; ^a
- R is the reproducibility in measurements units;
- $R\%$ is the reproducibility in percent. ^a

^a These values represent percent relative, i.e. percent of a percent.

Table 2 — Precision data for *trans* content

Sample	Mean level %	Within lab			Between labs		
		s_r	r	$r\%$	s_R	R	$R\%$
A	3,5	0,13	0,36	10,3	0,22	0,61	17,4
B	1,86	0,16	0,44	23,7	0,35	0,97	52,1
C	50,2	0,4	1,11	2,21	0,42	1,16	2,31
Pooled or average values	18,52	0,26	0,72	3,89	0,34	0,94	5,08

where

- s_r is the within-lab standard deviation;
- s_R is the between-labs standard deviation;
- r is the repeatability in measurement units;
- $r\%$ is the repeatability in percent; ^a
- R is the reproducibility in measurements units;
- $R\%$ is the reproducibility in percent. ^a

^a These values represent percent relative, i.e. percent of a percent.

Table 3 — Precision data for vinyl content

Sample	Mean level %	Within lab			Between labs		
		s_r	r	$r\%$	s_R	R	$R\%$
A	3,05	0,10	0,28	9,18	0,31	0,86	28,2
B	0,35	0,11	0,30	85,7	0,19	0,53	151,4
C	9,62	0,13	0,36	3,74	0,17	0,47	4,89
Pooled or average values	4,34	0,11	0,30	6,91	0,23	0,64	14,75

where

- s_r is the within-lab standard deviation;
- s_R is the between-labs standard deviation;
- r is the repeatability in measurement units;
- $r\%$ is the repeatability in percent; ^a
- R is the reproducibility in measurements units;
- $R\%$ is the reproducibility in percent. ^a

^a These values represent percent relative, i.e. percent of a percent.

9 Test report

The test report shall include the following information:

- a) a reference to this International Standard;
- b) full identification of the rubber analysed;
- c) whether any gel was present (see 7.2);
- d) the results of the analysis;
- e) details of any deviations from the method specified;
- f) the date of the test.

ISO 12965:2000(E)

ICS 83.060.00

Price based on 7 pages

© ISO 2000 – All rights reserved