201 P454370 E0P1384 B 8PP1 19N3-75EE1 02I.QT2

# INTERNATIONAL STANDARD

ISO 13327

> First edition 1998-09-01

# Motorcycle tyres — Method of measuring rolling resistance

Pneumatiques pour motocycles — Méthode de mesure de la résistance au roulement

This material is reproduced from ISO documents under International Organization for Standardization (ISO) Copyright License number IHS/ICC/1996. Not for resale. No part of these ISO documents may be reproduced in any form, electronic retrieval system or otherwise, except as allowed in the copyright law of the country of use, or with the prior written consent of ISO (Case postale 56, 1211 Geneva 20, Switzerland, Fax +41 22 734 10 79), IHS or the ISO Licensor's members.



Reference number ISO 13327:1998(E)

## **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 13327 was prepared by Technical Committee ISO/TC 31, Tyres, rims and valves, Subcommittee SC 10, Cycle, moped, motorcycle tyres and rims.

Annex A forms an integral part of this International Standard. Annexes B and C are for information only.

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization Case postale 56 • CH-1211 Genève 20 • Switzerland Internet iso@iso.ch

Printed in Switzerland

ii

# Motorcycle tyres — Method of measuring rolling resistance

## 1 Scope

This International Standard specifies methods for measuring rolling resistance, under controlled laboratory conditions, for new pneumatic tyres designed primarily for use on motorcycles. The relationship between values obtained and the fuel economy of the vehicle is undetermined, and such values are not intended to be used to indicate levels of performance or quality.

This International Standard is applicable to all motorcycle tyres.

It enables comparisons to be made between the rolling resistance of new tyres when they are free-rolling straight ahead, in a position perpendicular to the drum outer surface, and in steady-state conditions.

In measuring tyre rolling resistance, it is necessary to measure small forces in the presence of much larger forces. It is, therefore, essential that equipment and instrumentation of appropriate accuracy be used.

## 2 Normative reference

The following standard contains provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the edition indicated was valid. All standards are subject to revision and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent edition of the standard indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 4223-1:1989, Definitions of some terms used in the tyre industry — Part 1: Pneumatic tyres.

## 3 Definitions

For the purposes of this International Standard, the definitions given in ISO 4223-1 and the following definitions apply.

#### 3.1

#### rolling resistance

F,

loss of energy (or energy consumed) per unit of distance

NOTE — The SI unit conventionally used for the rolling resistance is the newton metre per metre (N·m/m).

This is equivalent to the drag force in newtons (N).

#### 3.2

## rolling resistance coefficient

C

ratio of the rolling resistance, in newtons, to the load on the tyre, in newtons

NOTE — This quantity is dimensionless.

© ISO

#### 3.3

#### capped inflation

process of inflating the tyre and allowing the inflation pressure to build up, as the tyre is warmed up while running

#### 3.4

#### regulated inflation

process of inflating the tyre to the required pressure independent of its temperature, and maintaining this inflation pressure while the tyre runs under load

NOTE — This is most commonly done by using a regulated pressure source attached to the tyre through a rotating union.

#### 3.5

#### parasitic loss

loss of energy (or energy consumed) per unit distance excluding tyre losses, and attributable to aerodynamic loss, bearing friction and other sources of systematic loss which may be inherent in the measurement

#### 3.6

#### skim reading

type of parasitic loss measurement, in which the tyre is kept rolling, without slippage, while reducing the tyre load to a level at which energy loss within the tyre itself is virtually zero

#### 3.7

## machine reading

type of parasitic loss measurement, involving losses of the test machine, exclusive of losses in the rotating spindle which carries the tyre and rim

#### 4 Test methods

The following alternative measurement methods are given in this International Standard:

- a) Force method: the reaction force at the tyre spindle.
- b) Torque method: the torque input to the test drum.
- c) Power method: the power input to the test drum.
- d) Deceleration method: the deceleration of the test drum and tyre assembly.

## 5 Test equipment

#### 5.1 Drum specifications

#### 5.1.1 Diameter

The test dynamometer shall have a cylindrical flywheel (drum) with a diameter of between 1,5 m and 3 m inclusive (reference drum diameter: 1,70 m). It should be noted that the results are different; see 9.3 for drum diameter correction for comparisons, if necessary.

#### 5.1.2 Surface

The surface of the drum shall be smooth steel or textured and shall be kept clean (see clause A.6).

## 5.1.3 Width

The width of the drum test surface shall exceed the width of the test tyre tread.

#### 5.2 Test rim

The tyre shall be mounted on a test rim, as specified in annex A.

## 5.3 Load, alignment, control and instrumentation accuracy

Measurement of these parameters shall be sufficiently accurate and precise to provide the required test data. The specific and respective values are shown in annex A.

## 5.4 Thermal environment

#### 5.4.1 Reference conditions

The reference ambient temperature, as measured on the rotational axis of the tyre, 1 m away from the plane touching the nearest tyre sidewall, shall be 25 °C.

#### 5.4.2 Alternative conditions

If the reference temperature cannot be obtained, the rolling resistance measurement shall be corrected to standard temperature conditions in accordance with 9.2.

## 5.4.3 Drum surface temperature

Care should be taken to ensure that the temperature of the test drum surface is approximately the same as the ambient temperature at the beginning of the test.

## 6 Test conditions

The test consists of a measurement of rolling resistance in which the tyre is inflated and the inflation pressure allowed to build up (i.e. "capped air").

## 6.1 Test speeds

The value shall be obtained at a drum velocity of

80 km/h for tyres marked with a speed symbol above "L";

50 km/h for tyres marked with a speed symbol "L" and below.

#### 6.2 Test load

The standard test load shall be computed from

65 % of the maximum load capacity of the tyre for light and standard load versions;

80 % of the maximum load capacity of the tyre for reinforced version.

It shall be kept within the tolerance specified in annex A.

## 6.3 Test inflation pressure

The inflation pressure shall be

200 kPa for light and standard load versions;

250 kPa for reinforced version.

The inflation pressure shall be capped with the accuracy specified in A.4.1.

## 6.4 Duration and velocity

When the deceleration method is selected, the following requirements apply:

- a) for duration,  $\Delta t$ , the time increments shall not exceed 0,5 s;
- b) any variation of the test drum velocity shall not exceed 1 km/h.

## 7 Test procedure

## 7.1 General

The choice of an individual method is left to the tester. For each method, the test measurements shall be converted to a rolling resistance force acting at the tyre/drum interface.

The test procedure steps described in 7.2 to 7.7 shall be followed in the sequence given.

## 7.2 Break-in

To ensure repeatability of measurements, an initial break-in and cooling period is required prior to the start of the test. Such a break-in should be carried out on a test drum of at least 1,5 m diameter for a period of at least 1 h, at a minimum velocity of 80 km/h, with the load and inflation pressure given in 6.2 and 6.3 respectively.

## 7.3 Thermal conditioning

Place the inflated tyre in the thermal environment of the test location for at least 3 h.

## 7.4 Pressure adjustment

After thermal conditioning, the inflation pressure shall be adjusted to the test pressure, and verified 10 min after the adjustment was made.

#### 7.5 Warm-up


The tyre shall be run at constant test velocity until reaching a stabilised steady-state value of rolling resistance. A warm-up period of at least 30 min at the test speed is required.

## 7.6 Measurement and recording

The following shall be measured and recorded (see figure 1):

- a) test velocity,  $U_n$ ;
- b) load on the tyre normal to the drum surface,  $L_{\rm m}$ ;
- c) test inflation pressure:
  - 1) initial, as defined in 7.4,
  - 2) final, for capped inflation;
- d) the driving torque on the drive shaft,  $T_t$ , the tyre spindle force,  $F_t$ , the input power,  $V \times A$ , or the deceleration of the test drum/tyre/wheel assembly,  $\Delta \omega \Delta t$ , depending on the method;
- e) distance,  $r_L$  (see 8.2.1);

- f) ambient temperature, tamb;
- g) test drum radius, R;
- h) test method chosen;
- i) test rim (designation and material).

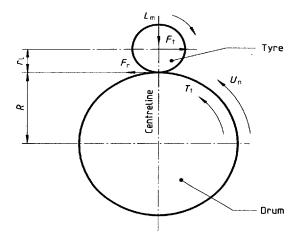

 $F_{r}$  is the rolling resistance

 $T_{t}$  is the torque driving the drum

 $F_{t}$  is the spindle force on the tyre axle

 $U_n$  is the test drum velocity

 $L_{\rm m}$  is the test load

R is the drum radius

 $r_1$  is the distance from the tyre axis to the drum outer surface under steady-state conditions

Figure 1 — Free-body diagram of tyre/drum system, assuming no bearing and windage losses

## 7.7 Measurement of parasitic losses

Determine parasitic losses by one of the procedures given in 7.7.1 to 7.7.3.

#### 7.7.1 Skim reading

- a) Reduce the load to maintain the tyre at the test velocity without slippage to, for example, 50 N.
- b) Record the spindle force,  $F_p$ , input torque,  $T_p$ , or the power, whichever applies.
- c) Record the load on the tyre normal to the drum surface,  $L_{\rm p}$ .

NOTE — The measured value includes the bearing and aerodynamic losses of the wheel, the tyre, and the drum losses which are also to be considered.

#### 7.7.2 Machine reading

- a) Remove the tyre from the drum surface.
- b) At the test velocity,  $U_n$ , record the input torque,  $T_p$ , the power, or the test drum deceleration, whichever applies.

NOTE — The measured value includes the drum losses to be considered.

#### 7.7.3 Deceleration method

- a) Remove the tyre from the test surface.
- b) Record the deceleration of the test drum,  $\Delta\omega_{\rm o}/\Delta t$  and that of the unloaded tyre,  $\Delta\omega_{\rm po}/\Delta t$ .

NOTE — The measured value includes the bearing and aerodynamic losses of the wheel, the tyre, and the drum losses which are also to be considered.

## 8 Data interpretation

## 8.1 Subtraction of parasitic losses

The parasitic losses shall be subtracted as shown in 8.1.1, 8.1.2 or 8.1.3.

## 8.1.1 Skim reading

Subtract the skim reading from the test measurement.

#### 8.1.2 Machine reading

Subtract the machine reading from the test measurement.

NOTE — When the machine reading method is used to determine parasitic losses for the torque or power method, the resulting rolling resistance includes aerodynamic losses of the tyre and wheel as well as the tyre-spindle friction.

#### 8.1.3 Parasitic losses for the deceleration method

Calculate the parasitic losses  $F_{\rm pl}$ , in newtons as

$$F_{\rm pl} = \frac{I_{\rm D}}{R} \left( \frac{\Delta \omega_{\rm vo}}{\Delta t_{\rm o}} \right) + \frac{I_{\rm T}}{R_{\rm r}} \left( \frac{\Delta \omega_{\rm po}}{\Delta t_{\rm o}} \right)$$

where

 $I_{\rm D}$  is the test drum inertia in rotation, in kilogram metres squared;

R is the test drum surface radius, in metres;

 $\omega_{vo}$  is the test drum angular velocity, without tyre, in radians per second;

 $\Delta t_0$  is the time increment chosen for the measurement of the parasitic losses without tyre, in seconds;

 $I_{\mathsf{T}}$  is the tyre and wheel inertia in rotation, in kilogram metres squared;

 $R_r$  is the tyre rolling radius, in metres;

 $\omega_{\mathrm{po}}$  is the tyre angular velocity, unloaded tyre, in radians per second.

## 8.2 Rolling resistance calculation

The net values of driving torque, spindle force, power or deceleration are to be converted to rolling resistance,  $F_r$ , expressed in newtons, using the appropriate method, as shown in 8.2.1 to 8.2.4.

## 8.2.1 Force method at tyre spindle

The rolling resistance,  $F_r$ , in newtons, is calculated with the equation:

$$F_r = F_t[1+(r_1/R)]$$

where

 $F_{t}$  is the tyre spindle force, in newtons;

 $r_{\rm L}$  is the distance from the tyre axis to the drum outer surface under steady-state conditions, in metres;

R is the test drum radius, in metres.

#### 8.2.2 Torque method at drum axis

The rolling resistance,  $F_r$ , in newtons, is calculated with the equation

$$F_{\rm r} = \frac{T}{R}$$

where

T is the input torque, in newton metres;

R is the test drum radius, in metres.

#### 8.2.3 Power method at drum axis

The rolling resistance,  $F_r$ , in newtons, is calculated with the equation

$$F_{\rm r} = \frac{3.6V \times A}{U_{\rm n}}$$

where

V is the electrical potential applied to the machine drive, in volts;

A is the electric current drawn by the machine drive, in amperes;

 $U_{\mathrm{n}}$  is the test drum velocity, in kilometres per hour.

#### 8.2.4 Deceleration method

The rolling resistance,  $F_r$ , in newtons, is calculated with the equation

$$F_{\rm r} = \frac{I_{\rm D}}{R} \left( \frac{\Delta \omega_{\rm v}}{\Delta t_{\rm v}} \right) + \frac{R \times I_{\rm T}}{{R_{\rm r}}^2} \left( \frac{\Delta \omega_{\rm v}}{\Delta t_{\rm v}} \right) - F_{\rm pl}$$

where

 $I_{\mathsf{D}}$  is the test drum inertia in rotation, in kilogram metres squared;

R is the test drum surface radius, in metres;

 $\Delta t_{v}$  is the time increment chosen for measurement, in seconds;

© ISO

 $\omega_{v}$  is the test drum angular velocity, loaded tyre, in radians per second;

 $I_{\mathsf{T}}$  is the tyre and wheel inertia in rotation, in kilogram metres squared;

 $R_r$  is the tyre rolling radius, in metres;

 $F_{\rm pl}$  is as defined in 8.1.3.

Annex B gives guidelines and practical examples to measure the moments of inertia for the deceleration method.

## 9 Data analysis

## 9.1 Rolling resistance coefficient

The rolling resistance coefficient,  $C_r$ , is calculated by dividing the rolling resistance by the load on the tyre:

$$C_{\rm r} = \frac{F_{\rm r}}{L_{\rm m}}$$

where

 $F_r$  is the rolling resistance, in newtons;

 $L_{\rm m}$  is the test load, in newtons.

## 9.2 Temperature correction

If measurements at temperatures other than 25 °C are unavoidable (only temperatures not less than 20 °C nor more than 30 °C are acceptable), then a correction for temperature shall be made using the following equation, where  $F_{r25}$  is the rolling resistance referred at 25 °C, in newtons:

$$F_{r25} = F_r [1 + K(t_{amb} - 25)]$$

where

 $F_{r}$  is the rolling resistance, in newtons;

tamb is the ambient temperature, in degrees Celsius;

K is equal to 0,01 for motorcycle tyres.

## 9.3 Drum diameter correction

Test results obtained from different drum diameters may be compared by using the following theoretical formula:

$$F_{\text{r02}} \cong KF_{\text{r01}}$$

with

$$K = \sqrt{\left(\frac{R_1}{R_2}\right) \frac{\left(R_2 + r_{\mathsf{T}}\right)}{\left(R_1 + r_{\mathsf{T}}\right)}}$$

## where

 $R_1$  is the radius of drum 1, in metres;

 $R_2$  is the radius of drum 2, in metres;

 $r_{\rm T}$  is the nominal tyre radius, in metres;

 $F_{\rm r01}$  is the rolling resistance value measured on drum 1, in newtons;

 $F_{\rm r02}$  is the rolling resistance value measured on drum 2, in newtons.

## Annex A

(normative)

## **Test equipment tolerances**

## A.1 Purpose

The limits specified in this annex are necessary in order to achieve suitable levels of repeatable test results, which can also be correlated among various test laboratories. These tolerances are not meant to represent a complete set of engineering specifications for test equipment; instead, they should serve as guidelines for achieving reliable test results.

## A.2 Test rims

#### A.2.1 Width

The test rim width shall be equal to the standardized measuring rim. If this is not available, then the next wider rim may be chosen. It should be noted that a change in rim width will result in different test results.

#### A.2.2 Run-out

Run-out shall meet the following criteria:

- maximum radial run-out: 0,5 mm;
- maximum lateral run-out: 0,5 mm.

## A.3 Alignment

Angle deviations are critical to the test results.

#### A.3.1 Load application

The direction of tyre loading application shall be kept normal to the test surface and shall pass through the wheel centre within

- 1 mrad for the force and deceleration methods:
- 5 mrad for the torque and power methods.

## A.3.2 Tyre alignment

## A.3.2.1 Camber angle

The plane of the wheel shall be normal to the test surface within 2 mrad for all methods.

## A.3.2.2 Slip angle

The plane of the tyre shall be parallel to the direction of the test surface motion within 1 mrad for all methods.

© ISO

ISO 13327:1998(E)

## A.4 Control accuracy

## A.4.1 General accuracy

Exclusive of perturbations induced by the tyre and rim non-uniformity, the test equipment shall be capable of checking the test variables within the following limits:

- tyre loading: ± 20 N;
- inflation pressure: ± 3 kPa;
- surface velocity:
  - $\pm$  0,2 km/h for the power, torque and deceleration methods,
  - ± 0,5 km/h for the force method;
- time: ± 0,02 s;
- angular velocity: ± 0,2 %.

## A.4.2 Optional compensation for load/spindle force interaction and load misalignment

Compensation of both load/spindle force interaction ("cross talk") and load misalignment may be accomplished either by recording the spindle force for both forward and reverse tyre rotation or by dynamic machine calibration. If spindle force is recorded for forward and reverse directions (at each test condition), compensation is achieved by subtracting the "reverse" value from the "forward" value and dividing the result by two. If dynamic machine calibration is intended, the compensation terms may be easily incorporated in the data reduction.

NOTE — This compensation applies for the force method only.

## A.5 Instrumentation accuracy

The instrumentation used for readout and recording of test data shall be accurate within the tolerances stated below:

- tyre load: ± 10 N;
- inflation pressure: ± 1 kPa;
- spindle force: ± 0,5 N;
- torque input: ± 0,5 N·m;
- distance: ± 1 mm;
- electrical power: ± 10 W;
- temperature: ± 0,2 °C;
- surface velocity: ± 0,1 km/h (for all methods);
- time: ± 0,01 s;
- angular velocity:  $\pm$  0,1 %.

© ISO

## A.6 Test surface roughness

The roughness, measured laterally, of the smooth steel drum surface shall have a maximum centreline average height value of  $6.3 \, \mu m$ .

In cases where a textured drum surface is used instead of a smooth steel surface, this fact shall be noted in the test report. The surface texture shall then be  $180 \mu m$  deep (80 grit).

## A.7 Tyre spindle bearing friction

When using the machine reading as a method for determining the parasitic losses, tyre spindle bearing friction should be regularly verified as being sufficiently small as to be considered negligible (e.g. a coast-down from 80 km/h to 0 km/h in not less than 5 min with a freely rotating tyre).

## Annex B

(informative)

# Measurement methods of moment of inertia for drum and tyre assembly — Deceleration method

## **B.1** Limitation

The methods presented here should be considered only as guidelines or practical examples of methods used to measure moments of inertia by the deceleration method to achieve reliable test results.

## **B.2** Test drum inertia

## **B.2.1 Measurement method**

## **B.2.1.1** Equipment needed

The arrangement shown in figure B.1 requires, in addition to the drum and its angular encoder:

- a lightweight pulley mounted on low-friction bearings;
- a weight of known mass, m, in the range 50 kg to 100 kg;
- suitable wire rope and attachments.

## **B.2.1.2** Experimental arrangement

See figure B.1.

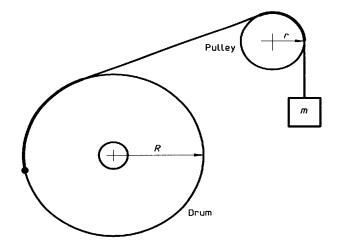


Figure B.1 — Test arrangement

© ISO

#### B.2.1.3 Theory

Application of laws of mechanics to the system shown in figure B.1 leads to the following equation:

$$I_{D} = \frac{mgR - C}{\left(\Delta\omega_{D}/\Delta t\right)} - mR^{2} - I_{p} \frac{R^{2}}{r^{2}}$$

where

m is the mass, in kilograms;

 $I_{\mathbf{p}}$  is the pulley inertia, in kilogram metres squared;

r is the pulley radius, in metres;

R is the drum radius, in metres;

 $I_{\rm D}$  is the drum inertia, in kilogram metres squared;

C is the friction torque of drum bearings, in newton metres;

g is the earth's gravity equal to 9,81 m/s<sup>2</sup>;

 $\Delta\omega_{\rm D}/\Delta t$  is the angular acceleration or deceleration, in radians per second squared.

NOTE — The friction torque of pulley bearings can be neglected.

#### **B.2.1.4** Method

When the mass, m, is released, the angular acceleration is measured through the angular encoder fitted to the drum axle (and otherwise used to measure drum decelerations).

The friction torque, C, of drum bearings can also be measured, provided that the rope can be separated from the drum once mass, m, has given sufficient momentum to the drum, for the subsequent drum deceleration is directly related to C by:

$$C = I_{\rm D} \left( \frac{\Delta \omega_{\rm D}}{\Delta t} \right)$$

where the values are as defined B.2.1.3.

#### **B.2.1.5** Determination method

The drum inertia is estimated by calculation.

The drum inertia,  $I_D$ , in kilogram metre squared, is determined by the summation of the inertia of each drum part (flange, disc, reinforced rib):

$$I_D = I_f + I_d + I_r$$

where

If is the drum flange inertia;

Id is the drum disc inertia;

I<sub>r</sub> is the reinforced rib inertia;

all values being expressed in kilogram metres squared.

## **B.3** Tyre assembly inertia

## **B.3.1 Spring method**

## **B.3.1.1** Equipment needed

Torsion pendulum of inertia  $I_0$  and spring constant K (see figure B.2).

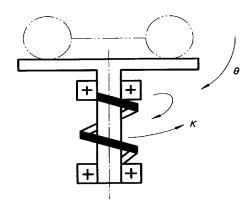


Figure B.2 — Spring method

## B.3.1.2 Theory

Equation of free movement of pendulum, if  $\theta$  is the angle from equilibrium:

$$I_0 \frac{d^2 \theta}{dt^2} + K\theta = 0$$

Natural oscillation period,  $T_0$ :

$$T_{\rm o} = 2\pi \sqrt{\frac{I_{\rm o}}{K}}$$

where

- $\theta$  is the angle of oscillation, in radians;
- t is the period of time, in seconds;
- $I_{\mathrm{o}}$  is the torsion pendulum inertia, in kilogram metres squared;
- K is the spring constant.

## B.3.1.3 Method

Measurement of oscillation periods, with the tyre assembly,  $T_1$ , and without,  $T_0$ , can be used to give the tyre assembly inertia,  $I_T$ ,

$$I_{\mathsf{T}} = \frac{K}{4\pi^2} \left( T_1^2 - T_0^2 \right)$$

## B.3.2 Bifilar pendulum (rope) method

Tyre inertia can be obtained by the period time of twisted oscillation of a tyre hanging from two steel ropes of exactly the same length (see figure B.3).

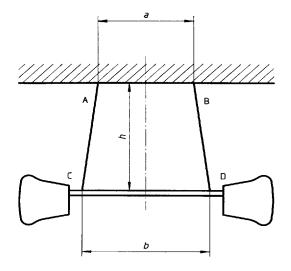


Figure B.3 — Bifilar pendulum (rope) method

## B.3.2.1 Theory

The tyre inertia,  $I_T$ , in kilogram metres squared, is determined by

$$I_{\mathsf{T}} = \tau^2 \times \frac{Wab}{4\pi^2 h}$$

#### where

- au is the oscillation period, in seconds;
- W is the tyre and wheel weight, in newtons;
- a is the distance between points A and B, in metres;
- b is the distance between points C and D, in metres;
- h is the vertical distance between lines AB and CD, in metres.

## B.3.2.2 Method

The time period,  $\tau$ , of the twisted oscillation of a tyre is measured, and tyre inertia can be calculated from the equation given in B.3.2.1.

# Annex C (informative)

## **Bibliography**

- [1] ISO 4249-1:1985, Motorcycles tyres and rims (code designated series) Part 1: Tyres.
- [2] ISO 4249-2:1990, Motorcycles tyres and rims (code designated series) Part 2: Tyre load ratings.
- [3] ISO 4249-3:1997, Motorcycles tyres and rims (code designated series) Part 3: Rims.
- [4] ISO 5751-1:1994, Motorcycle tyres and rims (metric series) Part 1: Design guides.
- [5] ISO 5751-2:1994, Motorcycle tyres and rims (metric series) Part 2: Dimensions and load-carrying capacities.
- [6] ISO 5751-3:1994, Motorcycle tyres and rims (metric series) Part 3: Range of approved rim contours.
- [7] ISO 5995-1:1982, Moped tyres and rims Part 1: Tyres.
- [8] ISO 5995-2:1988, Moped tyres and rims Part 2: Rims.
- [9] ISO 6054-1:1994, Motorcycle tyres and rims (code-designated series) Diameter codes 4 to 12 Part 1: Tyres.
- [10] ISO 6054-2:1990, Motorcycle tyres and rims (code-designated series) Diameter codes 4 to 12 Part 2: Rims.

ICS 83.160.10

Descriptors: road vehicles, motorcycles, tyres, pneumatic tyres, tests, laboratory tests, physical tests, rolling tests.

Price based on 17 pages