
Plastics piping systems — End-load-bearing and non-end-load-bearing assemblies and joints for thermoplastics pressure piping — Test method for long-term leaktightness under internal water pressure

Systèmes de canalisations en plastiques — Assemblages et jonctions avec et sans effet de fond pour canalisations thermoplastiques avec pression — Méthode d'essai pour vérifier l'étanchéité à long terme sous une pression d'eau interne



Reference number
ISO 13846:2000(E)

© ISO 2000

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 13846 was prepared by the European Committee for Standardization (CEN) in collaboration with ISO Technical Committee TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 2, *Plastics pipes and fittings for water supplies*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this standard, read "...this European Standard..." to mean "...this International Standard...".

Contents

	Page
Foreword.....	v
1 Scope	1
2 Principle.....	1
3 Apparatus	1
3.1 Ambient temperatures.....	1
3.2 Elevated temperatures	1
3.3 Pressure control device	2
3.4 Support	2
3.5 Compensating device.....	2
4 Test piece.....	3
4.1 Preparation	3
4.2 Number.....	4
5 Procedure	4
5.1 Preparation	4
5.2 Conditioning.....	4
5.3 Pressure control	4
5.4 Examination of the test assembly.....	5
5.5 Examination at the mid-point and at the end of the test period.....	5
5.6 Rupture	5
6 Test report	5
Bibliography	6

Foreword

The text of EN ISO 13846:2000 has been prepared by Technical Committee CEN/TC 155 "Plastics piping systems and ducting systems", the secretariat of which is held by NNI, in collaboration with Technical Committee ISO/TC 138 "Plastics pipes, fittings and valves for the transport of fluids".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2001, and conflicting national standards shall be withdrawn at the latest by April 2001.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

The material-dependent parameters and/or performance requirements are incorporated in the System Standard(s) concerned.

This standard is one of a series of standards on test methods which support System Standards for plastics piping systems and ducting systems.

1 Scope

This standard specifies a test method for the long-term leaktightness of end-load-bearing and non-end-load-bearing mechanically jointed assemblies and joints between fittings, ancillaries, valves and thermoplastics pressure pipes, including integral pipe joints.

This method is applicable to joints where similar or different materials are connected, where sealing mechanisms include elastomeric sealing rings or adhesives.

This method is applicable in addition to the hydrostatic pressure tests for materials and components.

2 Principle

The test simulates expansion of the joint area due to creep. This is related to the permissible working conditions for 50 years and based on the properties of the components assembled.

The leaktightness of the joint(s) is tested as an assembly comprising either:

- a) at least one fitting joined to pipes; or
- b) an ancillary component or a valve joined to pipes; or
- c) a pipe-to-pipe joint.

The test is carried out for at least 1000 h at ambient temperature and at the maximum allowed working temperature for the piping system for which the assembly or joint is intended to be used.

The test piece and its joint(s) are subjected to a specified internal hydrostatic water pressure at a specified temperature for the period of time (1000 h or more) specified in the referring standard. Additional reinforcement of the joint area is not permitted for this test.

NOTE It is assumed that the following test parameters are set by the standard making reference to this standard:

- a) the minimum test period under pressure, i.e. 1000 h or more (see clause 2 and 5.4);
- b) the free length, L , of the pipe sections under test (see 4.1);
- c) the number of test pieces (see 4.2);
- d) the test temperature (e.g. ambient or maximum allowed working temperature) (see 5.2);
- e) the test pressure (see 5.3).

3 Apparatus

3.1 Ambient temperatures

For tests at ambient temperatures (see 5.2), a test room or water bath, capable of being maintained at a temperature to within $\pm 2^\circ\text{C}$.

3.2 Elevated temperatures

For tests at elevated temperatures, an air chamber or water bath, capable of being maintained at the specified test temperature to within $\begin{pmatrix} +3 \\ -1 \end{pmatrix}^\circ\text{C}$.

3.3 Pressure control device

A pressure control device connected to the test assembly and capable of applying a constant hydrostatic pressure to within $\begin{pmatrix} +2 \\ -1 \end{pmatrix}$ %.

3.4 Support

Support for end-load-bearing assemblies and joints such that the assemblies and joints shall be subjected to the axial forces generated during the test and such that the support shall not provide any axial restraint. (For bibliography see EN 715^[1].) An example of solvent cement type test assembly is shown in figure 1.

3.5 Compensating device

A compensating device for non-end-load-bearing assemblies and joints, capable of sustaining the axial forces generated by the internal water pressure, whilst maintaining the axial alignment of the joint assembly. (For bibliography see EN 714^[2].) Connecting rods or external frames between non-end-load bearing sealing devices to keep them in place as necessary to prevent any separation. Examples of test assemblies are shown in figures 2 and 3.

NOTE Precautions can be necessary to maintain the alignment of the joint assemblies, particularly for removal of the test assemblies from the test bath.

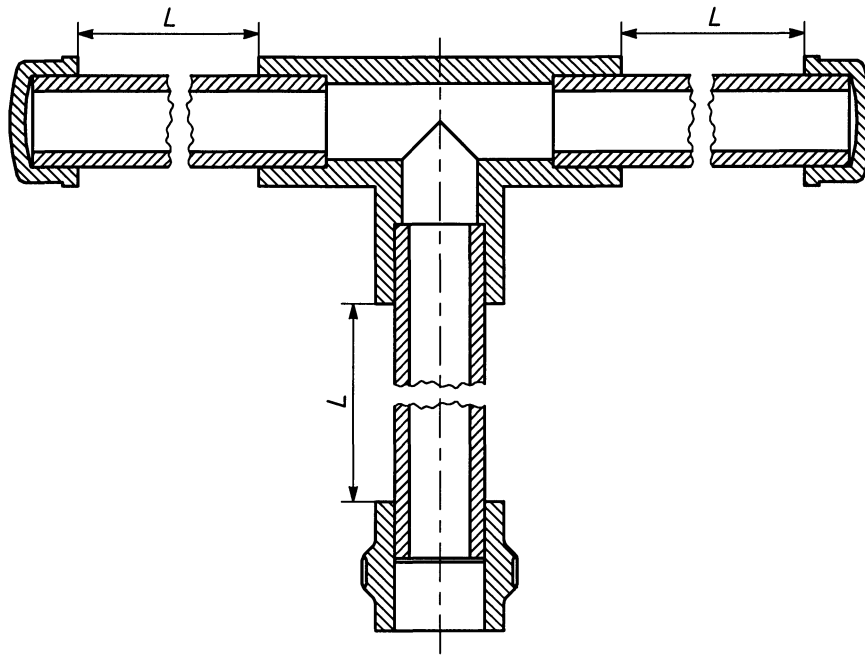


Figure 1 — Example of solvent cement type test assembly

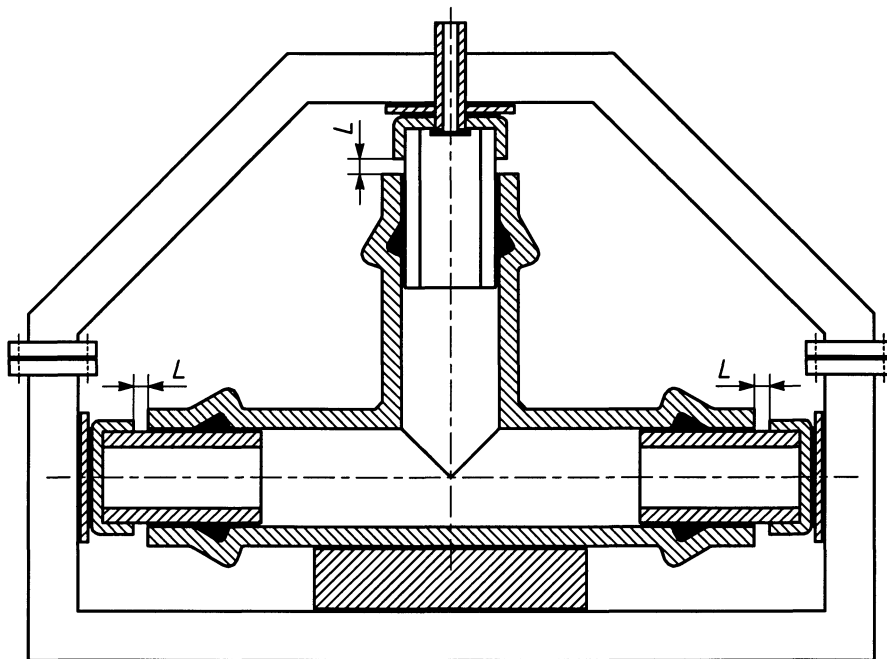


Figure 2 — Example of elastomeric sealing ring type test assembly

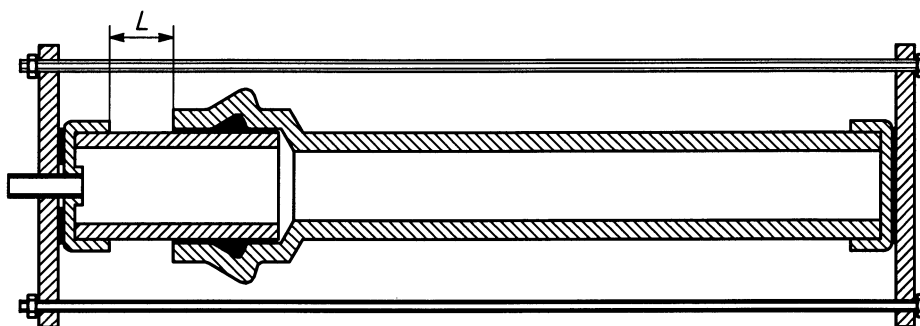


Figure 3 — Example of integral joint type test assembly

4 Test piece

4.1 Preparation

The test piece shall comprise an assembly containing at least one pipe sample joined to a socket of a fitting or to a socketed pipe or joined with an assembled finished product (such as a valve or union). Additional components may be added to the test assembly as required.

Components of the same nominal pressure, PN, or the same pipe series S, shall be used for the assembly.

The relevant dimensions of the joint components shall be measured and recorded, i.e. the mean outside diameter and out-of-roundness of any spigot or pipe joint area, the mean inside diameter and out-of-roundness of any socket and the relevant dimensions of any intermediate component (see note at the end of this clause).

ISO 13846:2000(E)

The minimum length of the pipe section shall be such that its free length, L , between the assembly under test and the joint or the end closure (plug or cap) shall be as specified in the referring standard.

NOTE If the free length is not specified in the referring standard, it should be not less than the nominal outside diameter of the pipe, with a minimum of 150 mm.

All components shall conform to the appropriate part of the applicable System Standard. In addition the elastomeric sealing rings shall conform to the manufacturer's specifications.

The assembly shall be carried out in accordance with the manufacturer's instructions.

For non-end-load-bearing joints connecting rods or external frames may be used as necessary to prevent any separation (see 3.5).

NOTE For this test components should be selected which are as near as possible to the extremes of their respective tolerance bands which provide the most severe test conditions, e.g. for elastomeric sealing ring joints the socket and the diameter of the ring groove housing should be at or as near as possible to their maximum value, the spigot of the pipe or fitting should be at or as near as possible to the minimum value, and the sealing ring should be at or as near as possible to the minimum cross-section specified by the manufacturer.

4.2 Number

The number of test piece components and/or joints tested shall be as specified in the referring standard.

5 Procedure

WARNING All necessary precautions should be taken when testing using components under pressure.

5.1 Preparation

Fill the test assembly with water. Set up the test assembly, without any deformation, in the apparatus appropriate to the type of joint and adjust the pipe section(s) in line with the axis (axes) of the socket(s).

5.2 Conditioning

Condition the test assembly in the test room or conditioning chamber for at least 3 h for test temperatures more than 25 °C or for at least 20 min for test temperatures equal to or less than 25 °C. If the test temperature is specified as "ambient temperature", carry out the conditioning at any temperature between 15 °C and 25 °C. During subsequent testing in accordance with 5.3 to 5.5 inclusive, maintain the test temperature constant to within ± 2 °C and within the range of 15 °C to 25 °C.

5.3 Pressure control

Connect the test assembly to the pressure control device. Evacuate all air from the test assembly and within the period 30 s to 1 min apply the test pressure as specified in the referring standard.

Record the time when the test pressure is achieved as the commencement of the test period.

Inspect the assembly for any signs of leakage and report the result.

5.4 Examination of the test assembly

When required (see 5.5), inspect the test assembly, as appropriate, as follows.

- a) If the test is carried out in air, thoroughly dry the whole outside surface of the test piece and examine it for leakage.
- b) If the test is carried out in water, remove the test assembly from the test bath, dry the surface of the test piece, examine it for leakage and if leakage is not observed, return the test assembly to the bath as soon as possible.

5.5 Examination at the mid-point and at the end of the test period

Repeat the examination of the test assembly for leakage (see 5.4) at the mid-point and at the end of the test period, which shall be at least 1000 h, unless a longer minimum period is specified in the referring standard or prior failure of the assembly occurs in a manner which does not allow continuation in accordance with 5.6.

5.6 Rupture

If rupture occurs in the pipe section between the joints under test or in an end closure not included as part of the test assembly, disregard the test and replace the failed component by another. After replacement, continue the test procedure. If the failure of the component causes damage to any of the joints or assemblies on test, reject these test pieces and repeat the test procedure.

6 Test report

The test report shall include the following information:

- a) a reference to this standard and to the referring standard;
- b) the identities of the component(s), e.g. fitting(s), valve(s), pipe(s), comprising the test assembly;
- c) the nominal pressure, PN, and/or S series of the component(s) and pipe(s) comprising the test assembly;
- d) the test pressure, p , in bars;
- e) the test temperature, T , in degrees Celsius;
- f) the time under pressure, t , in hours;
- g) as applicable, the following dimensions for the components under test:
 - 1) the measured mean outside diameter of the pipe or spigot;
 - 2) the mean inside diameter of the socket or component comprising the joint;
 - 3) any out-of-roundness of the pipe, spigot or socket;
- h) details of any leakage, i.e. location, extent, time, or a declaration that the joint(s) or assembly(ies) did not leak;
- i) any factors which may have affected the results, such as any incidents or any operating details not specified in this standard;
- j) the date of test;
- k) the testing laboratory and the responsible person.

Bibliography

- [1] EN 715, *Thermoplastics piping systems - End-load-bearing joints between small diameter pressure pipes and fittings - Test method for leaktightness under internal water pressure, including end thrust*
- [2] EN 714, *Thermoplastics piping systems - Non-end-load-bearing elastomeric sealing ring type joints between pressure pipes and moulded fittings - Test method for leaktightness under internal hydrostatic pressure without end thrust*

ICS 23.040.60

Price based on 6 pages

© ISO 2000 – All rights reserved