

---

---

**Iron ores for blast furnace feedstocks —  
Determination of low-temperature  
reduction-disintegration indices by  
dynamic method**

*Minerais de fer pour charges de hauts fourneaux — Détermination des  
indices de désintégration par réduction à basse température, par  
méthode dynamique*



Reference number  
ISO 13930:2007(E)

© ISO 2007

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Sampling, sample preparation and preparation of test portions</b> .....	<b>2</b>
<b>6 Apparatus</b> .....	<b>2</b>
<b>7 Test conditions</b> .....	<b>3</b>
<b>8 Procedure</b> .....	<b>4</b>
<b>9 Expression of results</b> .....	<b>5</b>
<b>10 Test report</b> .....	<b>6</b>
<b>11 Verification</b> .....	<b>6</b>
<b>Annex A (normative) Flowsheet of the procedure for the acceptance of test results</b> .....	<b>9</b>

.....

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 13930 was prepared by Technical Committee ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 3, *Physical testing*.

This second edition cancels and replaces the first edition (ISO 13930:1998), which has been revised to homogenise with other physical test standards.

## Introduction

This International Standard concerns one of a number of physical test methods that have been developed to measure various physical parameters and to evaluate the behaviour of iron ores, including reducibility, disintegration, crushing strength, apparent density, etc. This method was developed to provide a uniform procedure, validated by collaborative testing, to facilitate comparisons of tests made in different laboratories.

The results of this test should be considered in conjunction with other tests used to evaluate the quality of iron ores as feedstocks for blast furnace processes.

This International Standard may be used to provide test results as part of a production quality control system, as a basis of a contract, or as part of a research project.

.....

# Iron ores for blast furnace feedstocks — Determination of low-temperature reduction-disintegration indices by dynamic method

**CAUTION** — This International Standard may involve hazardous materials, operations and equipment. This standard does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

## 1 Scope

This International Standard specifies a method to provide a relative measure for evaluating the degree of size degradation of iron ores when reduced under conditions resembling those prevailing in the low-temperature reduction zone of the blast furnace.

This International Standard is applicable to lump ores and hot-bonded pellets.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3082:2000<sup>1)</sup>, *Iron ores — Sampling and sample preparation procedures*

ISO 3310-1:2000, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

ISO 3310-2:1999, *Test sieves — Technical requirements and testing — Part 2: Test sieves of perforated metal plate*

ISO 4701<sup>2)</sup>, *Iron ores and direct reduced iron — Determination of size distribution by sieving*

ISO 11323:2002, *Iron ore and direct reduced iron — Vocabulary*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

---

1) Under revision to incorporate ISO 10386, *Iron ores — Method of sampling and sample preparation for physical testing*.

2) To be published. (Revision of ISO 4701:1999.)

## 4 Principle

The test portion is isothermally reduced in a rotating tube bed, at 500 °C, using a reducing gas consisting of CO, CO<sub>2</sub>, H<sub>2</sub> and N<sub>2</sub>, for 60 min. The reduced product is sieved with sieves having square openings of 6,30 mm, 3,15 mm and 500 µm. Three low-temperature reduction-disintegration indices (LTD) are calculated as the mass percentage of material greater than 6,30 mm, less than 3,15 mm and less than 500 µm.

## 5 Sampling, sample preparation and preparation of test portions

### 5.1 Sampling and sample preparation

Sampling of a lot and preparation of a test sample shall be in accordance with ISO 3082.

The size range for pellets shall be either – 16,0 mm + 12,5 mm or – 12,5 mm + 10,0 mm.

The size range for lump ores shall be – 12,5 mm + 10,0 mm.

A test sample of at least 2,0 kg, on a dry basis, of the sized material shall be obtained.

Oven-dry the test sample to constant mass at 105 °C ± 5 °C and cool it to room temperature before preparation of the test portions.

NOTE Constant mass is achieved when the difference in mass between two subsequent measurements becomes less than 0,05 % of the initial mass of the test sample.

### 5.2 Preparation of test portions

Collect each test portion by taking ore particles at random.

At least 4 test portions, each of approximately 500 g (± the mass of 1 particle) shall be prepared from the test sample.

Weigh the test portions to the nearest 1 g and register the mass of each test portion on its recipient label.

## 6 Apparatus

### 6.1 General

The test apparatus shall comprise

- a) ordinary laboratory equipment, such as an oven, hand tools, a time-control device and safety equipment;
- b) a reduction-tube assembly;
- c) a furnace, with a system to rotate the reduction tube;
- d) a system to supply the gases and regulate the flow rates;
- e) test sieves;
- f) a weighing device.

Figure 1 shows an example of the test apparatus.



**6.2 Reduction tube**, made of non-scaling, heat-resistant metal to withstand temperatures higher than 500 °C and resistant to deformation. The internal diameter shall be 150 mm and the internal length shall be 540 mm. Four equally spaced steel angle lifters, 540 mm long × 20 mm high × 4 mm thick, shall be solidly attached longitudinally inside the tube by welding, in such a manner as to prevent accumulation of material between the lifter and tube. A dust collector shall be connected to the tube to trap any fine particles carried in the gas stream out of the tube during the test. The tube shall be replaced, in any case, when its wall thickness is reduced to 3 mm in any area, and the lifters when their height is reduced to less than 18 mm.

Figure 2 shows an example of a reduction tube.

**6.3 Furnace**, having a heating capacity and temperature control able to reach the test temperature within 45 min and to maintain the entire test portion, as well as the gas entering the test portion, at 500 °C ± 5 °C.

**6.4 Rotation equipment**, capable of rotating the reduction tube at a constant rate of 10 r/min ± 0,2 r/min.

**6.5 Gas-supply system**, capable of supplying the gases and regulating the gas flow rates.

**6.6 Test sieves**, conforming to ISO 3310-1 or ISO 3310-2 and having square apertures of the following nominal sizes: 6,30 mm; 3,15 mm; 500 µm.

**6.7 Weighing device**, capable of weighing the test sample and test portions to an accuracy of 0,1 g.

## 7 Test conditions

### 7.1 General

Volumes and flow rates of gases are as measured at a reference temperature of 0 °C and at a reference atmospheric pressure of 101,325 kPa (1,013 25 bar).

### 7.2 Reducing gas

#### 7.2.1 Composition

The reducing gas shall consist of:

CO 20,0 % ± 0,5 % (volume fraction)

CO<sub>2</sub> 20,0 % ± 0,5 % (volume fraction)

H<sub>2</sub> 2,0 % ± 0,2 % (volume fraction)

N<sub>2</sub> 58,0 % ± 1,0 % (volume fraction)

#### 7.2.2 Purity

Impurities in the reducing gas shall not exceed:

O<sub>2</sub> 0,1 % (volume fraction)

H<sub>2</sub>O 0,2 % (volume fraction)

#### 7.2.3 Flow rate

The flow rate of the reducing gas, during the entire reducing period, shall be maintained at 20 L/min ± 1 L/min.

### 7.3 Heating and cooling gas

Nitrogen (N<sub>2</sub>) shall be used as the heating and cooling gas. Impurities shall not exceed 0,1 % (volume fraction).

The flow rate of N<sub>2</sub> shall be maintained at 20 L/min until the test portion reaches 500 °C, during the temperature-equilibration period and during cooling.

### 7.4 Temperature of the test portion

The temperature of the entire test portion shall be maintained at 500 °C ± 5 °C during the entire reducing period and, as such, the reducing gas shall be preheated before entering the test portion.

## 8 Procedure

### 8.1 Number of determinations for the test

Carry out the test as many times as required by the procedure in Annex A.

### 8.2 Reduction

Take, at random, one of the test portions prepared in 5.2 and place it in the reduction tube (6.2).

Insert the reduction tube into the furnace (6.3). Close the reduction tube, connect the thermocouple, ensuring that its tip is in the middle of the reduction tube, and connect the gas supply system.

By means of the rotation equipment (6.4), commence rotation of the reduction tube at 10 r/min ± 0,2 r/min.

Pass a flow of N<sub>2</sub> through the test portion at a rate of 20 L/min. Heat the test portion, bring the temperature inside the reduction tube to 500 °C within 45 min and stabilise the temperature within the next 15 min. If this requirement is not met, discontinue the test and start a new one.

**DANGER — Carbon monoxide, hydrogen and the reducing gas, which contains carbon monoxide and hydrogen, are toxic and explosive, and therefore hazardous. Testing shall be carried out in a well ventilated area or under a hood. Precautions should be taken for the safety of the operator, in accordance with the safety codes of each country.**

Introduce the reducing gas at a flow rate of 20 L/min ± 1 L/min to replace the N<sub>2</sub>. After 60 min of reduction, stop the flow of the reducing gas, stop the rotation of the reduction tube and cool the test portion to a temperature below 350 °C in the reduction tube under N<sub>2</sub> at a flow rate of 20 L/min. Then lift the reduction tube from the furnace and cool the test portion to below 100 °C, still under the flow of inert gas.

### 8.3 Sieving

Remove all the material carefully from the reduction tube, scraping, if necessary, to remove any material adhering to the tube wall.

Determine and register the mass of the reduced material ( $m_0$ ) and sieve it mechanically on 6,30 mm, 3,15 mm and 500 µm sieves, in accordance with ISO 4701. Determine and record the mass of each fraction retained on the 6,30 mm ( $m_1$ ), 3,15 mm ( $m_2$ ) and 500 µm ( $m_3$ ) sieves. The dry weight of the dust trapped in the dust collector, and material lost during sieving, shall be considered to be part of the – 500 µm fraction.

## 9 Expression of results

### 9.1 Calculation of the low-temperature disintegration indices (LTD<sub>+6,3</sub>, LTD<sub>-3,15</sub> and LTD<sub>-0,5</sub>)

The low-temperature disintegration indices LTD<sub>+6,3</sub>, LTD<sub>-3,15</sub> and LTD<sub>-0,5</sub>, expressed as percentages by mass, are calculated from the following equation:

$$\text{LTD}_{+6,3} = \frac{m_1}{m_0} \times 100$$

$$\text{LTD}_{-3,15} = \frac{m_0 - (m_1 + m_2)}{m_0} \times 100$$

$$\text{LTD}_{-0,5} = \frac{m_0 - (m_1 + m_2 + m_3)}{m_0} \times 100$$

where

$m_0$  is the mass, in grams, of the test portion after reduction, including the dust trapped in the dust collector;

$m_1$  is the mass, in grams, of the fraction retained on the 6,30 mm sieve;

$m_2$  is the mass, in grams, of the fraction retained on the 3,15 mm sieve;

$m_3$  is the mass, in grams, of the fraction retained on the 500 µm sieve.

Record each result to one decimal place.

### 9.2 Repeatability and acceptance of test results

Follow the procedure in Annex A, for each LTD index, by using the repeatability value given in Table 1. The results shall be reported to one decimal place.

**Table 1 — Repeatability ( $r$ )**

Mean value of LTD (%)		$r$ %, absolute
Over	Up to and including	
98		—
93	98	2,0
88	93	2,5
12	88	3,0
7	12	2,5
2	7	2,0
0	2	—

## 10 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 13930:2007;
- b) all details necessary for the identification of the sample;
- c) the name and address of the test laboratory;
- d) the date of the test;
- e) the date of the test report;
- f) the signature of the person responsible for the test;
- g) details of any operation and any test conditions not specified in this International Standard or regarded as optional, as well as any incident which may have had an influence on the results;
- h) the low-temperature disintegration indices,  $LTD_{+6,3}$ ,  $LTD_{-3,15}$ ,  $LTD_{-0,5}$ , plus the results of the individual determinations;
- i) the mass of the test portion before and after reduction;
- j) the sieving conditions, i.e. the type of sieving machine used, the kind of motion and the sieving time;
- k) the type of sieve used.

## 11 Verification


Regular checking of the apparatus is essential to ensure test result reliability. The frequency of checking is a matter for each laboratory to determine.

The conditions of the following items shall be checked:

- sieves;
- weighing device;
- reduction tube;
- tube-rotation equipment;
- temperature control and measurement devices;
- gas flow meters;
- purity of gases;
- time-control device.

It is recommended that internal reference material be prepared and used periodically to check test repeatability.

Appropriate records of verification activities shall be maintained.

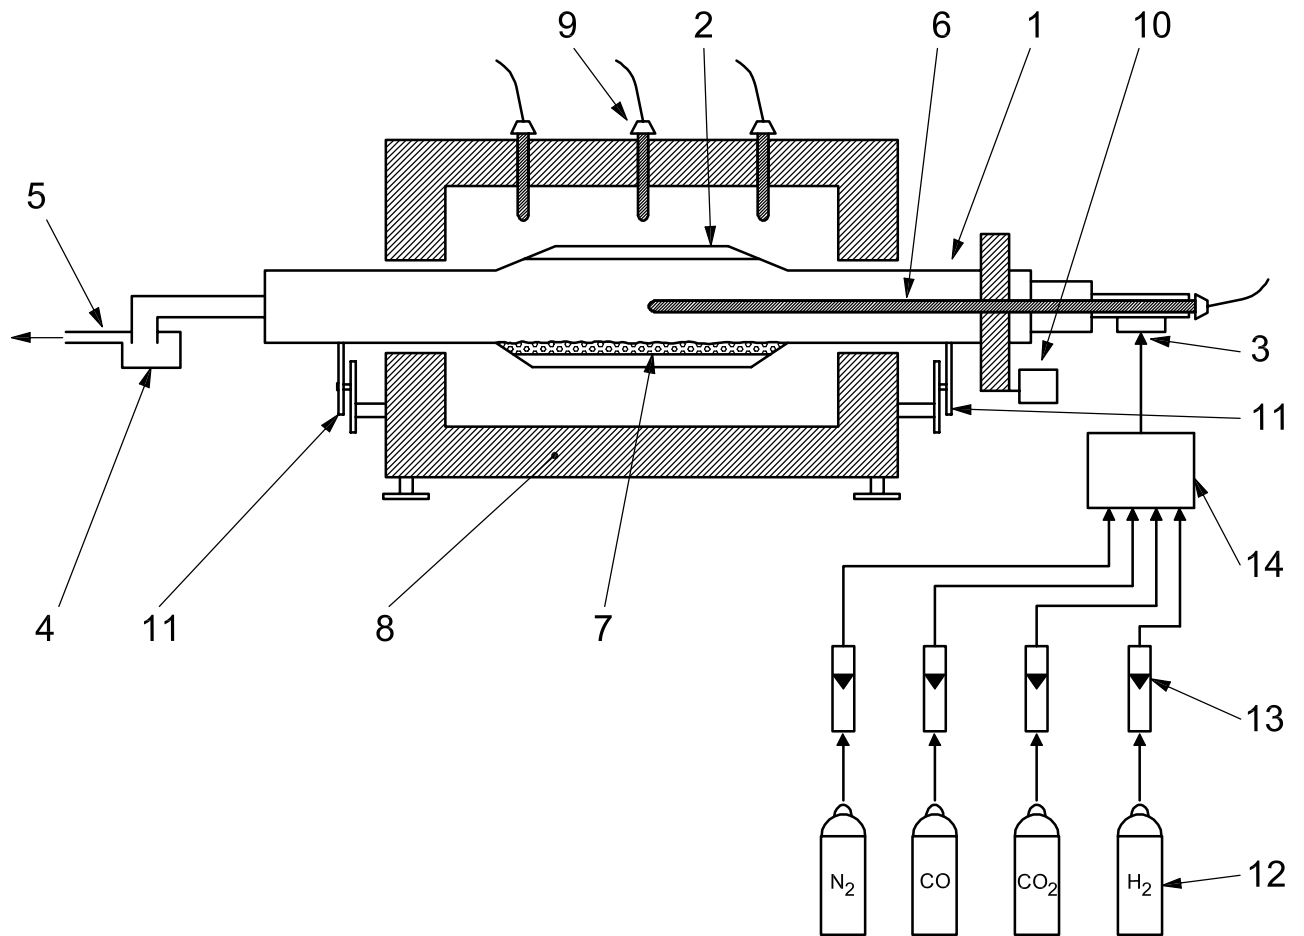**Key****Reduction tube**

- 1 reduction tube
- 2 lifters (four)
- 3 gas inlet
- 4 dust collector
- 5 gas outlet
- 6 thermocouple for measuring the reduction temperature
- 7 test portion


**Furnace**

- 8 electrically heated furnace
- 9 thermocouples for temperature regulation of furnace
- 10 rotation equipment (electric motor)
- 11 tube-support wheels

**Gas-supply system**

- 12 gas cylinders
- 13 gas flow meters
- 14 mixing vessel

**Figure 1 — Example of test apparatus (schematic diagram)**

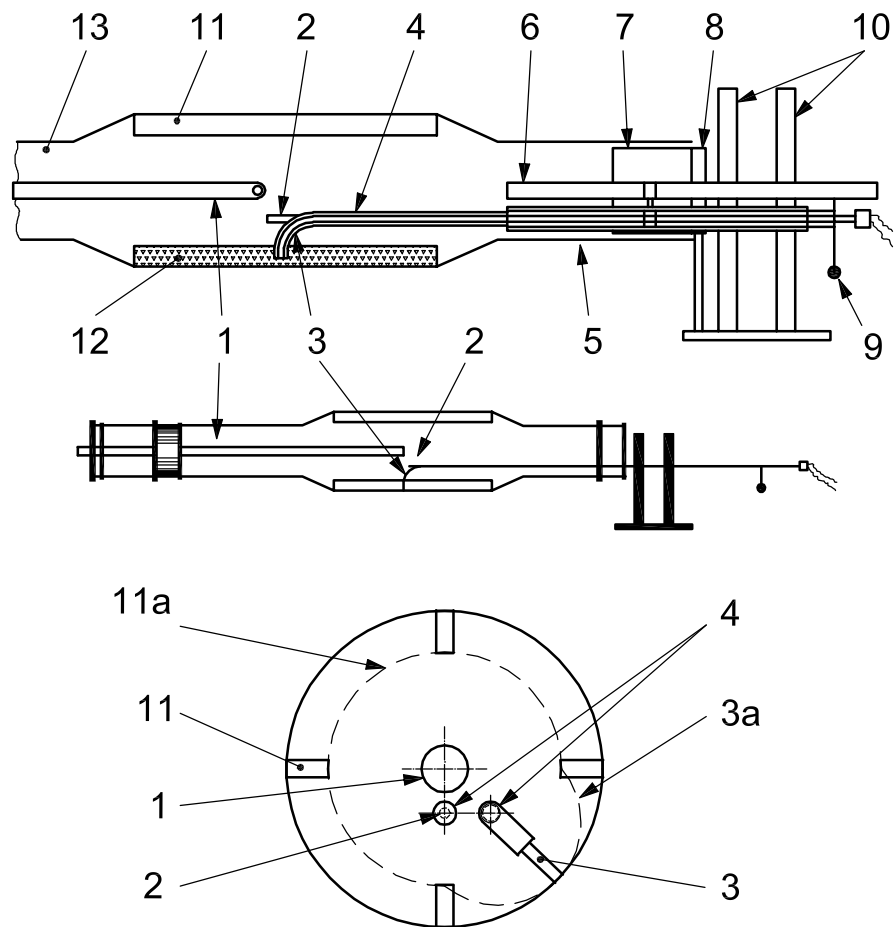


**Key**

- 1 standard thermocouple (thermocouple 6 in Figure 1)
- 2 straight thermocouple, sheathed, 3 mm diameter
- 3 curved thermocouple, sheathed, 3 mm diameter
- 3a path traced by curved thermocouple
- 4 support tubes (diameter 6 mm) for thermocouples 2 and 3
- 5 sliding mounting (diameter 10 mm) for each support tube 4, designed to move along the reduction tube
- 6 support tube (diameter 15 mm) for mounting 5, fitted with a scale
- 7 fixation ring
- 8 thermal insulation (ceramic wool)
- 9 arm-mounted counterweight to compensate for thermocouple 3
- 10 height-adjustable stand with baseplate
- 11 lifters (four)
- 11a path traced by lifters
- 12 test portion
- 13 gas inlet

**Figure 2 — Example of an installation, which could be used to measure the temperature and temperature distribution within the gas stream and test portion in the reduction tube**

## Annex A (normative)

### Flowsheet of the procedure for the acceptance of test results

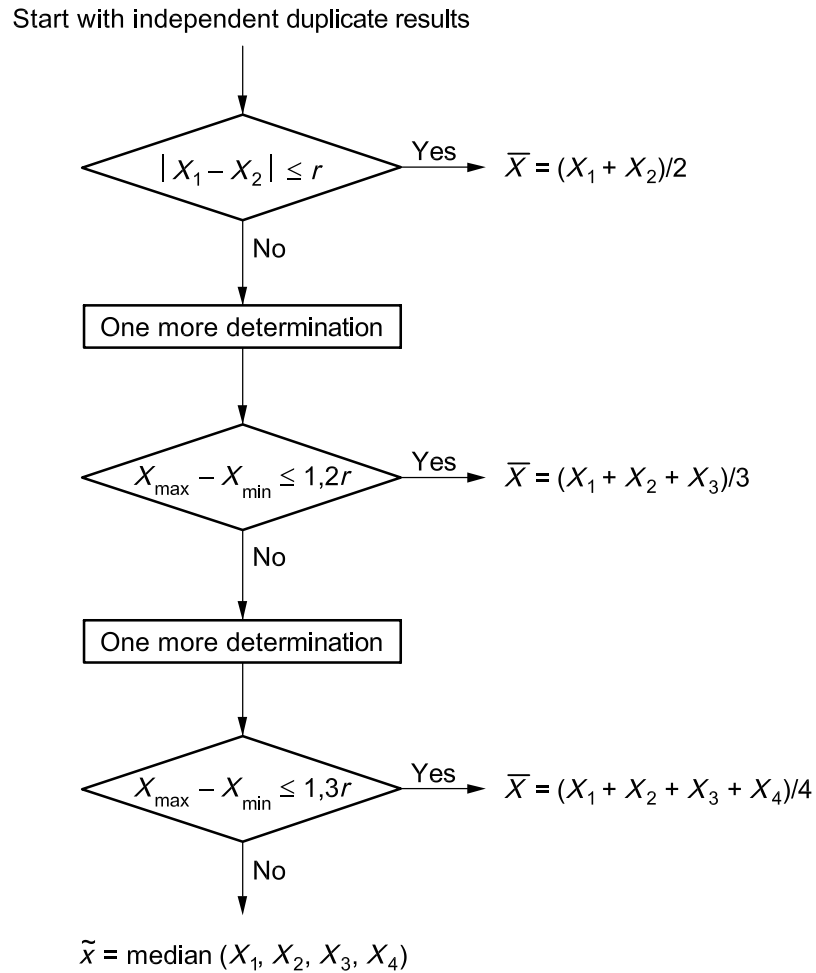

$r$ : see Table 1

---

---

**ICS 73.060.10**

Price based on 9 pages