
**Specification and qualification of welding
procedures for metallic materials —
Welding procedure test —**

**Part 2:
Arc welding of aluminium and its alloys**

*Descriptif et qualification d'un mode opératoire de soudage pour les
matériaux métalliques — Épreuve de qualification d'un mode opératoire
de soudage —*

Partie 2: Soudage à l'arc de l'aluminium et de ses alliages



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15614-2 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 10, *Unification of requirements in the field of metal welding*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

ISO 15614 consists of the following parts, under the general title *Specification and qualification of welding procedures for metallic materials — Welding procedure test*:

- *Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys*
- *Part 2: Arc welding of aluminium and its alloys*
- *Part 3: Arc welding of cast iron*
- *Part 4: Finishing welding of aluminium castings*
- *Part 5: Arc welding of titanium, zirconium and their alloys*
- *Part 6: Arc welding of copper and its alloys*
- *Part 7: Corrosion resistant overlay, cladding restore and hardfacing*
- *Part 8: Welding of tubes to tube-plate joints*
- *Part 9: Arc underwater hyperbaric wet welding*
- *Part 10: Underwater hyperbaric dry welding*
- *Part 11: Electron and laser beam welding*
- *Part 12: Spot, seam and projection welding*
- *Part 13: Resistance butt and flash welding*

Annex ZB provides a list of corresponding International and European Standards for which equivalents are not given in the text.

For the purposes of this part of ISO 15614, the CEN annex regarding fulfilment of European Council Directives has been removed.

Contents

Page

Foreword.....	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Preliminary welding procedure specification (pWPS)	2
5 Welding procedure test	2
6 Test piece	3
6.1 General.....	3
6.2 Shape and dimensions of test pieces	3
6.3 Welding of test pieces	7
7 Examination and testing	7
7.1 Extent of testing.....	7
7.2 Location of test specimens	8
7.3 Non-destructive testing.....	12
7.4 Destructive tests	12
7.5 Acceptance levels.....	15
7.6 Re-testing	15
8 Range of qualification	16
8.1 General.....	16
8.2 Related to the manufacturer.....	16
8.3 Related to the parent material	16
8.4 Common to all welding procedures.....	19
8.5 Specific to processes.....	22
9 Welding procedure qualification record (WPQR)	22
Annex A (informative) Welding Procedure Qualification Record form (WPQR)	24
Annex ZB (normative) Normative references to international publications with their relevant European publications	27
Bibliography	29

Figures

Figure 1 — Test piece for a butt joint in plate with full penetration	4
Figure 2 — Test piece for a butt joint in pipe with full penetration	5
Figure 3 — Test piece for a T-joint.....	5
Figure 4 — Test piece for a branch connection	7
Figure 5 — Location of test specimens for a butt joint in plate	9
Figure 6 — Location of test specimens for a butt joint in pipe	10
Figure 7 — Location of test specimens for a T-joint.....	11
Figure 8 — Location of test specimens for a branch connection or a fillet weld on pipe	11

Tables

Table 1 — Examination and testing of the test pieces	8
Table 2 — Efficiency for tensile strength of butt joints	13
Table 3 — Examples of maximum calculated former diameter for some elongations and thicknesses	15
Table 4 — Range of qualification for similar and dissimilar metal joints	17
Table 5 — Range of qualification for parent material thickness for plates and pipes	18
Table 6 — Range of qualification for the throat thickness for plates and pipes	19
Table 7 — Range of qualification for pipe and branch connection diameters.....	19
Table 8 — Range of qualification for type of joint	21

Foreword

This document (EN ISO 15614-2:2005) has been prepared by Technical Committee CEN/TC 121 “Welding”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2005, and conflicting national standards shall be withdrawn at the latest by October 2005.

This document supersedes EN 288-4:1992.

EN ISO 15614 consists of the following parts, under the general title *Specification and qualification of welding procedures for metallic materials — Welding procedure test*:

- *Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys*
- *Part 2: Arc welding of aluminium and its alloys*
- *Part 3: Welding procedure tests for the arc welding of cast iron ¹⁾*
- *Part 4: Finishing welding of aluminium castings ¹⁾*
- *Part 5: Arc welding of titanium, zirconium and their alloys*
- *Part 6: Arc welding of copper and its alloys ¹⁾*
- *Part 7: Overlay welding¹⁾*
- *Part 8: Welding of tubes to tube-plate joints*
- *Part 10: Hyperbaric dry welding ¹⁾*
- *Part 11: Electron and laser beam welding*
- *Part 12: Spot, seam and projection welding*
- *Part 13: Resistance butt and flash welding ¹⁾*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

¹⁾ To be published.

Introduction

All new welding procedure tests are to be carried out in accordance with this document from the date of this issue.

However, this document does not invalidate previous welding procedure tests made to former standards or specifications or previous issues of this document.

Where additional tests have to be carried out to make the qualification technically equivalent, it is only necessary to do the additional tests on a test piece which should be made in accordance with this document.

Requests for official interpretations of any aspect of this document should be directed to the Secretariat of ISO/TC 44/SC 10 via your national standards body, a complete listing which can be found at www.iso.org.

.....

1 Scope

This document specifies how a preliminary welding procedure specification is qualified by welding procedure tests.

This document is part of a series of standards, details of this series are given in EN ISO 15607:2003, Annex A.

This document defines the conditions for the execution of welding procedure tests and the range of qualification for welding procedures for all practical welding operations within the range of variables listed in Clause 8.

This document applies to the arc welding of wrought and cast aluminium and its alloys. In this document the term aluminium stands for aluminium and for aluminium alloys.

This document does not apply to finishing welding of aluminium castings which is dealt by prEN ISO 15614-4.

Arc welding of aluminium is covered by the following welding processes in accordance with EN ISO 4063:

- 131 : metal inert gas welding (MIG welding);
- 141 : tungsten inert gas welding (TIG welding);
- 15 : plasma arc welding.

NOTE Specific service, material or manufacturing conditions may require more comprehensive testing than is specified by this document (see 7.1).

The principles of this document may be applied to other fusion welding processes.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 515, *Aluminium and aluminium alloys — Wrought products — Temper designations*.

EN 571-1, *Non destructive testing — Penetrant testing — Part 1: General principles*.

EN 1714, *Non-destructive examination of welds — Ultrasonic examination of welded joints*.

EN ISO 6947, *Welds — Working positions — Definitions of angles of slope and rotation (ISO 6947:1993)*.

EN ISO 9606-2, *Qualification test of welders — Fusion welding — Part 2: Aluminium and aluminium alloys (ISO 9606-2:2004)*.

EN ISO 15607:2003, *Specification and qualification of welding procedures for metallic materials — General rules (ISO 15607:2003)*.

EN ISO 15609-1, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 1: Arc welding (ISO 15609-1:2004)*.

EN ISO 15613, *Specification and qualification of welding procedures for metallic materials — Qualification based on pre-production welding test (ISO 15613:2004)*.

ISO 4136, *Destructive tests on welds in metallic materials — Transverse tensile test*.

ISO 5173, *Destructive tests on welds in metallic materials — Bend tests*.

ISO 15614-2:2005(E)

ISO 9017, *Destructive tests on welds in metallic materials — Fracture test.*

ISO 10042, *Arc-welded joints in aluminium and its weldable alloys — Guidance on quality levels for imperfections.*

ISO 14175, *Welding consumables — Shielding gases for arc welding and cutting.*

ISO 14732, *Welding personnel — Approval testing of welding operators for fusion welding and resistance weld setters for fully mechanized and automatic welding of metallic materials.*

ISO 17635, *Non-destructive testing of welds — General rules for fusion welds in metallic materials .*

ISO 17636, *Non-destructive testing of welds — Radiographic testing of fusion-welded joints.*

ISO 17637, *Non-destructive testing of welds — Visual testing of fusion-welded joints*

ISO 17639, *Destructive tests on welds in metallic materials — Macroscopic and microscopic examination of welds.*

ISO/TR 15608, *Welding — Guidelines for a metallic material grouping system.*

ISO/TR 17671-1, *Welding — Recommendations for welding of metallic materials — Part 1: General guidance for arc welding.*

ISO/TR 17671-4, *Welding — Recommendations for welding of metallic materials — Part 4: Arc welding of aluminium and aluminium alloys.*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 15607:2003 and the following apply.

3.1 finishing welding

welding carried out during production in order to remove casting defects and core openings to ensure the agreed quality of castings

4 Preliminary welding procedure specification (pWPS)

The preliminary welding procedure specification shall be prepared in accordance with EN ISO 15609-1. It shall specify the tolerance for all the relevant parameters.

Guidance for the welding of aluminium is given in ISO/TR 17671-1 and ISO/TR 17671-4.

5 Welding procedure test

The welding and testing of test pieces shall be in accordance with Clauses 6 and 7.

The welder or welding operator who undertakes the welding procedure test satisfactorily in accordance with this document is qualified for the appropriate range of qualification in accordance with EN ISO 9606-2 or ISO 14732, providing that the relevant testing requirements are met.

6 Test piece

6.1 General

The welded joint to which the welding procedure will relate in production shall be represented by making a standardized test piece or pieces, as specified in 6.2. Where the production/joint geometry requirements do not represent the standardized test pieces as shown in this document, the use of EN ISO 15613 shall be required.

6.2 Shape and dimensions of test pieces

6.2.1 General

The length or number of test pieces shall be sufficient to allow all required tests to be carried out.

Additional test pieces, or longer test pieces than the minimum size, may be prepared in order to allow for extra and or for re-testing specimens (see 7.6).


For all test pieces except branch connections (see Figure 4) and T-joints (see Figure 3) the material thickness, t , shall be the same for both plates/pipes to be welded. If required by the application standard, the direction of working, e.g. for extrusion, shall be marked on the test piece.

The material thickness and/or pipe outside diameter of the test pieces shall be selected in accordance with 8.3.2.1 to 8.3.2.4.

The shape and minimum dimensions of the test piece shall be as follows:

6.2.2 Butt joint in plate with full penetration

The test piece shall be prepared in accordance with Figure 1.

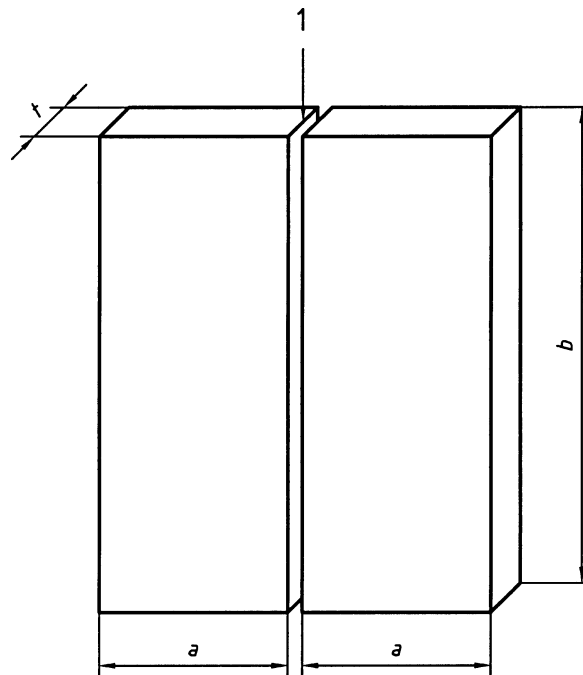

Key

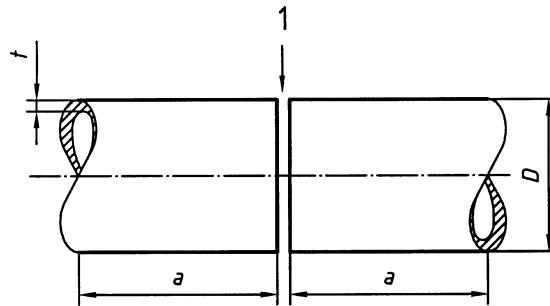
- 1 Joint preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)
- a* Minimum value 150 mm (transverse bend test specimens may require a larger *a*, see 7.4)
- b* Minimum value 300 mm
- t* Material thickness

Figure 1 — Test piece for a butt joint in plate with full penetration

6.2.3 Butt joint in pipe with full penetration

The test piece shall be prepared in accordance with Figure 2.

NOTE The word "pipe" alone or in combination is used to mean "pipe", "tube" or "hollow section".

**Key**


- 1 Joint preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)
- a Minimum value 150 mm
- D Outside pipe diameter
- t Material thickness

Figure 2 — Test piece for a butt joint in pipe with full penetration

6.2.4 T-joint

The test piece shall be prepared in accordance with Figure 3.

This may be used for fully penetrated butt welds or fillet welds.

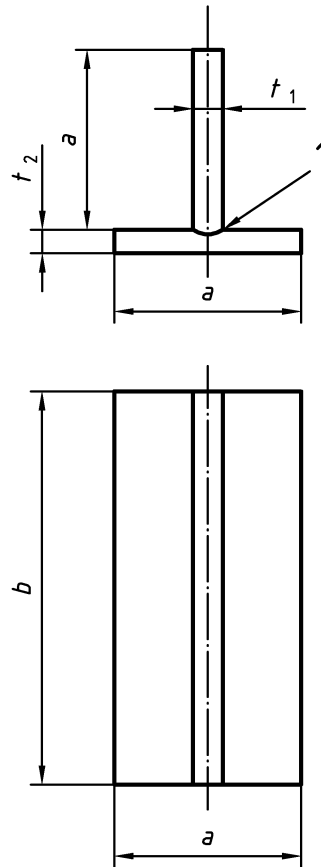

Key


- 1 Weld one side or both sides and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)
- a* Minimum value 150 mm
- b* Minimum value 300 mm
- t* Material thickness

Figure 3 — Test piece for a T-joint

6.2.5 Branch connection and fillet weld on pipe

The test piece shall be prepared in accordance with Figure 4. The branch angle α is the minimum to be used in production.

This may be used for fully penetrated joints (set-on or set-in or set-through joint) and for T-joints.

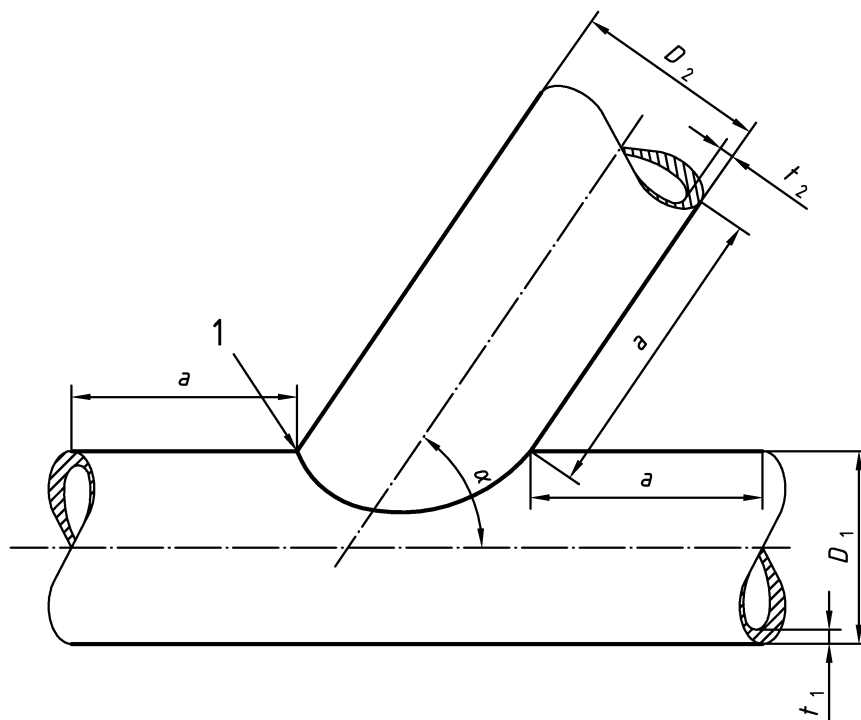

Key

- 1 Joint preparation and fit-up as detailed in the preliminary Welding Procedure Specification (pWPS)
- a Minimum value 150 mm
- D_1 Outside diameter of the main pipe
- D_2 Outside diameter of the branch pipe
- t_1 Main pipe material thickness
- t_2 Branch pipe material thickness
- α Branch angle

Figure 4 — Test piece for a branch connection

6.3 Welding of test pieces

Preparation and welding of test pieces shall be carried out in accordance with the pWPS and under the conditions of welding in production which they shall represent. Welding positions and limitations for the angle of slope and rotation of the test piece shall be in accordance with EN ISO 6947. If tack welds are to be fused into the production joint, they shall be included in the test piece.

Welding and testing of the test pieces shall be witnessed by an examiner or examining body.

7 Examination and testing

7.1 Extent of testing

Testing includes both non-destructive testing (NDT) and destructive testing, which shall be in accordance with the requirements of Table 1.

An application standard may specify additional tests, e.g.:

- longitudinal weld tensile test;
- weld metal bend test or special weld metal bend test to measure elongation;
- tensile test for the determination of the 0,2 % proof strength and/or elongation;
- chemical analysis;
- cruciform test.

NOTE Specific service, material or manufacturing conditions may require more comprehensive testing than is specified by this document in order to gain more information and to avoid repeating the welding procedure test at a later date just to obtain additional test data.

Table 1 — Examination and testing of the test pieces


Test piece	Type of test	Extent of testing	Footnote
Butt joint with full penetration (Figures 1 and 2)	Visual	100 %	—
	Radiographic or ultrasonic	100 %	—
	Penetrant testing	100 %	—
	Transverse tensile test	2 test specimens	—
	Transverse bend test or fracture test for cast materials or wrought/cast combinations	2 root and 2 face test specimens	a
	Macroscopic examination	1 test specimen	—
	Microscopic examination	1 test specimen	b
T- joint with full penetration - Figure 3 Branch connection ^c with full penetration Figure 4	Visual	100 %	—
	Penetrant testing	100 %	—
	Macroscopic examination	4 test specimens	d
	Microscopic examination	1 test specimen	b
Fillet welds ^c Figure 3 and Figure 4	Visual	100 %	—
	Penetrant testing	100 %	—
	Macroscopic examination	2 test specimens	—
	Microscopic examination	1 test specimen	b
<p>^a Two root and two face bend test specimens may be preferably substituted by four side bend test specimens for $t \geq 12$ mm.</p> <p>^b Only for material group 23 and all casting alloys.</p> <p>^c Tests as detailed do not provide information on the mechanical properties of the joint. Where these properties are relevant to the application an additional qualification shall also be held e.g. a butt joint qualification.</p> <p>^d For test specimens according to Figure 3, only two macro test specimens.</p>			

7.2 Location of test specimens

Test specimens shall be taken in accordance with Figures 5, 6, 7 and 8.

Test specimens shall be taken after all non-destructive testing (NDT) has been carried out and which has passed the relevant inspection criteria for the NDT method(s) used.

It is acceptable to take the test specimens from locations avoiding areas which have imperfections within the acceptance limits for the NDT method(s) used.

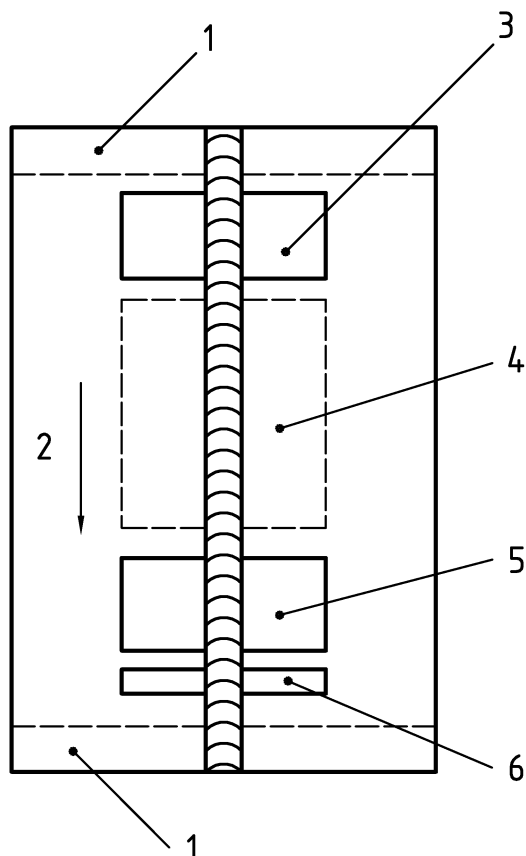


Key

- 1 Discard 25 mm
- 2 Welding direction
- 3 Area for:
 - 1 tensile test specimen
 - bend test specimens or fracture test specimens
- 4 Area for:
 - additional test specimens if required
- 5 Area for:
 - 1 tensile test specimen
 - bend test specimens or fracture test specimens
- 6 Area for:
 - 1 macro test specimen
 - 1 micro test specimen

NOTE Not to scale.

Figure 5 — Location of test specimens for a butt joint in plate

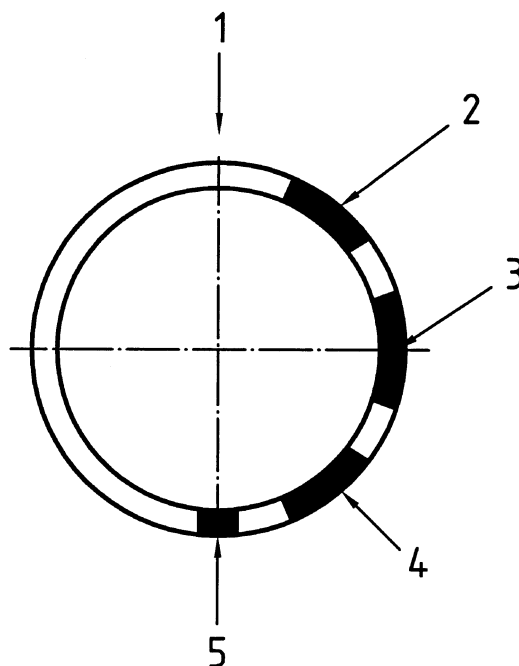


Key

- 1 Top of fixed pipe
- 2 Area for: — 1 tensile test specimen
— bend test specimens or fracture test specimens
- 3 Area for: — additional test specimens if required
- 4 Area for: — 1 tensile test specimen
— bend test specimens or fracture test specimens
- 5 Area for: — 1 macro test specimen
— 1 micro test specimen

NOTE Not to scale.


Figure 6 — Location of test specimens for a butt joint in pipe

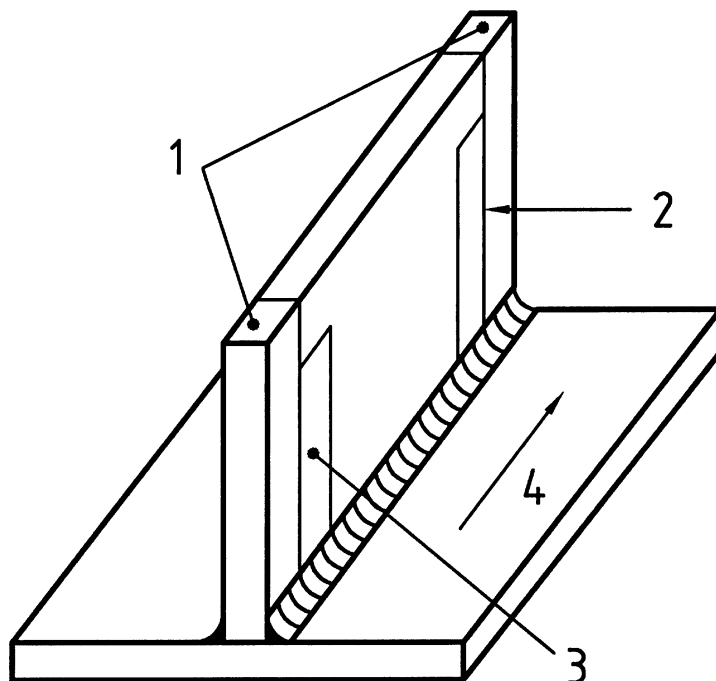

Key

- 1 Discard 25 mm
- 2 Micro and macro test specimens
- 3 1 macro test specimen
- 4 Welding direction

Figure 7 — Location of test specimens for a T-joint

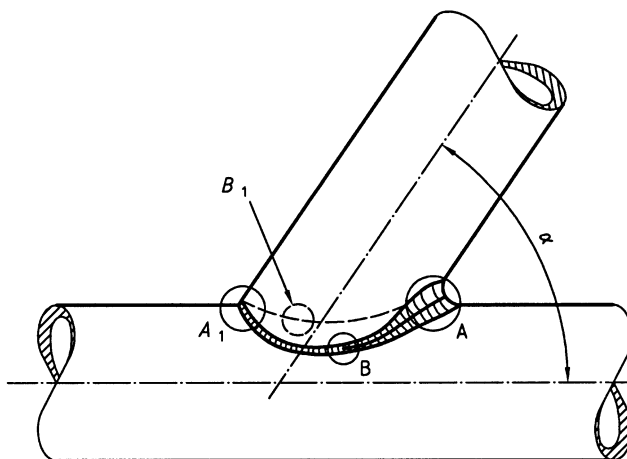

Key

α Branch angle

Macro test specimens to be taken in positions A and A₁ and B and B₁
 Micro test specimen to be taken in position A

Figure 8 — Location of test specimens for a branch connection or a fillet weld on pipe

7.3 Non-destructive testing

All non-destructive testing in accordance with 7.1 and Table 1 shall be carried out on the test pieces prior to cutting of the test specimens.

Depending upon joint geometry, materials and the requirements for work, the NDT shall be carried out as required in Table 1 in accordance with ISO 17637 (visual examination), ISO 17636 (radiographic examination), EN 1714 (ultrasonic examination), EN 571-1 (penetrant testing).

7.4 Destructive tests

7.4.1 General

The extent of testing shall be as required by Table 1.

7.4.2 Transverse tensile test

Test specimens and testing for transverse tensile testing for butt joints shall be in accordance with ISO 4136.

For pipes > 50 mm outside diameter, the excess weld metal shall be removed on both faces to give the test specimen a thickness equal to the wall thickness of the pipe.

For pipes ≤ 50 mm outside diameter, and when full section small diameter pipes are used, the excess weld metal may be left undressed on the inside surface of the pipe.

The tensile strength of the test specimen shall not be less than the corresponding specified minimum value for the parent material required in the relevant standard, in the "O" condition for groups 21 and 22, see Table 2.

The tensile strength $R_m(w)$ of the welded test specimen in the as post-welded condition shall satisfy the following requirement:

$$R_m(w) = R_m(pm) \times T$$

where

$R_m(w)$ is the tensile strength of the welded test specimen in the as post-welded condition;

$R_m(pm)$ is the specified minimum tensile strength of the parent material required in the relevant standard;

T is the joint efficiency factor.

For combinations between different alloys the lowest individual $R_m(w)$ value shall be achieved.

Table 2 — Efficiency for tensile strength of butt joints

Material group or sub-group (see ISO/TR 15608)	Temper condition of parent material before welding ^{a b}	Post weld condition ^c	$T = \frac{R_m(w)}{R_m(pm)}$
21	All temper conditions	As welded	1,0 ^d
22	All temper conditions	As welded	1,0 ^d
23.1	T4	Natural ageing	0,7
	T4	Artificial ageing	0,7 ^{e f}
	T5 and T6	Natural ageing	0,6
	T5 and T6	Artificial ageing	0,7 ^f
23.2	T4	Natural ageing	0,95
	T4	Artificial ageing	0,75 ^{e f}
	T6	Natural ageing	0,75
	T6	Artificial ageing	0,75 ^f
Other alloys	All temper conditions	— ^g	— ^g

^a See EN 515.
^b For parent material in other tempers not shown in the Table, $R_m(w)$ shall be in accordance with the design specification.
^c Ageing conditions shall be in accordance with the design specification.
^d $R_m(pm)$ is based on the specified minimum tensile strength of the "O" condition, irrespective of the actual parent material temper used for the test.
^e When the test pieces are artificially aged after welding and prior to testing, the efficiency factor T applies to the T6 parent material condition.
^f Higher properties may be achieved if post-weld full heat treatment is applied. $R_m(w)$ shall be in accordance with the design specification.
^g The post weld ageing conditions and $R_m(w)$ shall be in accordance with the design specification.

7.4.3 Bend test

Test specimens for bend testing for butt joints shall be in accordance with ISO 5173.

For all groups the bend angle shall be 180° using the calculated former diameter based upon material elongation as follows:

— For elongation > 5 %

$$d = \frac{100 \times t_s}{A} - t_s$$

where

d is the maximum former diameter

t_s is the thickness of the bend test specimen (this includes side bends)

A is the minimum tensile elongation required by the manufacturer material specification (for combination between different alloys the lowest individual value shall be used).

Table 3 gives examples of maximum calculated former diameter for some elongations and thicknesses.

ISO 15614-2:2005(E)

Values shall be rounded down to aid those performing tests.

A smaller former diameter may be used at the discretion of the testing facility.

- For elongation $\leq 5\%$ annealing shall be carried out before testing. The former diameter shall be calculated with the elongation given by the specified "O" temper conditions.

During testing, the test specimens shall not reveal any one single flaw > 3 mm in any direction. Flaws appearing at the corners of a test specimen during testing shall be ignored in the evaluation.

Table 3 — Examples of maximum calculated former diameter for some elongations and thicknesses

Thickness of the bend test specimen t_s mm	Elongation A %							
	8	10	12	15	17	20	25	35
	Maximum calculated former diameter d mm							
4	46	36	29	23	20	16	12	7
6	69	54	44	34	29	24	18	11
8	92	72	59	45	39	32	24	15
10	115	90	73	57	49	40	30	19
12	138	108	88	68	59	48	36	22
15	172	135	110	85	73	60	45	28
20	230	180	147	113	98	80	60	37
25	288	225	183	142	122	100	75	46
30	345	270	220	170	146	120	90	56
35	402	315	257	198	171	140	105	65
40	460	360	293	227	195	160	120	74

7.4.4 Fracture test

Test specimens and testing for fracture test for butt joints shall be in accordance with ISO 9017.

7.4.5 Macroscopic/Microscopic examination

The test specimen shall be prepared and examined in accordance with ISO 17639 on one side to clearly reveal the fusion line, the HAZ and the build up of the runs.

The macroscopic examination shall include unaffected parent material.

The acceptance levels stated in 7.5 shall apply.

Care should be taken when etching certain alloys to avoid producing crack like indications.

7.5 Acceptance levels

A welding procedure is qualified if the imperfections in the test piece are within the specified limits of level B in EN 30042 except for imperfection types as follows: excess weld metal, excess convexity, excess throat thickness and excessive penetration, for which level C shall apply.

The correlation between the quality levels of ISO 10042 and the acceptance levels of the different NDT techniques are given in ISO 17635.

7.6 Re-testing

If the test piece fails to comply with any of the requirements for visual examination or NDT specified in 7.5, one further test piece shall be welded and subjected to the same examination. If this additional test piece does not comply with the requirements, the welding procedure test has failed.

If any test specimens fail to comply with the requirements for destructive testing in accordance with 7.4 but only due to weld imperfections, two further test specimens shall be tested for each one that failed. The additional test specimens can be taken from the same test piece, if there is sufficient material, or from a new test piece.

If a tensile test specimen fails to meet the requirements of 7.4.2, two further test specimens shall be obtained for each one that failed. Both shall satisfy the requirements of 7.4.2.

Each additional test specimen shall be subjected to the same tests as the initial test specimen that failed. If either of the additional test specimens does not comply with the requirements, the welding procedure test has failed.

8 Range of qualification

8.1 General

Each of the conditions given in Clause 8 shall be met in order to comply with this document.

Changes outside of the ranges specified shall require a new welding procedure test.

8.2 Related to the manufacturer

A qualification of a pWPS by a welding procedure test according to this document obtained by a manufacturer is valid for welding in workshops or sites under the same technical and quality control of the manufacturer.

Welding is under the same technical and quality control when the manufacturer who performed the welding procedure test retains complete responsibility for all welding carried out to it.

8.3 Related to the parent material

8.3.1 Parent material grouping

In order to minimize the number of welding procedure tests, aluminium and aluminium alloys are grouped according to ISO/TR 15608.

The grouping is made in respect of the intentional added elements but not for trace impurities.

Separate welding procedure qualifications are required for each parent material or parent material combinations not covered by the grouping system.

Permanent backing material shall be considered as a parent material within the qualification (sub-)group.

The range of qualification for similar and dissimilar joints is given in Table 4.

Any dissimilar metal joint not covered by Table 4 shall require a specific test with no range of qualification for other parent materials.

For verification of mechanical properties additional test pieces may be required on similar metal joints.

Any qualification obtained for a dissimilar metal joint gives qualification for each sub-group of parent material welded with the same type of filler metal.

Table 4 — Range of qualification for similar and dissimilar metal joints

Material (sub-) group of the test piece	Similar joint range (sub-) groups	Dissimilar joint range (sub-) groups
21 to 21	21 to 21	Not applicable
22.1 to 22.1	22.1 to 22.1	22.1 to 22.2
	22.2 to 22.2	
22.2 to 22.2	22.2 to 22.2	22.1 to 22.2
	22.1 to 22.1	
22.3 to 22.3	22.3 to 22.3	Combinations between 22.1, 22.2, 22.3 and 22.4
	22.1 to 22.1	
	22.2 to 22.2	
	22.4 to 22.4	
22.4 to 22.4	22.4 to 22.4	Combinations between 22.1, 22.2, 22.3 and 22.4
	22.1 to 22.1	
	22.2 to 22.2	
	22.3 to 22.3	
23.1 to 23.1	23.1 to 23.1	Combinations between 22.1, 22.2 ^a , 22.3 ^a and 22.4 ^a
	22.1 to 22.1	
	22.2 to 22.2 ^a	
	22.3 to 22.3 ^a	
	22.4 to 22.4 ^a	
23.2 to 23.2	23.2 to 23.2	23.2 to 23.1 Combinations between 22.1, 22.2 ^a , 22.3 ^a and 22.4 ^a
	23.1 to 23.1	
	22.1 to 22.1	
	22.2 to 22.2 ^a	
	22.3 to 22.3 ^a	
	22.4 to 22.4 ^a	
24.1 to 24.1	24.1 to 24.1	Not applicable
24.2 to 24.2	24.2 to 24.2	24.2 to 24.1 and 24.2 to 23.1 ^b
	24.1 to 24.1	
	23.1 to 23.1 ^b	
25 to 25	25 to 25	25 to 24.1 25 to 24.2
	24.1 to 24.1	
	24.2 to 24.2	
26 to 26	26 to 26	26 to any of 24.1 ^c , 24.2 ^c or 25 ^c
	24.1 to 24.1 ^c	
	24.2 to 24.2 ^c	
	25 to 25 ^c	
NOTE The qualification is valid provided the same filler material is used.		
^a Provided Al-Mg filler material is used.		
^b Provided Al-Si filler material is used.		
^c Only for castings.		

8.3.2 Parent material thickness and pipe diameter

8.3.2.1 General

Nominal thickness t shall have the following meanings:

a) For a butt joint:

the parent material thickness which, for joints between dissimilar thicknesses, is that of the thinner material.

b) For a fillet weld:

the parent material thickness qualified for joints between different thicknesses is that of the thinner material. For each thickness range qualified as in Table 5 there is also an associated range of qualified fillet weld throat thicknesses as given in 8.3.2.3.

c) For a set-on branch connection:

the thickness of the branch pipe.

d) For a set-in or set-through branch connection:

the thickness of the main pipe.

8.3.2.2 Range of qualification for parent material thickness

The qualification of a welding procedure test on thickness *t* for single and multi-run processes shall include qualification for thickness ranges given in Table 5.

For multi-process procedures, the deposited weld metal thickness for each welding process may be used as a basis for the range of qualification for the individual welding process.

For automatic single run processes the depth of penetration is the maximum depth qualified.

Table 5 — Range of qualification for parent material thickness for plates and pipes

Dimensions in millimetres

Thickness of the test piece <i>t</i>	Range of qualification
$t \leq 3$	0,5 <i>t</i> to 2 <i>t</i>
$3 < t \leq 20$	3 to 2 <i>t</i>
$t > 20$	$\geq 0,8 t$

8.3.2.3 Range of qualification for throat thickness of fillet welds

In addition to the requirements of Table 5, the range of qualification of the throat thickness a is given in Table 6.

Table 6 — Range of qualification for the throat thickness for plates and pipes

Dimensions in millimetres

Throat thickness of the test piece a	Range of qualification
$a < 10$	0,75 a to 1,5 a
$a \geq 10$	$\geq 7,5$

Where a fillet weld is qualified by means of a butt weld test, the throat thickness range qualified shall be based on the thickness of the deposited weld metal.

Where the majority of production work is fillet welding, an additional fillet weld test may be required.

8.3.2.4 Range of qualification for the diameter of pipes and branch connections

The qualification of a welding procedure test on diameter D shall include qualification for diameters in the following ranges given in Table 7.

Qualification given for plates also covers pipes when the outside diameter is > 500 mm or when the diameter is > 150 mm welded in the welding position PA or PC (rotated position).

Table 7 — Range of qualification for pipe and branch connection diameters

Dimensions in millimetres

Diameter of the test piece D^a	Range of qualification
$D \leq 25$	0,5 D to 2 D
$D > 25$	$\geq 0,5 D$ (25 mm min)
NOTE For structural hollow section, D is the dimension of the smaller side.	
^a D is the outside diameter of the pipe or outside diameter of the branch pipe.	

8.3.3 Angle of branch connection

A welding procedure test carried out on a branch connection with angle α shall qualify all branch angles α_1 in the range of $\alpha \leq \alpha_1 \leq 90^\circ$.

8.4 Common to all welding procedures

8.4.1 Welding process

Each degree of mechanisation shall be qualified independently (manual, partly mechanised, fully mechanised and automatic).

The qualification is only valid for the welding process(es) used in the welding procedure test.

For multi-process procedures the welding procedure qualification may be carried out with separate welding procedure tests for each welding process. It is also possible to make the welding procedure test as a multi-

process procedure test. The qualification of such a test is only valid for the process sequence carried out during the multi-process procedure test.

NOTE It is not allowed to use a multi-process procedure test to qualify any single process unless the testing carried out on the welding process conforms to this document.

8.4.2 Welding positions

Welding of a test in any one position (pipe or plate) qualifies for welding in all positions (pipe or plate) except for PG and J-L045 where a separate welding procedure test is required.

8.4.3 Type of joint

The range of qualification for the types of welded joints used in the welding procedure test is given in Table 8. In this table the range of qualification is indicated in the same horizontal line.

It is not permitted to change a multi-run deposit into a single run (or single run on each side) or vice versa for a given welding process.

1

Table 8 — Range of qualification for type of joint

Type of joint in the test piece used in the welding procedure test			Range of qualification								
			Butt joint on plate ^b				Butt joint on pipe		Branch connections		Fillet welds on pipe and plate
			Welded from one side		Welded from both sides		Welded from one side		Welded from one side	Welded from both sides	
			with backing	no backing	with gouging	no gouging	with backing	no backing	—	—	—
Butt joint on plate ^b	Welded from one side	with backing	X	—	X	—	X ^a	—	—	X ^a	X
		no backing	X	X	X	X	X ^a	X ^a	X ^a	X ^a	X
	Welded from both sides	with gouging	X	—	X	—	X ^a	—	—	X ^a	X
		no gouging	X	—	X	X	—	—	—	X ^a	X
Butt joint on pipe	Welded from one side	with backing	X	—	X	—	X	—	—	X	X
		no backing	X	X	X	X	X	X	X	X	X
Branch connections	Welded from one side	—	—	—	—	—	—	—	X	X	X
	Welded from both sides	—	—	—	—	—	—	—	—	X	X
Fillet welds on plate and pipe	—	—	—	—	—	—	—	—	—	—	X

Key :
X indicates those welding types of joint covered by the WPS.
— indicates those welding types of joint not covered by the WPS.
^a Plate qualifies pipe with $D > 500$ mm.
^b Butt joints on plate qualify T-joints.

8.4.4 Filler metal, designation

The range of qualification for filler metals covers other filler metals within the same type defined in ISO/TR 17671-4.

8.4.5 Type of current

The qualification is given for the type of current (alternating current (AC), direct current (DC), pulsed current) and polarity used in the welding procedure test.

8.4.6 Heat Input

The requirements of this clause only apply when the control of heat input is specified.

ISO 15614-2:2005(E)

The upper limit of heat input qualified is 25 % greater than that used in welding the test piece.

The lower limit of heat input qualified is 25 % lower than that used in welding the test piece.

Heat input is calculated in accordance with ISO/TR 17671-1.

8.4.7 Preheat temperature

When preheating is required, the lower limit of qualification is the nominal preheat temperature applied at the start of the welding procedure test.

8.4.8 Interpass temperature

The upper limit of qualification is the highest interpass temperature reached in the welding procedure test.

8.4.9 Post-weld heat treatment or ageing

Post weld heat treatment e.g. artificial ageing, natural ageing shall be specified in the pWPS in accordance with EN 515. Addition or deletion of post-weld heat treatment or ageing is not permitted.

The temperature range and the ageing conditions specified in the pWPS is the range qualified.

8.5 Specific to processes

8.5.1 Process 131

8.5.1.1 The qualification given to the shielding gas is restricted to the symbol according to ISO 14175. Shielding gases not covered by ISO 14175 are restricted to the nominal composition used in the test.

8.5.1.2 The qualification given is restricted to the wire system used in the welding procedure test (e.g. single-wire or multiple-wire system).

8.5.2 Process 141

The qualification given to shielding gas and backing gas is restricted to the symbol according to ISO 14175 used in the welding procedure test. Shielding gases not covered by ISO 14175 are restricted to the nominal composition used in the test.

8.5.3 Process 15

8.5.3.1 The qualification given is restricted to the nominal composition of the plasma gas used in the welding procedure test.

8.5.3.2 The qualification given to the shielding gas and backing gas is restricted to the designation according to ISO 14175 used in the welding procedure test. Shielding gases not covered by ISO 14175 are restricted to the nominal composition used in the test.

9 Welding procedure qualification record (WPQR)

The welding procedure qualification record (WPQR) is a statement of the results of assessing each test piece including re-tests. The relevant items listed for the WPS in EN ISO 15609-1 shall be included, together with

details of any features that would be rejectable by the requirements of Clause 7. If no rejectable features or unacceptable test results are found, a WPQR detailing the welding procedure test piece results is qualified and shall be signed and dated by the examiner or examining body.

A WPQR format shall be used to record details for the welding procedure and the test results, in order to facilitate uniform presentation and assessment of the data.

An example of the WPQR format is shown in Annex A.

Annex A
(informative)

Welding Procedure Qualification Record form (WPQR)

Welding procedure qualification - Test certificate

Manufacturer's WPQR No.: Examiner or examining body

Manufacturer: Reference No.:

Address:

Code/ testing standard:

Date of welding:

Range of qualification

Welding process(es):

Type of joint and weld:

Parent material group (s) and sub-group(s):

Parent material thickness (mm):

Throat thickness (mm):

Single run/multi run:

Outside pipe diameter (mm):

Filler metal type:

Designation of shielding gas:

Designation of backing gas:

Type of welding current and polarity:

Heat input:

Welding positions:

Preheat temperature:

Interpass temperature:

Post-weld heat treatment and/or ageing:

Other information:

Certified that test welds prepared, welded and tested satisfactorily in accordance with the requirements of the code/testing standard indicated above.

Location	Date of issue	Examiner or examining body
		Name, date and signature

Record of weld test

Location: Examiner or examining body:
 Manufacturer's pWPS No.: Method of preparation and cleaning:
 Manufacturer's WPQR No.: Parent material specification:
 Manufacturer: Material thickness (mm):
 Welder's name: Outside pipe diameter (mm):
 Welding process: Welding position:
 Joint type and weld:
 Weld preparation details (sketch)* :

Joint design	Welding sequences

Welding details

Run	Welding process	Size of filler metal	Current A	Voltage V	Type of current/Polarity	Wire feed speed	Travel speed*	Heat input

Filler metal designation: Other information * e.g.:
 Any special baking or drying: weaving (maximum width of run):
 Gas : - Shielding: Oscillation (amplitude, frequency, dwell time):
 - Backing: Pulse welding details:
 Gas flow rate- Shielding: Distance contact tube/ workpiece:
 - Backing: Plasma welding details:
 Tungsten electrode type/size: Torch angle:
 Details of back gouging/backing:
 Preheat temperature:
 Interpass temperature:
 Post-weld heat treatment and/or ageing
 (time, temperature, method,
 heating and cooling rates):

.....
 Manufacturer
 Name, date and signature

.....
 Examiner or examining body
 Name, date and signature

* if required.

Test results

Manufacturer's WPQR No.:

Examiner or examining body

Reference No.:

Non-destructive testing

Type	Acceptable	Non-acceptable	Report No.
Visual examination			
Penetrant testing			
Radiographic testing			
Ultrasonic testing			

Metallographic examinations

Type	Acceptable	Non-acceptable	Report No.
Macro			
Micro			

Destructive tests

Tensile tests Required Yes No
:

Test temperature :

Type/No.	R_e N/mm ²	R_m N/mm ²	A % on	Z %	Fracture location	Remarks
Requirement						
1						
2						

Acceptable Yes No

Bend tests Required: Yes No

Type/No.	Bend side	Former diameter <i>d</i>	Result

Acceptable Yes No

Other tests*:

Remarks:

Tests carried out in accordance with the requirements of:

Laboratory report reference No.:

Test results were acceptable/not acceptable (delete as appropriate)

Tests carried out in the presence of:

.....
Examiner or examining body
Name date and signature

* if required.

Annex ZB (normative)

Normative references to international publications with their relevant European publications

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

NOTE Where an International Publication has been modified by common modifications, indicated by (mod.), the relevant EN/HD applies.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN</u>	<u>Year</u>
ISO 14175		Welding consumables — Shielding gases for arc welding and cutting	EN 439	
ISO 4136		Destructive tests on welds in metallic materials — Transverse tensile test	EN 895	
ISO 5173		Destructive tests on welds in metallic materials — Bend tests	EN 910	
ISO 17637		Non-destructive testing of welds — Visual testing of fusion-welded joints	EN 970	
ISO/TR 17671-1		Welding — Recommendations for welding of metallic materials — Part 1: General guidance for arc welding.	EN 1011-1	
ISO/TR 17671-4		Welding — Recommendations for welding of metallic materials — Part 4: Arc welding of aluminium and aluminium alloys.	EN 1011-4	
ISO 9017		Destructive tests on welds in metallic materials — Fracture test	EN 1320	
ISO 17639		Destructive tests on welds in metallic materials — Macroscopic and microscopic examination of welds	EN 1321	
ISO 14732		Welding personnel — Approval testing of welding operators for	EN 1418	

ISO 15614-2:2005(E)

fusion welding and of resistance weld setters for fully mechanized and automatic welding of metallic materials

ISO 17636		Non-destructive testing of welds — Radiographic testing of fusion-welded joints	EN 1435	
ISO 17635		Non-destructive testing of welds — General rules for fusion welds in metallic materials	EN 12062	
ISO 10042		Arc-welded joints in aluminium and its weldable alloys — Guidance on quality levels for imperfections	EN 30042	
ISO 6947		Welds — Working positions — Definitions of angles of slope and rotation.	EN ISO 6947	
ISO 9606-2		Qualification test of welders — Fusion welding — Part 2 : Aluminium and aluminium alloys	EN ISO 9606-2	
ISO 15607	2003	Specification and qualification of welding procedures for metallic materials — General rules.	EN ISO 15607	2003
ISO/TR 15608		Welding — Guidelines for a metallic material grouping system.	CR 15608	
ISO 15609-1		Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 1: Arc welding.	EN ISO 15609-1	
ISO 15613		Specification and qualification of welding procedures for metallic materials — Qualification based on pre-production welding test.	EN ISO 15613	

Bibliography

EN ISO 4063, *Welding and allied processes — Nomenclature of processes and reference numbers (ISO 4063:1998)*.

prEN ISO 15614-4, *Specification and qualification of welding procedures for metallic materials — Welding procedure tests — Part 4 : Finishing welding of aluminium castings* .

ICS 25.160.10

Price based on 29 pages