

---

---

**Plastics — Determination of the  
ultimate anaerobic biodegradation  
under high-solids anaerobic-digestion  
conditions — Method by analysis of  
released biogas**

*Plastiques — Évaluation de la biodégradation anaérobie ultime dans  
des conditions de digestion anaérobie à teneur élevée en solides —  
Méthode par analyse du biogaz libéré*





**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Test environment</b> .....	<b>2</b>
<b>6 Reagents</b> .....	<b>2</b>
<b>7 Apparatus</b> .....	<b>3</b>
<b>8 Procedure</b> .....	<b>3</b>
8.1 Preparation of the inoculum.....	3
8.2 Preparation of test material and reference material.....	4
8.3 Start-up of the test.....	4
8.4 Incubation period.....	4
8.5 Termination of the test.....	5
<b>9 Calculation and expression of results</b> .....	<b>5</b>
9.1 Calculation of gaseous carbon.....	5
9.2 Calculation of the percentage biodegradation.....	5
9.3 Calculation of loss in mass.....	6
9.4 Expression of results.....	6
<b>10 Validity of results</b> .....	<b>6</b>
<b>11 Test report</b> .....	<b>6</b>
<b>Annex A (informative) Principle of test system</b> .....	<b>8</b>
<b>Annex B (informative) Example of loss in mass determination</b> .....	<b>9</b>
<b>Bibliography</b> .....	<b>10</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information.

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

This second edition cancels and replaces the first edition (ISO 15985:2004). It also incorporates the Technical Corrigendum ISO 15985:2004/Cor.1:2007.

The main changes are:

- a) requirements regarding disintegration removed in the whole document;
- b) units added where necessary;
- c) bibliography updated.

## Introduction

New types of plastic are being developed in which biodegradability is a specifically sought-for characteristic. These plastics and derived products can be added to or used as feedstock for biological recycling and recovery in aerobic composting plants or anaerobic biogasification plants. To make sure these plastics are fit for biological recycling, their biodegradability must be demonstrated, preferably by standard test methods.

Standard test methods which determine the degree of biodegradation under aerobic, high-solids conditions have been developed (e.g. ISO 14855-1 and ISO 14855-2). However, it is well known from the literature that the degree of biodegradation can differ significantly depending on the environmental conditions such as the presence or the absence of oxygen (aerobic or anaerobic). To have a complete understanding of the biodegradation characteristics of a plastic under these different environmental conditions, various methods are required.

This International Standard specifies a method for the determination of the ultimate anaerobic biodegradation of plastic materials under high-solids conditions. This is representative of systems for the anaerobic biogasification of the organic fraction of municipal solid waste. Another method for determining the degree of anaerobic biodegradation is ISO 11734. However, this method is designed for soluble test materials in aqueous test conditions and at low concentrations (typically detergents) which is not typical of plastics.



# Plastics — Determination of the ultimate anaerobic biodegradation under high-solids anaerobic-digestion conditions — Method by analysis of released biogas

## 1 Scope

This International Standard specifies a method for the evaluation of the ultimate anaerobic biodegradability of plastics based on organic compounds under high-solids anaerobic-digestion conditions by measurement of evolved biogas at the end of the test. This method is designed to simulate typical anaerobic digestion conditions for the organic fraction of mixed municipal solid waste. The test material is exposed in a laboratory test to a methanogenic inoculum derived from anaerobic digesters operating only on pretreated household waste. The anaerobic decomposition takes place under high-solids (more than 20 % total solids) and static non-mixed conditions. The test method is designed to yield the percentage of carbon in the test material and its rate of conversion to evolved carbon dioxide and methane (biogas).

The conditions described in this International Standard might not always correspond to the optimum conditions for the maximum degree of biodegradation to occur.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 8245, *Water quality — Guidelines for the determination of total organic carbon (TOC) and dissolved organic carbon (DOC)*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **ultimate anaerobic biodegradation**

breakdown of an organic compound by microorganisms in the absence of oxygen to carbon dioxide, methane, water, and mineral salts of any other elements present (mineralization) plus new biomass

### 3.2

#### **total dry solids**

amount of solids obtained by taking a known mass of test material or inoculum and drying at about 105 °C to constant mass

### 3.3

#### **volatile solids**

amount of solids obtained by subtracting the residue of a known mass of test material or inoculum after incineration at about 550 °C from the total dry solids content of the same sample

Note 1 to entry: The volatile solids content is an indication of the amount of organic matter present.

### 3.4

#### **lag phase**

time, measured in days, from the start of a test until adaptation and/or selection of the degrading microorganisms is achieved and the degree of biodegradation of a chemical compound or organic matter has increased to about 10 % of the maximum level of biodegradation

### 3.5

#### **maximum level of biodegradation**

degree of biodegradation, measured in per cent, of a chemical compound or organic matter in a test, above which no further biodegradation takes place during the test

### 3.6

#### **biodegradation phase**

time, measured in days, from the end of the lag phase of a test until about 90 % of the maximum level of biodegradation has been reached

### 3.7

#### **plateau phase**

time, measured in days, from the end of the biodegradation phase until the end of the test

## 4 Principle

The test method is designed to be an optimized simulation of an intensive anaerobic digestion process and determines the ultimate biodegradability of a test material under high-solids anaerobic digestion conditions. The methanogenic inoculum is derived from anaerobic digesters operating on pretreated household waste, preferably only the organic fraction.

The test material is mixed with the inoculum and introduced into a static digestion vessel where it is intensively digested under optimum temperature and moisture conditions for a test period of 15 d or longer until a plateau in the biodegradation has been reached.

During the anaerobic biodegradation of the test material, methane, carbon dioxide, water, mineral salts, and new microbial cellular constituents (biomass) are the ultimate biodegradation products. The biogas (methane and carbon dioxide) evolved is continuously monitored or measured at regular intervals in test and blank vessels to determine the cumulative biogas production. The percentage biodegradation is given by the ratio of the amount of biogas evolved from the test material to the maximum theoretical amount of biogas that can be produced from the test material. The maximum theoretical amount of biogas produced is calculated from the measured total organic carbon (TOC). This percentage biodegradation does not include the amount of carbon converted to new cell biomass which is not metabolized in turn to biogas during the course of the test.

Additionally, the loss in mass of the test material can be determined at the end of the test.

## 5 Test environment

Incubation shall be in the dark or in diffused light in an enclosure that is maintained at a constant temperature of  $52\text{ °C} \pm 2\text{ °C}$ .

## 6 Reagents

Use only analytical-grade reagents.

Use thin-layer chromatography (TLC) grade cellulose with a particle size of less than  $20\text{ }\mu\text{m}$  as the positive-control reference material.



## 7 Apparatus

Ensure that all glassware is thoroughly cleaned and, in particular, free from organic or toxic matter.

The usual laboratory equipment and the following are required:

**7.1 Digestion vessels**, conical or other suitable glass flasks connected up so that no loss of gas occurs.

A minimum volume of 750 ml is recommended in view of the requirements of [8.2](#) and [8.3](#).

Weigh each empty digestion vessel if the loss in mass of the test material is to be determined.

**7.2 Gas volume measurement system**, comprising an inverted graduated cylinder or plastic column in water or another suitable device for measuring gas volume.

The water in contact with the gas shall be at a pH of less than 2 during the whole period of the test to avoid CO<sub>2</sub> loss through dissolution in the water. The gas volume measuring device, as well as the gas tubing, shall be of sufficient quality to prevent gas migration and diffusion between the system and the surrounding air.

**7.3 Apparatus for gas analysis** (optional), comprising a gas chromatograph, or other apparatus, equipped with a suitable detector and column(s) for measuring the methane and carbon dioxide concentration in the evolved gases.

**7.4 Analytical apparatus** (optional), for determining volatile fatty acids by aqueous-injection chromatography, as well as total Kjeldahl nitrogen, ammonia nitrogen, dry solids (at 105 °C) and volatile solids (at 550 °C).

## 8 Procedure

### 8.1 Preparation of the inoculum

The inoculum shall be obtained from a properly operating anaerobic digester using pretreated household waste as the sole feedstock. The pretreated household waste should preferably come from an existing waste treatment facility that is treating municipal solid waste where, through sorting, shredding, sieving or other means, a fairly homogeneous organic fraction is produced with a particle size of less than 60 mm.

The digester should have been operating for a period of at least 4 months using this organic fraction, with a retention time of a maximum of 30 d under thermophilic conditions (52 °C ± 2 °C). Gas evolution yields should be at least 15 ml of biogas at standard temperature and pressure per gram of dry solids in the digester and per day on average for at least 30 d.

The inoculum should be derived from a digester operating under dry (>20 % total solids) conditions. It can, however, also be derived from a wet fermentation process, the digested sludge being dewatered by centrifugation, by using a press or by drying at a maximum temperature of 55 °C to a total solids content of at least 20 %.

The prepared inoculum should undergo a short post-fermentation of approximately 7 d at the same operating temperature as that of the facility from which it was derived. This means that the inoculum is not fed but allowed to postferment anaerobically by itself. This is to ensure that large, easily biodegradable particles are degraded during this period and also to reduce the background level of degradation of the inoculum itself.

The most important biochemical characteristics of the inoculum shall be as follows:

— pH: between 7,5 and 8,5;

- volatile fatty acids (VFA): below 1 g/kg of wet mass;
- ionized-ammonia nitrogen ( $\text{NH}_4^+\text{-N}$ ): between 0,5 g/kg and 2 g/kg of wet mass.

## 8.2 Preparation of test material and reference material

Determine the total organic carbon (TOC) in the test material and the reference material using e.g. ISO 8245 and report it preferably as grams of TOC per gram of total dry solids. Alternatively, if the materials do not contain inorganic carbon, it is possible to determine the carbon content by elemental analysis. The test material shall have sufficient organic carbon to yield methane and carbon dioxide in amounts suitable for the determination. Normally, a minimum of 20 g of total dry solids containing 8 g of TOC is required per vessel.

If the loss in mass is to be determined, determine the total dry solids and volatile solids of the test material.

**NOTE** The loss in mass of the test material and reference material during the test can be determined, optionally, as additional information. In the example given in [Annex B](#), the volatile-solids content of the test material is determined at the beginning of the test and compared with that at the end of the test.

Use test material in the form of granules, powder, film, or simple shapes (e.g. dumb-bells). The maximum surface area of any individual piece of test material shall be about 2 cm × 2 cm. If any pieces in the original test material are large, reduce them in size.

## 8.3 Start-up of the test

Set up at least the following number of digestion vessels ([7.1](#)):

- a) three vessels for the test material;
- b) three vessels for the reference material;
- c) three vessels for blank controls.

Remove enough inoculum (approximately 10 kg) from the post-fermentation vessel and mix carefully and consistently by hand in order to obtain a homogeneous medium.

To every 1 000 g of wet mass (at least 20 % dry solids) of inoculum, add an amount of test material or reference material containing 15 g to 20 g of volatile solids for each test vessel. Use a minimum amount of 500 g of wet mass of inoculum per test vessel. Mix the test mixture manually in a small container for a period of 2 min to 3 min.

Treat the three blanks, containing inoculum only, in similar manner, by manually mixing the inoculum in a small container for a period of 2 min to 3 min with the same intensity as was done for the other vessels containing test material or reference material.

Place the mixtures in the digestion vessels and gently spread and compact the material evenly in the vessels to a uniform density. Put the vessels in a water bath or incubator and connect them to the gas-measurement or gas-collection device. The length of time between mixing the inoculum with the test or reference material and connection to the gas-measurement system should not be longer than 2 h. Record the temperature and atmospheric pressure prior to turning on the heating system of the incubator or water bath.

If loss in mass measurements are to be carried out, accurately weigh and record the mass of inoculum and test material placed in each individual digestion vessel.

## 8.4 Incubation period

Incubate the digestion vessels in the dark or in diffused light for a nominal period of 15 d at a constant temperature of  $52 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$ , which is representative of full-scale anaerobic digestion. The incubation

time can be extended until a constant plateau phase is reached, if significant biodegradation of the test material is still observable.

Measure the volume of biogas evolved at different time intervals to obtain a plot of evolved biogas volume as a function of time. More frequent measurements in the early stages of the experiment might be required.

## 8.5 Termination of the test

At the end of the digestion period, allow the digester vessels to cool to room temperature and determine the total volume of biogas evolved during the test. Record the room temperature and atmospheric pressure.

If the loss in mass of the test material is to be determined, weigh the digester vessels with their test mixtures. Take samples of the test mixtures from all vessels. Determine the total dry solids and the volatile solids (see [Annex B](#)).

Optionally, the methane and carbon dioxide (biogas) concentrations can be measured by using analytical apparatus suitable for the detection and quantification of these gases, such as a gas chromatograph with an appropriate detector.

It is recommended that further investigations be carried out with any test material remaining such as measuring relevant physical properties, chemical analysis and taking photographs.

## 9 Calculation and expression of results

### 9.1 Calculation of gaseous carbon

First, the amount of gaseous carbon  $C_g$  evolved from each digestion vessel is calculated. The volumes of methane and carbon dioxide evolved are converted to volumes at standard conditions of temperature (273 K) and pressure (1 013,25 hPa) (= STP) using the ideal-gas equation:

$$\frac{pV}{T} = \text{constant} \quad (1)$$

where

$p$  is the pressure in hPa;

$V$  is the volume in litres;

$T$  is the temperature in K.

These volumes are also corrected for water vapour pressure and atmospheric pressure variations during the test.

The corrected volume of biogas evolved is converted to the corresponding amount of gaseous carbon evolved using the standard equation: 22,4 ml of biogas at STP = 12 mg of  $C_g$ .

### 9.2 Calculation of the percentage biodegradation

Calculate the mean (of the three replicates) net amount, in grams, of gaseous carbon evolved by anaerobic biodegradation of the test material by subtracting the mean amount, in grams, of gaseous carbon evolved from the controls (three replicates) containing only inoculum.

## ISO 15985:2014(E)

Calculate the percentage biodegradation using the following equation:

$$\% \text{ biodegradation} = \frac{m_{C,g}(\text{test}) - m_{C,g}(\text{blank})}{m_{C,i}} \times 100 \quad (2)$$

where

$m_{C,g}$  is the amount of gaseous carbon evolved, in grams;

$m_{C,i}$  is the amount of carbon initially in the test material, in grams.

Calculate the standard error  $\sigma_M$  of the percentage biodegradation as follows:

$$\sigma_M = \sqrt{\left[ \frac{\sigma^2(\text{test})}{n_1} + \frac{\sigma^2(\text{blank})}{n_2} \right]} \times \frac{100}{m_{C,i}} \quad (3)$$

where

$n_1$  and  $n_2$  are the number of replicate test and blank digesters, respectively;

$\sigma$  is the standard deviation of the total amount of gaseous carbon produced.

Use the same equations to calculate the percentage biodegradation of the reference material and its standard error.

### 9.3 Calculation of loss in mass

An example of the optional calculation of loss in mass based on volatile-solids content is given in [Annex B](#).

### 9.4 Expression of results

Compile tables containing the measured and calculated data on the test material, the reference material, and the blank controls.

Plot the cumulative amount of biogas evolved from each digestion vessel (blank, test material and reference material) as a function of time. Plot a biodegradation curve (percentage biodegradation as a function of time) for the test material and the reference material. Use mean values if the differences between the individual values are less than 20 %. If this is not the case, plot biodegradation curves for each digester vessel.

Read from the plateau phase of the biodegradation curve the mean degree of biodegradation and report it as the final test result.

## 10 Validity of results

The test is considered as valid if

- the percentage biodegradation of the reference material is more than 70 % after 15 d, and
- the difference between the percentage biodegradation of the reference material in the different vessels is less than 20 % of the mean value.

## 11 Test report


The test report shall provide all pertinent information, particularly the following:

- a reference to this International Standard;

- b) all information necessary to identify and describe the test material, such as dry- or volatile-solids content, organic-carbon content, shape and visual appearance;
- c) all information necessary to identify and describe the reference material and its organic-carbon content;
- d) the volume of the digester vessels, the amounts of inoculum, test material and reference material used, and the main characteristics of the equipment used to determine the volume of biogas produced;
- e) information on the inoculum, such as source, age, date of collection, storage, handling, stabilization, total dry solids, volatile solids, pH of suspension, total nitrogen content, and volatile fatty acids, as appropriate;
- f) the results obtained for the biogas evolution and percentage biodegradation for each digester vessel and the averages, in tabular form and graphically, as well as the final percentage biodegradation for the test material and the reference material and the activity of the inoculum;
- g) the results of visual observations on the test material and inoculum during and at the end of the test, such as physical measurements and/or photographs;
- h) the mass of each digester vessel at the start and the end of the test and details of any loss in mass measurements, if performed;
- i) the reasons for rejection of any test results.

**Annex A**  
(informative)

**Principle of test system**

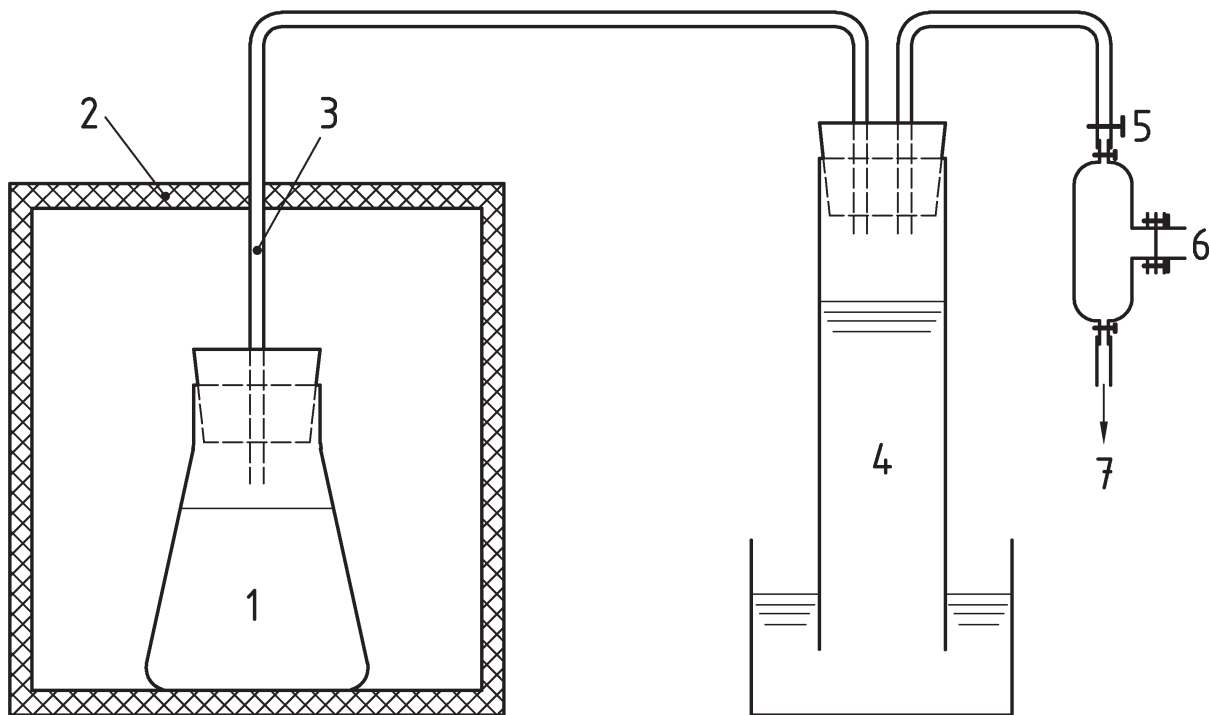

**Key**

- 1 digester
- 2 incubator
- 3 gas outlet
- 4 gas collector
- 5 valve
- 6 gas sampling
- 7 gas discharge

**Figure A.1 — Apparatus for high-solids anaerobic-digestion test**

## Annex B (informative)

### Example of loss in mass determination

Determine and calculate the percentage of mass loss of the test material based on volatile-solids content using the following procedure. Use the same procedure for the reference material.

$$\text{Mass loss from replicate } i \text{ (\%)} = \frac{b_i}{a_i} \times 100 \quad (\text{B.1})$$

where

$a_i$  is the mass of the volatile solids in the test material in replicate  $i$  at the start (g/vessel);

$b_i$  is the loss in mass of volatile solids from the test material in replicate  $i$  (g/vessel).

Thus, the mass loss from replicate  $b_i$  (%) is given by

$$\frac{[(w_{t1,i} \times d_{t1,i} \times v_{t1,i}) - (w_{t2,i} \times d_{t2,i} \times v_{t2,i})] - [(w_{b1} \times d_{b1} \times v_{b1}) - (w_{b2} \times d_{b2} \times v_{b2})]}{[(w_{t1,i} \times d_{t1,i} \times v_{t1,i}) - (w_{b1} \times d_{b1} \times v_{b1})]} \times 100 \quad (\text{B.2})$$

where

$w_{t1,i}$  is the wet mass in test vessel  $i$  at the start (g/vessel);

$w_{t2,i}$  is the wet mass in test vessel  $i$  at the end (g/vessel);

$w_{b1}$  is the average wet mass in the blank vessels at the start (g/vessel);

$w_{b2}$  is the average wet mass in the blank vessels at the end (g/vessel);

$d_{t1,i}$  is the dry solids in test vessel  $i$  at the start (% relative to the wet mass);

$d_{t2,i}$  is the dry solids in test vessel  $i$  at the end (% relative to the wet mass);

$d_{b1}$  is the average dry solids in the blank vessels at the start (% relative to the wet mass);

$d_{b2}$  is the average dry solids in the blank vessels at the end (% relative to the wet mass);

$v_{t1,i}$  is the volatile solids in test vessel  $i$  at the start (% relative to the dry solids);

$v_{t2,i}$  is the volatile solids in test vessel  $i$  at the end (% relative to the dry solids);

$v_{b1}$  is the average volatile solids in the blank vessels at the start (% relative to the dry solids);

$v_{b2}$  is the average volatile solids in the blank vessels at the end (% relative to the dry solids).

## Bibliography

- [1] ISO 625, *Solid mineral fuels — Determination of carbon and hydrogen — Liebig method*
- [2] ISO 11734, *Water quality — Evaluation of the “ultimate” anaerobic biodegradability of organic compounds in digested sludge — Method by measurement of the biogas production*
- [3] ISO 14855-1, *Determination of the ultimate aerobic biodegradability of plastic materials under controlled composting conditions — Method by analysis of evolved carbon dioxide — Part 1: General method*
- [4] ISO 14855-2, *Determination of the ultimate aerobic biodegradability of plastic materials under controlled composting conditions — Method by analysis of evolved carbon dioxide — Part 2: Gravimetric measurement of carbon dioxide evolved in a laboratory-scale test*



.....

