

---

---

**Elastomeric seismic-protection  
isolators —**

**Part 4:  
Guidance on the application of  
ISO 22762-3**

*Appareils d'appuis structuraux en élastomère pour protection  
sismique —*

*Partie 4: Lignes directrices pour l'application de l'ISO 22762-3*





**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Guidance on the use of Clause 4 of ISO 22762-3</b> .....	<b>1</b>
<b>5 Guidance on the use of Clause 5 of ISO 22762-3</b> .....	<b>1</b>
<b>6 Guidance on the use of Clause 6 of ISO 22762-3</b> .....	<b>1</b>
6.1 General.....	1
6.2 Type tests and routine tests.....	1
6.3 Functional requirements.....	3
6.4 Design compressive force and design shear displacement.....	3
6.5 Performance requirements.....	4
<b>7 Guidance on the use of Clause 7 of ISO 22762-3</b> .....	<b>24</b>
7.1 General.....	24
7.2 Compressive stiffness.....	24
<b>8 Guidance on the use of Clause 8 of ISO 22762-3</b> .....	<b>31</b>
<b>9 Guidance on the use of Clause 9 of ISO 22762-3</b> .....	<b>31</b>
<b>10 Guidance on the use of Clause 10 of ISO 22762-3</b> .....	<b>31</b>
<b>11 Guidance on the use of Clause 11 of ISO 22762-3</b> .....	<b>31</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 4, *Products (other than hoses)*.

ISO 22762 consists of the following parts, under the general title *Elastomeric seismic-protection isolators*:

- *Part 1: Test methods*
- *Part 2: Applications for bridges — Specifications*
- *Part 3: Applications for buildings — Specifications*
- *Part 4: Guidance on the application of ISO 22762-3 [Technical Specification]*

# Elastomeric seismic-protection isolators —

## Part 4:

# Guidance on the application of ISO 22762-3

## 1 Scope

This Technical Specification provides guidance on the use of ISO 22762-3:2010. It includes example design calculations and provides data on the characteristics obtained from all types of elastomeric isolators.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 22762-1:2010, *Elastomeric seismic-protection isolators — Part 1: Test methods*

ISO 22762-3:2010, *Elastomeric seismic-protection isolators — Part 3: Applications for buildings — Specifications*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 22762-3:2010 apply.

## 4 Guidance on the use of Clause 4 of ISO 22762-3

No guidance is given.

## 5 Guidance on the use of Clause 5 of ISO 22762-3

No guidance is given.

## 6 Guidance on the use of Clause 6 of ISO 22762-3

### 6.1 General

Guidance is given for 6.2, 6.4, and 6.5.

### 6.2 Type tests and routine tests

An example of the scaled test pieces (scales A and B) for the type testing of the specific isolator size is given as follows.

Dimensions and properties of target isolator (isolator-X) are shown in [Table 1](#).

**Table 1 — Dimensions and properties of isolator-X**

Outer diameter, $d_o$ (mm)	1 000
Inner diameter, $d_i$ (mm)	25
Thickness of one rubber layer, $t_r$ (mm)	6,7
Thickness of reinforcing steel plate, $t_s$ (mm)	4,4
Number of rubber layer, $n$	30
First shape factor, $S_1$	36,4
Second shape factor, $S_2$	5,0
Shear stiffness, $K_h$ (N/mm $\times 10^3$ )	2,44
Equivalent damping ratio, $h_{eq}$	0,225
Compressive stiffness, $K_v$ (N/mm $\times 10^3$ )	5 450

In this case, requirement for scales A and B test piece are shown in Table 4 of ISO 22762-3:2010.

An example of dimensions and properties of scales A and B is shown in [Table 2](#).

**Table 2 — Examples of Scales A and B for Isolator-X**

Characteristics	Scale A	Scale B
Scale	0,25	0,6
Outer diameter, $d_o$ (mm)	250	600
Inner diameter, $d_i$ (mm)	0 (6,3)	15
Thickness of one rubber layer, $t_r$ (mm)	1,7	4,0
Thickness of reinforcing steel plate, $t_s$ (mm)	1,2	2,2
Number of rubber layer, $n$	30	30
First shape factor, $S_1$	36,4	36,4
Second shape factor, $S_2$	5,0	5,0
Shear stiffness, $K_h$ (N/mm $\times 10^3$ )	0,61	1,46
Equivalent damping ratio, $h_{eq}$	0,225	0,225
Compressive stiffness, $K_v$ (N/mm $\times 10^3$ )	1 360	3 270

For any dimension, variation of  $\pm 5\%$  from exact scale-downed dimensions can be allowed.

The scaling of reinforcing plate for scale A can be adjusted if the effect on characteristics of isolator is not significant. In the case of scale A in [Table 2](#), the thickness of the plate is computed as 1,1 mm and 1,2 mm is adopted for the test piece.

Number of the test pieces required is not specified in the text. The recommended number of the test pieces is shown in [Table 3](#) when each test piece is tested individually. In the case that double-shear testing arrangement is used for determining the shear properties, it is recommended that two tests are performed and the number of test pieces doubled.

**Table 3 — Recommended number of test pieces for each test item**

Properties		Number of test pieces
Compressive properties		2
Shear properties		2
Dependency of shear properties	Shear strain dep.	2
	Compressive stress dep.	2
	Others	1
Dependency of compressive properties		1
Ultimate properties		1
Durability		1

In the case shown in [Table 4](#), the available previous test results can be used for substitution of the test required for the newly designed isolator.

**Table 4 — An example of available previous type test results: Comparison of characteristics between newly designed and previously tested isolator**

Characteristics	Previously tested isolator	Newly designed isolator (-)	Newly designed isolator (+)	Remarks
Outer diameter, $d_o$ (mm)	1 100	1 000	1 200	within $\pm 10$ %
Inner diameter, $d_i$ (mm)	25	25	27	within $\pm 10$ %
Thickness of one rubber layer, $t_r$ (mm)	7,0	6,7	7,5	within $\pm 10$ %
Thickness of reinforcing plate, $t_s$ (mm)	4,4	4,4	4,8	within $\pm 10$ %
Number of rubber layer, $n$	30	30	30	same
First shape factor, $S_1$	38,4	36,4	42,0	within $\pm 10$ %
Second shape factor, $S_2$	5,2	5,0	5,3	within $\pm 10$ %
Maximum comp. stress for test, $\sigma_{max}$ (MPa)	30	25	30	Previous test more severe condition
Minimum comp. stress for test, $\sigma_{min}$ (MPa)	-0,5	5,0	0,5	Previous test more severe condition
Maximum shear strain for test, $\gamma_{max}$	3,5	3,0	3,2	Previous test more severe condition

### 6.3 Functional requirements

No guidance is given.

### 6.4 Design compressive force and design shear displacement

Design compressive force refers to the force under non-seismic conditions.

Any specification or guidance is not given regarding nominal stress,  $\sigma_{nom}$ . Recommended process to specify  $\sigma_{nom}$  is given as follows:

- $\sigma_{nom}$  is determined in the range less than 30 % of critical stress,  $\sigma_{cr}$ . Maximum  $\sigma_{nom}$  is less than or equal to 15 MPa.
- Adequacy of  $\sigma_{nom}$  is verified so that compressive stress dependency (change of shear property under  $0,5 \sigma_{nom}$  and  $2,0 \sigma_{nom}$ ) is acceptable. Maximum  $\sigma_{nom}$  is less than or equal to 15 MPa.

## 6.5 Performance requirements

Examples of tests for each requirement are introduced.

### 6.5.1 General

No guidance is given.

### 6.5.2 Compressive properties

Example for 6.5.2 of ISO 22762-3 on compressive properties is given.

#### 6.5.2.1 In case of HDR

##### a) Test piece and test conditions

Test piece is shown in [Table 5](#).

**Table 5 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Inner diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	700	15	36,4	5,0	12,0	1

Test conditions are given below:

- compressive stress amplitude: 12 MPa ± 30 %;
- number of cycles: 3 cycles;
- compressive stiffness,  $K_v$ , is computed from 3rd cycle.

##### b) Test result

The result for one type of HDR is plotted in [Figure 1](#) and [Table 6](#).

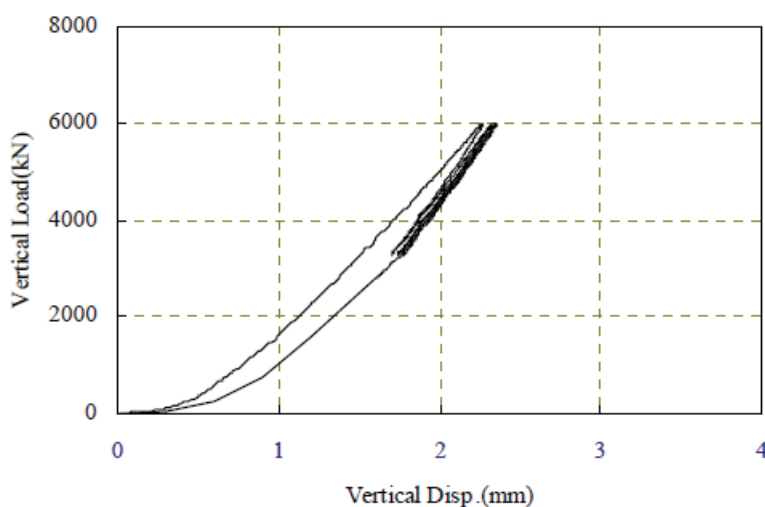

**Figure 1 — Compressive property test of HDR**



**Table 6 — Test results**

Characteristics	Test result
Compressive stiffness, $K_v$	4 592,0 kN/mm

### 6.5.3 Shear properties

Example for 6.2.2 of ISO 22762-3 on shear properties is given.

#### 6.5.3.1 In case of HDR

a) Test piece and test conditions

Test piece is shown in [Table 7](#).

**Table 7 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Inner diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	700	15	36,4	5,0	12,0	1

Test conditions are given below:

- compressive stress: 12 MPa;
- shear strain amplitude:  $\pm 100\%$  (141 mm);
- number of cycles: 3 cycles;
- shear stiffness,  $K_h$ , and damping ratio,  $h_{eq}$ , are computed from 3rd cycle.

b) Test results

The result for one type of HDR is shown in [Figure 2](#) and [Table 8](#).

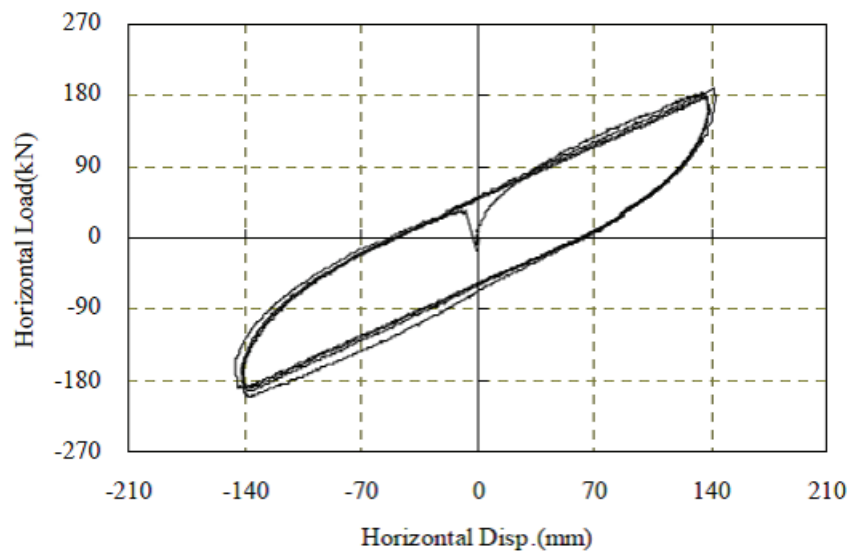**Figure 2 — Shear property test of HDR**

**Table 8 — Test piece**

Characteristics	Test result
Shear stiffness, $K_h$	4 592,0 kN/mm
Equivalent damping ration, $h_{eq}$	0,21

**6.5.4 Tensile properties**

Example for 6.5.4 of ISO 22762-3 on shear properties is given.

**6.5.4.1 In case of LNR**

a) Test piece and test conditions



Test pieces are shown in [Table 9](#).

**Table 9 — Test piece**

Type	Outer diameter (mm)	S <sub>1</sub>	S <sub>2</sub>
LNR	500	32,0	5,1
	800	31,7	5,1

b) Test results

Test results are shown in [Figures 3 a\) and b\)](#) and [Table 10](#).

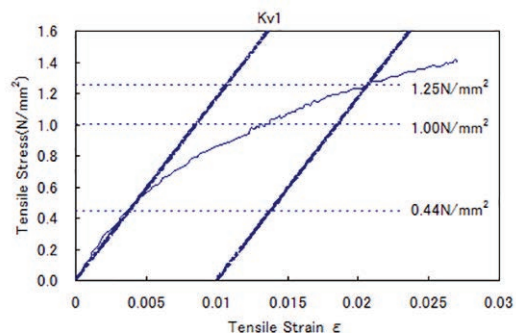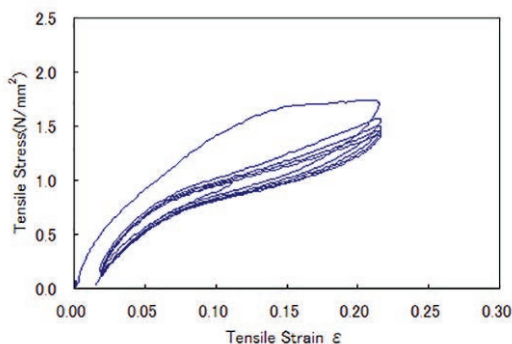

**a) relationship of tensile stress and tensile strain of LNR under shear-strain offset of 100%**

**b) measurement of tensile yield stress**

**Figure 3 — Tensile performance at  $\gamma = 100\%$**

**Table 10 — Test results**

Outer diameter (mm)	Tensile yield stress under shear strain of 100% (MPa)
500	1,25
800	1,19

**6.5.4.2 In case of HDR**

a) Test piece and test conditions


Test pieces are shown in [Table 11](#).

**Table 11 — Test piece**

Type	Outer diameter (mm)	S <sub>1</sub>	S <sub>2</sub>
HDR	800	36,1	4,0
	600	36,6	3,0

b) Test results

Test results are shown in [Figures 4 a\) and b\)](#) and [Table 12](#).

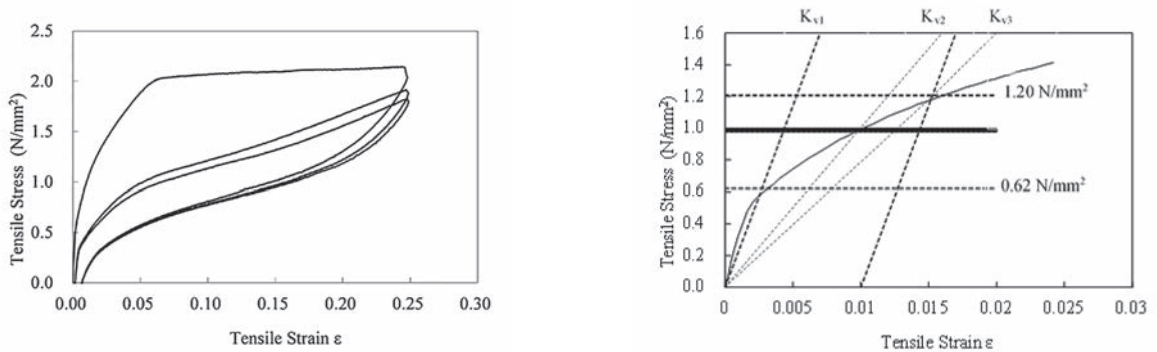

a) relationship of tensile stress and tensile strain of HDR under shear-strain offset of 100%

b) measurement of tensile yield stress

**Figure 4 — Tensile performance at  $\gamma = 100\%$**

**Table 12 — Test results**

Outer diameter (mm)	Tensile yield stress under shear strain of 100% (MPa)
800	1,2
600	1,4

**6.5.5 Dependencies of shear properties**

**6.5.5.1 Shear strain dependency**

Example for 6.5.5.1 of ISO 22762-3 on shear strain dependency is given.

**6.5.5.1.1 In case of HDR**

a) Test piece and test conditions

1) Scaled model

Test pieces of scaled model are shown in [Table 13](#).

Table 13 — Test isolators (scaled model)

Type	Outer dia. (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of isolators tested
HDR	225	35,2	3,3	9,3	1
	225	35,2	5,0	15,0	2
	225	35,2	8,3	15,0	1

Test conditions are given below:

- test vibration frequency: 0,33 Hz, sinusoidal wave;
- shear strain amplitude:  $\gamma = \pm 10\%$ ,  $\pm 20\%$ ,  $\pm 50\%$ ,  $\pm 100\%$ ,  $\pm 150\%$ ,  $\pm 200\%$ , and  $\pm 270\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle;
- test results were corrected to the corresponding value of the property at 20 °C by the specified method in ISO 22762-3, 6.5.3.3.3.

## 2) Full scale isolators

Test pieces of full scale isolators are shown in [Table 14](#).

Table 14 — Test isolators (full scale)

Type	Outer dia. (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of isolators tested
HDR	600	36,6	3,0	6,6	1
	800	36,1	4,0	12,1	1
	1 000	36,4	5,0	15,0	1
	1 200	35,8	6,0	15,0	1
	1 600	36,5	6,4	15,0	1

Test conditions are given below and in [Table 15](#).

- test wave: triangular wave;
- shear strain amplitude:  $\gamma = \pm 50\%$ ,  $\pm 100\%$ , and  $\pm 200\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle;
- test results were corrected to their counterpart with 0,33 Hz by the specified method in ISO 22762-3, 6.5.5.3;
- test results were corrected to the corresponding value of the property at 20 °C by the specified method in ISO 22762-3, 6.5.5.5.


**Table 15 — Test velocities**

Test velocity (mm/sec) [frequency (Hz)]		
±50 %	±100 %	±200 %
13,0 (0,033)	13,0 (0,017)	10,0 (0,006)

b) Test results

1) Scaled model

Figure 5 shows the test results by the scaled model specimens.

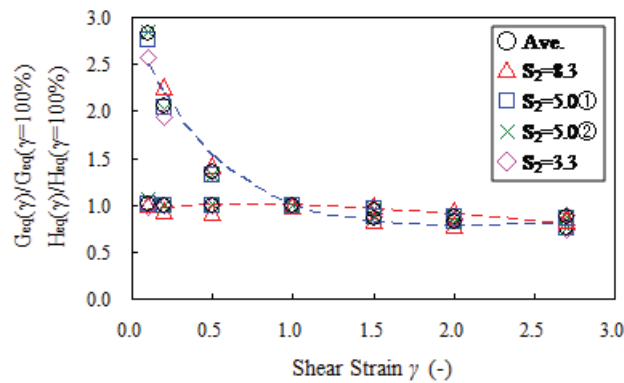

**Figure 5 — Shear strain dependency of shear properties of HDR (scaled isolator)**

The shear strain dependence of the shear properties (shear modulus, damping, and  $u$  function introduced in ISO 22762-1, Annex E) of HDR, as measured in dynamic loading tests are expressed by polynomial functions of shear strain, as shown in Table 16.

**Table 16 — An example of function for HDR**

Properties at $\gamma = 100\%$	Polynomial function
$G_{eq} = 0,62 \text{ (N/mm}^2\text{)}$ $H_{eq} = 0,240$ $u_0 = 0,408$	$G_{eq}(\gamma) = G_{eq} \times (2,855 - 3,878\gamma + 2,903\gamma^2 - 1,016\gamma^3 + 0,1364\gamma^4)$ $H_{eq}(\gamma) = H_{eq} \times (0,9150 + 0,2364\gamma - 0,1804\gamma^2 + 0,02902\gamma^3)$ $u_0(\gamma) = u_0 \times (0,9028 + 0,2711\gamma - 0,2083\gamma^2 + 0,03421\gamma^3)$

c) Full scale isolator

The test results for the full scale isolators are shown in Table 17.

**Table 17 — Test result: Horizontal characteristics normalized by value at 100 % strain**

Diameter (mm)	Items	Shear strain	
		±50 %	±200 %
600	$K_{eq}$	1,40	0,84
	$H_{eq}$	0,98	0,95
800	$K_{eq}$	1,27	0,91
	$H_{eq}$	0,96	0,95

Table 17 (continued)

Diameter (mm)	Items	Shear strain	
		±50 %	±200 %
1 000	$K_{eq}$	1,37	0,91
	$H_{eq}$	0,98	0,91
1 200	$K_{eq}$	1,38	0,89
	$H_{eq}$	0,95	0,95
1 600	$K_{eq}$	1,35	0,91
	$H_{eq}$	0,95	0,95

### 6.5.5.2 Compressive stress dependency

Example for 6.5.5.2 of ISO 22762-3 on compressive stress dependency is given.

#### 6.5.5.2.1 In case of HDR

##### a) Test piece and test conditions

Test pieces are shown in [Table 18](#).

Table 18 — Test piece


Type	Outer diameter (mm)	Inner diameter (mm)	$S_1$	$S_2$	Nominal compressive stress, $\sigma_s$ (N/mm <sup>2</sup> )	Total thickness of rubber (mm)
HDR	600 (15)	15	36,6	3,0	6,6	200
	800 (20)	20	36,1	4,0	12,1	200
	1 200 (55)	55	35,8	6,0	15,0	200

Test conditions are given below:

- shear strain amplitude:  $\gamma = 100$  (%);
- reference cycle: 3rd (cycle).

##### b) Test results

Test results are shown in [Table 19](#), [Figures 6 a\)](#) and [b\)](#).

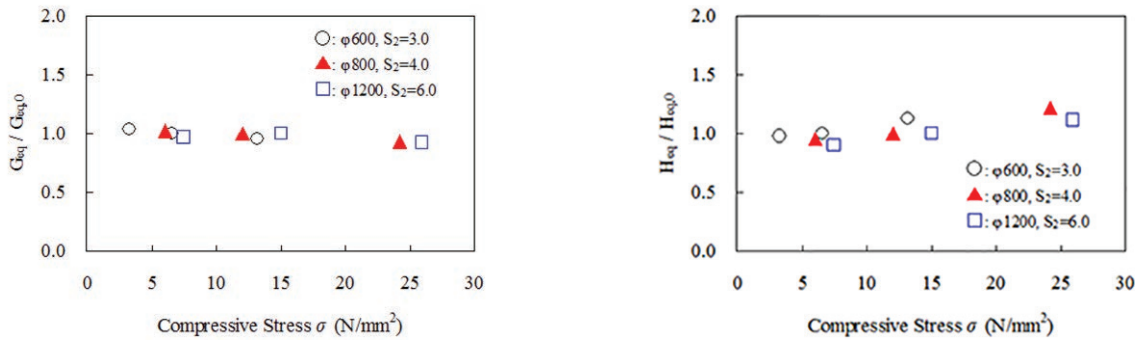

a) compressive stress dependency on shear modulus  $G_{eq}$

b) compressive stress dependency on equivalent damping ratio  $H_{eq}$

Figure 6 — Compressive stress dependency

Table 19 — Change in horizontal characteristics with respect to values at compressive stress,  $\sigma_s$

Outer diameter (mm)	Characteristics	Effect of compressive stress	
		$\sigma = 0,5\sigma_s$	$\sigma = 2\sigma_s$
600 (15)	$K_{eq}$	3,89 %	-4,39 %
	$H_{eq}$	-2,30 %	12,6 %
800 (20)	$K_{eq}$	2,13 %	-6,81 %
	$H_{eq}$	-4,76 %	21,5 %
1 200 (55)	$K_{eq}$	-3,06 %	-8,47 %
	$H_{eq}$	-10,5 %	11,6 %

### 6.5.5.3 Frequency dependency

Example for 6.5.5.3 of ISO 22762-3 on frequency dependency is given.

#### 6.5.5.3.1 In case of HDR

a) Test piece and test conditions

Test piece is shown in [Table 20](#). Shear block specimen can be used for the test.

Table 20 — Test isolators (scaled isolator)

Type	Outer diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	225	35,2	5,0	15,0	2


Test conditions are given below:

- test vibration frequency: 0,01 Hz, 0,03 Hz, 0,1 Hz and 0,33 Hz, sinusoidal wave;
- shear strain amplitude:  $\gamma = \pm 100 \%$ ;
- loading cycles: 3 cycles, respectively;

- reference cycle: 3rd cycle;
- test results were corrected to the corresponding value of the property at 23 °C by the specified method in ISO 22762-3, 6.5.5.5.

b) Test results

Test results are plotted in [Figure 7](#).

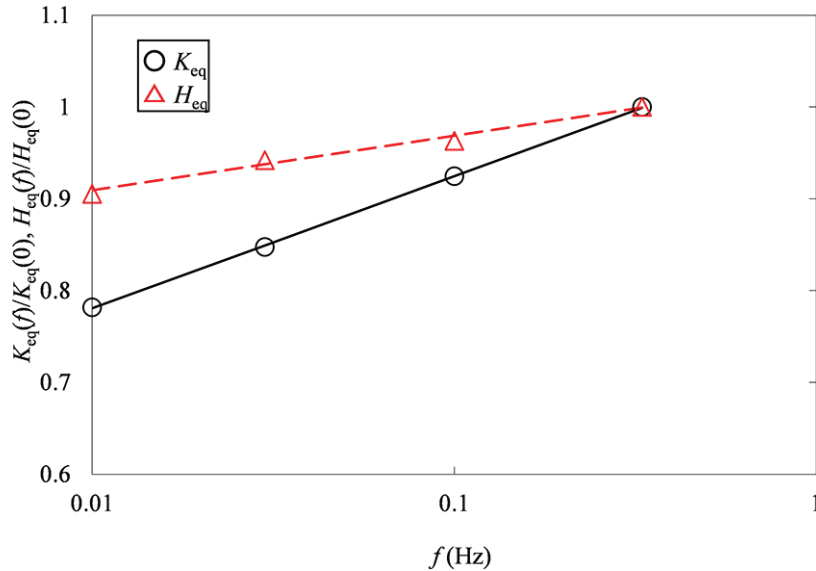

**Figure 7 — An example of frequency dependency test results of HDR**

The test result for each frequency is normalized by the result for the isolation frequency. By curve-fitting the results, correction factors that convert shear property values obtained at the testing frequency to values at the isolation frequency can be determined. Correction factors for loading frequency,  $f$ , can be derived as follows:

For shear stiffness:

$$\alpha_k = \frac{1}{a_k \log(f) + b_k} \tag{1}$$

For equivalent damping ratio:

$$\alpha_h = \frac{1}{a_h \log(f) + b_h} \tag{2}$$

where

$\alpha_k$  is the correction factor for shear stiffness,  $K_{eq}$ ;

$\alpha_h$  is the equivalent damping ratio,  $H_{eq}$ ;

$f$  is the loading frequency.

The values for  $a_k$ ,  $b_k$ ,  $a_h$ , and  $b_h$ , which are obtained from test results on a scaled model specimen are shown in [Table 21](#) for one type of HDR.



**Table 21 — An example of frequency correction factor**

Isolation frequency	$\alpha_k$	$b_k$	$\alpha_h$	$b_h$
0,33 Hz	0,144	1,07	0,059 4	1,010

The test results are corrected for frequency by multiplying the results of the shear property test by  $\alpha_k$  and  $\alpha_h$ .

For shear stiffness:

$$K_{eq}(0,33\text{Hz}) = K_{eq}(f:\text{test frequency}) \cdot \alpha_k \quad (3)$$

For equivalent damping ratio:

$$H_{eq}(0,33\text{ Hz}) = H_{eq}(f:\text{test frequency}) \cdot \alpha_h \quad (4)$$

### 6.5.5.3.2 In case of LRB

#### a) Test piece and test conditions

Test piece are shown in [Table 22](#). Shear block specimen is also available for this test.

**Table 22 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Lead plug diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
LRB	208	41,6	28,9	4,8	7,8	2

Test conditions are given below:

- test vibration frequency: 0,01 Hz, 0,03 Hz, 0,1 Hz, and 0,33 Hz, sinusoidal wave;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle;
- test results were corrected to the corresponding value of the property at 23 °C by the specified method in ISO 22762-3, 6.5.5.5.

#### b) Test results

The results for one type of LRB are plotted in [Figure 8](#).

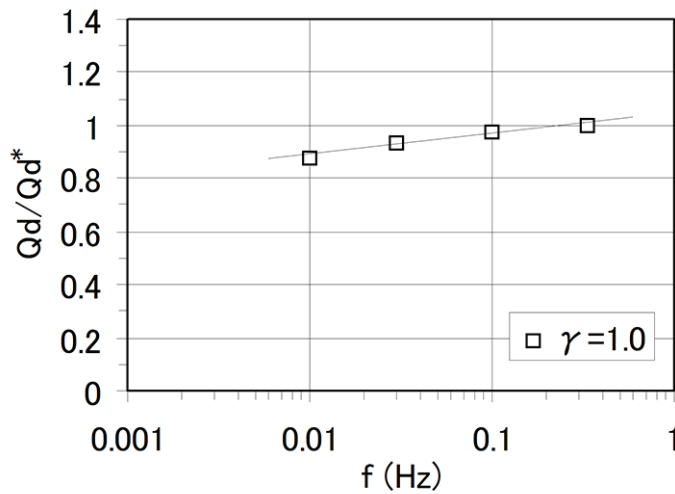

**Key**  
 Qd sine wave  
 Qd\* sine wave,  $f=0,33$  Hz

**Figure 8 — An example of frequency dependency test results of LRB**

The correction factor for frequency,  $f$ , can be derived using Formula (5).

For characteristic strength,  $Q_d$ :

$$\alpha_{Qd} = \frac{1}{a_Q \log_{10}(f) + b_Q} \tag{5}$$

where

$\alpha_{Qd}$  is the correction factor for characteristic strength,  $Q_d$ ;

$f$  is the loading frequency.

The values for  $a_Q$  and  $b_Q$ , which are obtained from test results on a scaled model specimen are shown in [Table 23](#) for one type of LRB.

**Table 23 — An example of frequency correction factor**

Isolation frequency	$a_{Qd}$	$b_{Qd}$
0,33 Hz	0,0829	1,049

The test results are corrected for frequency by multiplying the results of the shear property test by  $\alpha_{Qd}$ .

For characteristic strength,  $Q_d$ :

$$Q_d(0,33 \text{ Hz}) = Q_d(f:\text{test frequency}) \cdot \alpha_k \tag{6}$$

**6.5.5.3.3 In case of LNR**

a) Test piece and test conditions

Test piece is shown in [Table 24](#).

Shear block specimen can be used for the test.

**Table 24 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Inner diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
LNR	253	29	20,0	7,0	10,0	2

Test conditions are given below:

- test vibration frequency: 0,01 Hz, 0,25 Hz, 0,5 Hz, and 1,0 Hz, sinusoidal wave;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle;
- test results were corrected to the corresponding value of the property at 23 °C by the specified method in ISO 22762-3, 6.5.5.5.

#### b) Test results

The results for one type of LNR are plotted in [Figure 9](#).

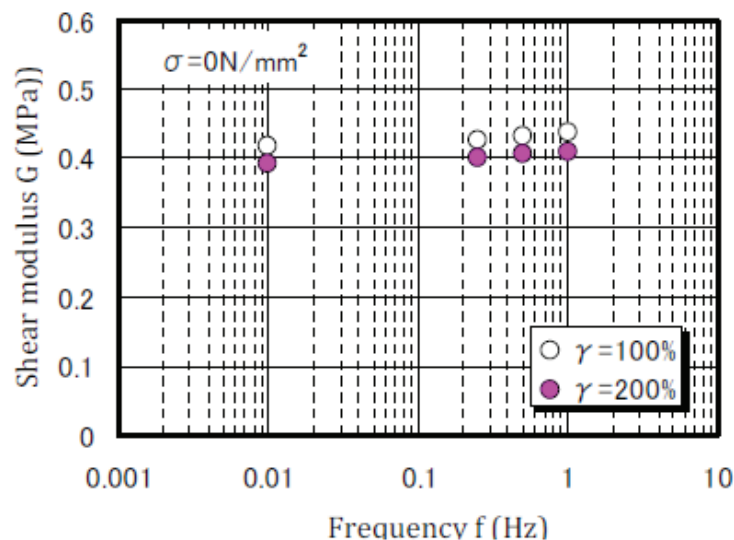

**Figure 9 — An example of frequency dependency test results of LNR**

Frequency dependency of LNR is negligible. Generally, no correction for frequency is required.

#### 6.5.5.4 Repeated loading dependency

Example for 6.5.5.4 of ISO 22762-3 on repeated loading dependency is given.

##### 6.5.5.4.1 In case of HDR

#### a) Test piece and test conditions

Test piece is shown in [Table 25](#).

**Table 25 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Inner diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	700	15	36,4	5,0	12,0	1

Test conditions are given below:


- test vibration frequency: 0,008 Hz, triangle wave;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 50 cycles;
- reference cycle: 3rd cycle;
- test results were corrected to the corresponding value of the property at 23 °C by a specified method.

**b) Test results**

The results are given in [Figure 10](#) and [Table 26](#).

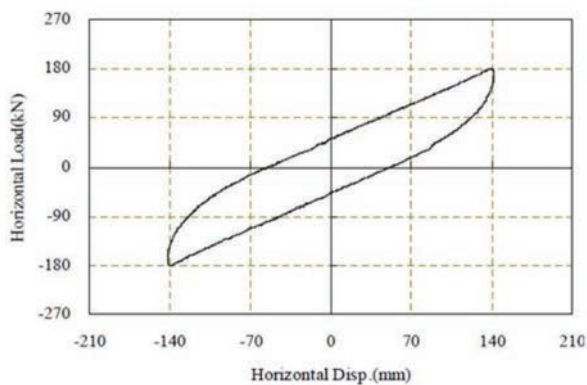

**a) Hysteresis loop (3<sup>rd</sup> cycle)**

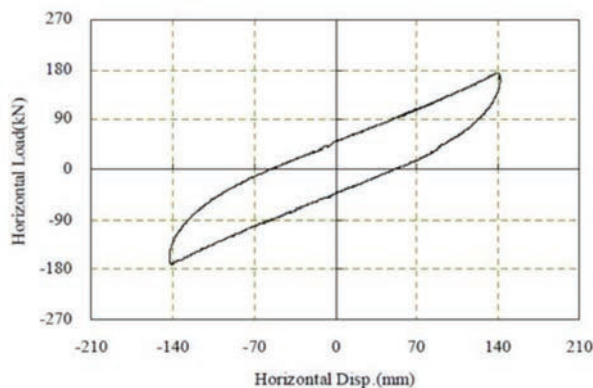

**b) Hysteresis loop (30<sup>th</sup> cycle)**

**Figure 10 — Repeated loading dependency of shear characteristics**

**Table 26 — Effect of repeated cycling [values normalized by corresponding value after third cycle (same correction as other part)]**

Number of cycles	$K_{eq}$	$H_{eq}$
3	1,000	1,000
5	0,99	0,99
10	0,98	0,97
30	0,95	0,95
50	0,94	0,92

**6.5.5.5 Temperature dependency**

Example for 6.5.5.5 of ISO 22762-3 on temperature dependency is given.

### 6.5.5.5.1 In case of HDR

#### a) Test piece and test conditions

Test piece is shown in [Table 27](#). Shear block specimen can be used for the test.

**Table 27 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	225	35,2	5,0	15,0	3

Test conditions are given below:

- test vibration frequency: 0,33 Hz, sinusoidal wave;
- test temperature: -10 °C, 0 °C, 23 °C, 30 °C, and 40 °C;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle.

#### b) Test results

The results for one type of HDR are plotted in [Figure 11](#).

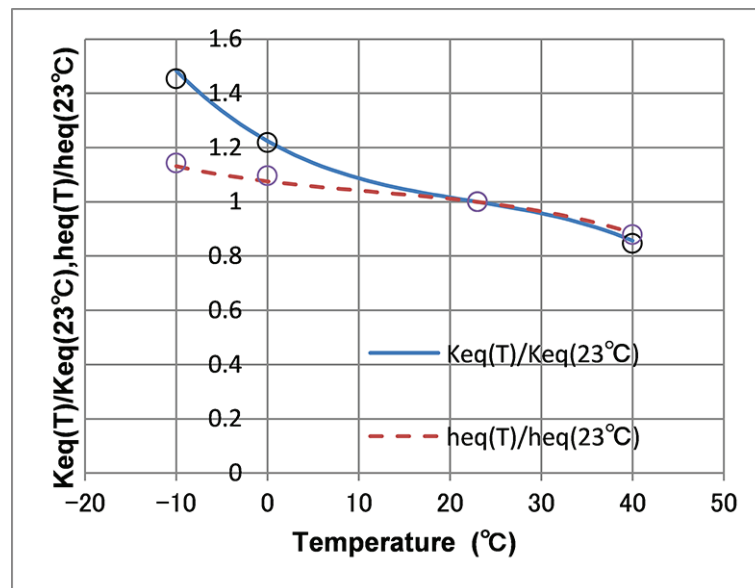

**Figure 11 — An example of temperature dependency test results of HDR**

The result at each temperature is normalized by the result for 23 °C.

Curve-fitting of the data gives a function expressing the dependence of the shear property on the temperature,  $T$  °C. Hence, a factor converting the value obtained at  $T$  °C to that, at 23 °C, can be derived as follows:

For shear modulus:

$$\beta_k = \frac{1}{a + bT + cT^2 + dT^3} \tag{7}$$

For equivalent damping ratio:

$$\beta_h = \frac{1}{e + fT + gT^2 + hT^3} \tag{8}$$

The values for *a*, *b*, *c*, *d*, *e*, *f*, *g*, and *h* for one type of HDR are shown in [Table 28](#).

**Table 28 — An example of temperature correction factor**

<i>a</i>	<i>B</i>	<i>c</i>	<i>d</i>
1,224	$-1,892 \times 10^{-2}$	$6,087 \times 10^{-4}$	$-9,135 \times 10^{-6}$
<i>e</i>	<i>F</i>	<i>g</i>	<i>h</i>
1,076	$-4,175 \times 10^{-3}$	$1,107 \times 10^{-4}$	$-3,133 \times 10^{-6}$

The test results can be corrected for temperature by multiplying the results of the shear property test by  $\beta_k$  and  $\beta_h$ .

For shear stiffness:

$$K_{eq}(23\text{ °C}) = K_{eq}(T:\text{test temperature}) \cdot \beta_k \tag{9}$$

For equivalent damping ratio:

$$H_{eq}(23\text{ °C}) = H_{eq}(T:\text{test temperature}) \cdot \beta_h \tag{10}$$

#### 6.5.5.5.2 In case of LRB

a) Test piece and test conditions

Test specimen is shown in [Table 29](#).

**Table 29 — Test isolators (scaled isolator)**


Type	Outer diameter (mm)	Lead plug diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
LRB	250	38	41,7	4,8	6,2	2

Test conditions are given below:

- test vibration frequency: 0,33 Hz, sinusoidal wave;
- test temperature: -10 °C, 0 °C, 23 °C, 30 °C, 40 °C;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle.

b) Test results

The results for one type of LRB are plotted in [Figure 12](#).

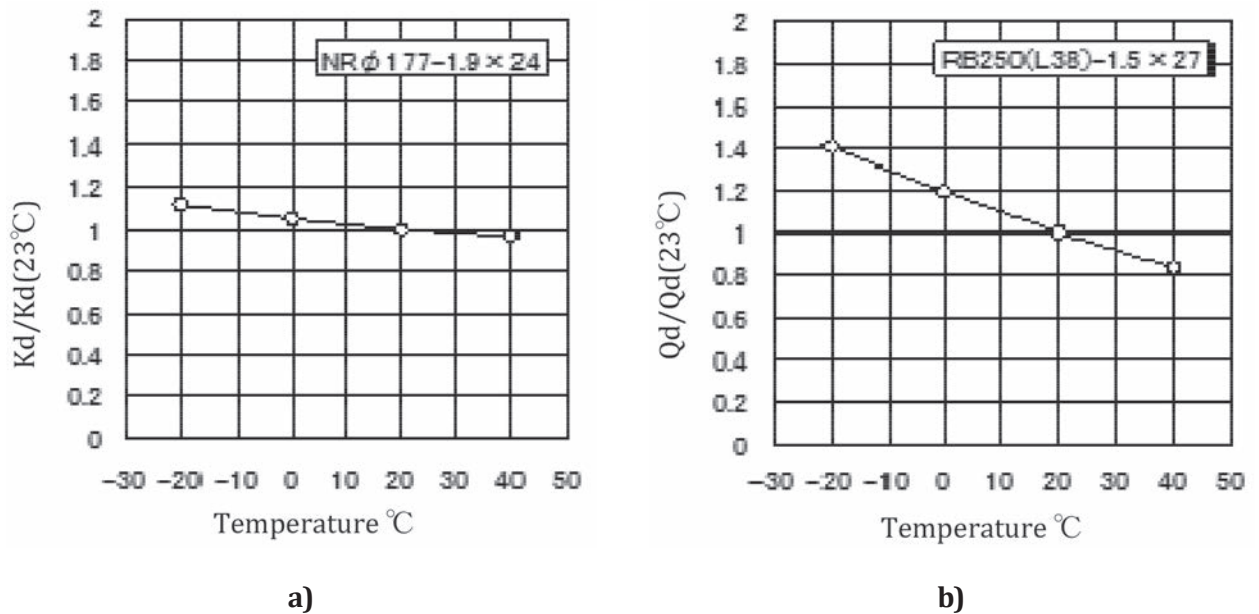

**Figure 12 — An example of temperature dependency test results of LRB**

The result at each temperature is normalized by the result for 23 °C.

Curve-fitting the data gives a function expressing the dependence of the shear property on the temperature,  $T$  °C. Hence, a factor converting the value obtained at  $T$  °C to that, at 23 °C, can be derived as follows:

For shear modulus of post-yielding stiffness:

$$\beta_{kd} = \frac{1}{a + bT + cT^2} \tag{11}$$

For characteristic strength:

$$\beta_{Qd} = \frac{1}{d + eT + fT^2} \tag{12}$$

The values for  $a, b, c, d, e, f, g,$  and  $h$  for one type of HDR are shown in [Table 30](#).

**Table 30 — An example of temperature correction factor**

$a$	$b$	$c$
1,052	$-2,955 \times 10^{-3}$	$1,895 \times 10^{-5}$
$d$	$e$	$f$
1,192	$-1,017 \times 10^{-2}$	$2,722 \times 10^{-5}$

The test results can be corrected for temperature by multiplying the results of the shear property test by  $\beta_k$  and  $\beta_h$ .

For post-yielding stiffness:

$$K_d(23\text{ °C}) = K_d(T:\text{test temperature}) \cdot \beta_{kd} \tag{13}$$

For characteristic strength:

$$Q_d(23\text{ °C}) = Q_d(T:\text{test temperature}) \cdot \beta_h \tag{14}$$

**6.5.5.5.3 In case of LNR**

a) Test piece and test conditions

Test piece is shown in [Table 31](#).

**Table 31 — Test piece**


Type	Outer diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of test isolator
HDR	225	35,2	5,0	15,0	1

Test conditions are given below:

- test vibration frequency: 0,33 Hz, sinusoidal wave;
- test temperature: -10 °C, 0 °C, 23 °C, 30 °C, 40 °C;
- shear strain amplitude:  $\gamma = \pm 100\%$ ;
- loading cycles: 3 cycles, respectively;
- reference cycle: 3rd cycle.

b) Test results

The results for one type of LNR are plotted in [Figure 13](#).

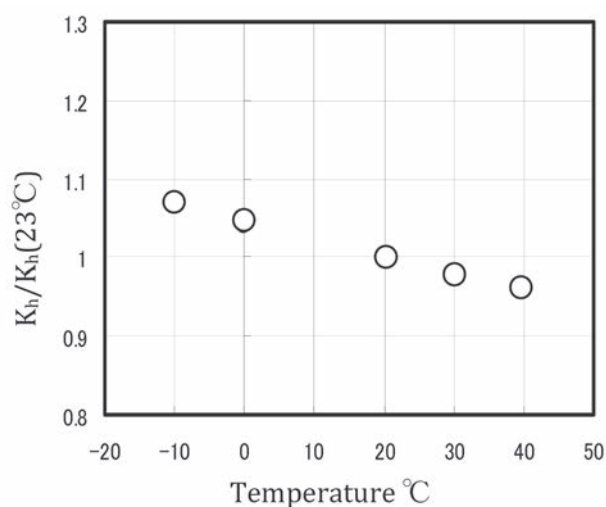

**Figure 13 — An example of temperature dependency test results of LNR**

The result at each temperature is normalized by the result for 23 °C.



Curve-fitting the data gives a function expressing the dependence of the shear property on the temperature,  $T$  °C. Hence, a factor converting the value obtained at  $T$  °C to that, at 23 °C, can be derived as follows:

For shear modulus of shear stiffness:

$$\beta_k = \frac{1}{a + bT + cT^2} \quad (15)$$

The values for  $a$ ,  $b$ , and  $c$  for one type of LNR are shown in [Table 32](#).

**Table 32 — An example of temperature correction factor**

$a$	$b$	$c$
1,052	$-2,955 \times 10^{-3}$	$1,895 \times 10^{-5}$

The test results can be corrected for temperature by multiplying the results of the shear property test by  $\beta_k$  and  $\beta_h$ .

For stiffness:

$$K_h(23 \text{ °C}) = K_h(T:\text{test temperature}) \cdot \beta_k \quad (16)$$

For characteristic strength:

$$Q_d(23 \text{ °C}) = Q_d(T:\text{test temperature}) \cdot \beta_h \quad (17)$$

### 6.5.6 Dependencies of compressive properties

No guidance is given.

### 6.5.7 Shear displacement capacity

Example for 6.5.7 of ISO 22762-3 on shear displacement capacity is given.

#### 6.5.7.1 In case of HDR

a) Test piece and test conditions

Test pieces for ramp loading test are shown in [Table 33](#).

**Table 33 — Test piece**

Type	Outer diameter (mm)	Inner diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Number of isolators
HDR	800	20	36,1	4,0	12,1	2

Test conditions are given below:

- test wave: triangular wave ( $V = 18$  mm/sec);
- loading cycles: 1 cycle, respectively.

b) Test results

The [Figure 14](#) and [Table 34](#) show the test results.

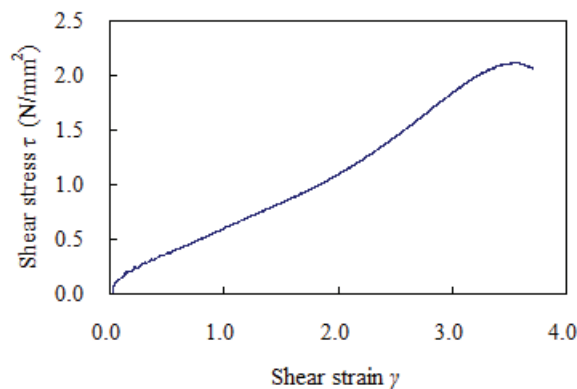


Figure 14 — Horizontal deformation capacity of HDR 800 mm diameter under ramp loading

Table 34 — Test results

Compressive stress (N/mm <sup>2</sup> )	Test shear strain (%)	Test results
12,1	357	No failure

6.5.8 Durability

Example for 6.5.8 of ISO 22762-3 on durability is given.

6.5.8.1 Change in properties on aging

a) Test piece and test conditions

Test piece is shown in [Table 35](#).

Table 35 — Test specimen

Type	Outer diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> ) <sup>1</sup>	Number of isolators	Remark
HDR	160	35	5,0	0,0	2	Initial
				0,0	1	30 years
				15,0	1	30 years
				0,0	1	60 years
				15,0	1	60 years

Accelerated aging condition for expected life under 23 °C is determined according to ISO 22762-1, Annex A as shown in [Table 36](#).

Table 36 — Accelerated ageing condition

Activation energy	Condition: 23 °C × 60 y Eq.
9,13 × 10 <sup>4</sup> J/mol	90 °C × 16 d

b) Test results


Test results for property changes in shear properties and ultimate properties are shown in [Tables 37](#) and [38](#). Ultimate property test results are plotted in [Figure 15](#).

**Table 37 — Test results: Shear property changes from initial value**

Outer diameter (mm)	First shape factor	Second shape factor	$G_{eq}$	$H_{eq}$
160	35	5,0	+9 %	-10 %
	35	5,0	+10 %	-5 %
	35	5,0	+7 %	-6 %

**Table 38 — Test results: Ultimate property changes**

Outer diameter (mm)	First shape factor	Second shape factor	Compressive stress (N/mm <sup>2</sup> )	Ultimate shear strain		
				Initial	30 years	60 years
160	35	5,0	15	4,51	-	-
				4,47	-	-
				-	4,43	-
				-	4,40	-
				-	4,54	-
				-	-	4,47
				-	-	4,32
				-	-	4,48
Average				4,49	4,46	4,42

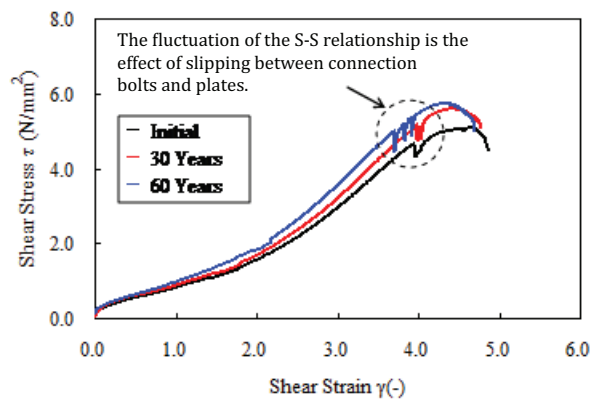

**Figure 15 — Change of ultimate shear strength with ageing**

### 6.5.8.2 Creep

a) Test piece and test conditions

Test piece is shown in [Table 39](#).

**Table 39 — Test isolators (scaled isolator)**

Type	Outer diameter (mm)	First shape factor	Second shape factor	Number of isolators
HDR	160	35,9	4,0	2


Test conditions are given below:

- compressive stress: 15,0 (MPa);
- testing time: 2 000 hr.

b) Test results

Test results are shown in [Figure 16](#) and [Table 40](#).

The creep at 2 000 h was extrapolated to 60 years to predict creep at 60 years ([Table 40](#)).

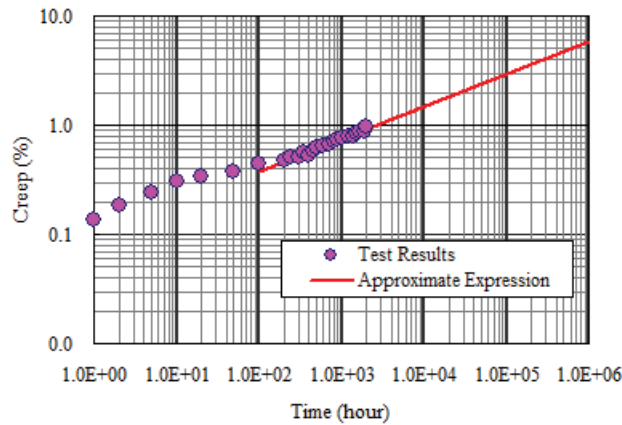

**Figure 16 — Creep properties**

**Table 40 — Test result**

Axial stress $\sigma$ (N/mm <sup>2</sup> )	Creep $\varepsilon$ (%)
15,0	within 9 %

## 7 Guidance on the use of Clause 7 of ISO 22762-3

### 7.1 General

Guidance is given for 7.3.1 of ISO 22762-3:2010.

### 7.2 Compressive stiffness

Two methods of evaluating compressive stiffness are given in Annex E of ISO 22762-3:2010. The values of  $E_{\infty}$  in Table E.1 of ISO 22762-3:2010, which are based on early test data obtained from compression of rubber discs, are lower than the results obtained directly from bulk compression tests (L.A. Wood et.al, 1964). A typical value of  $E_{\infty}$  is 2 000 MPa.

Examples for computation of isolator properties for each type (LNR, LRB, and HDR) are given below. The elastomer material constants used are only applicable to the compound chosen for the example calculation.

#### 7.2.1 In case of LNR

##### 7.2.1.1 Loading conditions and dimensional characteristics of isolators

- Compressive force:  $P = 7\,520$  (kN)

- Outer diameter:  $d_0 = 800,0$  (mm)
- Inner diameter:  $d_i = 40,0$  (mm)
- Unit rubber layer thickness:  $t_r = 6,0$  (mm)
- Number of layers:  $n = 26$
- Effective area:  $A = \frac{\pi}{4} \cdot (d_0^2 - d_i^2) = \frac{\pi}{4} \cdot (800^2 - 40^2) = 5\,014 \times 10^2$  (mm<sup>2</sup>)
- Compressive stress:  $\sigma = \frac{P}{A} = 7\,520 \times 10^3 / (5\,014 \times 10^2) = 15,0$  (N/mm<sup>2</sup>)  
 $\leq 15,0$  (N/mm<sup>2</sup>), nominal stress: OK
- First shape factor:  $S_1 = \frac{d_0 - d_i}{4 \cdot t_r} = (800 - 40) / (4 \cdot 6,0) = 31,7$
- Second shape factor:  $S_2 = \frac{d_0}{n \cdot t_r} = 800 / (26 \cdot 6,0) = 5,1$

### 7.2.1.2 Value of material constants used

- Young's modulus:  $E_0 = 3G = 1,323$  (N/mm<sup>2</sup>)
- Bulk modulus:  $E_\infty = 1\,961$  (N/mm<sup>2</sup>)
- Correction factor:  $\kappa = 0,85$
- Shear modulus at design strain of  $\gamma_0$ :  $G = 0,441$  (N/mm<sup>2</sup>)

### 7.2.1.3 Computation of design value

#### 7.2.1.3.1 Compressive properties

Computation according to E.3.2, Formula (1):

$$E_{ap} = E_0(1 + 2\kappa S_1^2) = 1,323 \cdot (1 + 2 \cdot 0,85 \cdot 31,7^2) = 2\,261 \text{ (N/mm}^2\text{)}$$

$$E_c = \left[ \frac{1}{E_{ap}} + \frac{1}{E_\infty} \right]^{-1} = (1/1961 + 1/2\,261)^{-1} = 1\,050 \text{ (N/mm}^2\text{)}$$

Compressive stiffness,  $K_v$ , is calculated as follows:

$$K_v = \frac{A \cdot E_c}{n \cdot t_r} = (5\,014 \times 10^2) \cdot 1\,050 / (26 \cdot 6,0) = 35\,100 \text{ kN/mm} \quad (18)$$

Computation according to E.3.2, Formula (2):

$$E_{ap} = 3G_{eq}(\gamma) \times (1 + 2S_1^2) \quad (19)$$

where  $G_{eq}(\gamma)$  is the shear modulus at the average shear strain,  $\gamma$ , produced by the compressive load.

For LNR,  $G_{eq}$  is not dependent on the shear strain,  $\gamma$ . Thus

$$E_{ap} = 3 \cdot 0,441 (1 + 2 \cdot 31,7^2) = 2\,660 \text{ N/mm}^2$$

The absence of the correction factor,  $\kappa$ , results in a slightly higher value of  $E_{ap}$  compared with method E3.1.

The values of  $E_c$  and  $K_v$  are calculated using the same formulae as for E.3.1. The values obtained are:

$$E_c = \left[ \frac{1}{E_{ap}} + \frac{1}{E_{\infty}} \right]^{-1} = (1/1\,961 + 1/2\,660)^{-1} = 1\,130 \text{ N/mm}^2$$

$$K_v = \frac{A \cdot E_c}{n \cdot t_r} = (5\,014 \times 10^2) \cdot 1\,130 / (26 \cdot 6,0) = 3\,630 \text{ N/mm}^2$$

**7.2.1.3.2 Shear properties**

Shear stiffness,  $K_h$ , is calculated as follows:

$$K_h = G \frac{A}{n \cdot t_r} = 0,441 \cdot 0,14 \times 10^2 / (26 \cdot 6,0) = 1,42 \times 10^3 \text{ (kN/m)}$$

**7.2.1.4 Examples of design results**

Examples of isolator design by specified design rules are given in [Table 41](#).

**Table 41 — Example for isolator design of LNR**

Shear modulus, $G$ (N/mm <sup>2</sup> )	0,441		
Outer diameter, $d_0$ (mm)	800	1 000	1 200
Inner diameter, $d_i$ (mm)	40	50	60
Unit rubber layer thickness, $t_r$ (mm)	6,0	7,5	9,0
Number of rubber layers, $n$	26	26	26
First shape factor, $S_1$	31,7	31,7	31,7
Second shape factor, $S_2$	5,1	5,1	5,1
Compressive stress, $\sigma$ (N/mm <sup>2</sup> )	15,0	15,0	15,0
Shear stiffness, $K_h$ ( $\times 10^3$ kN/m)	1,42	1,77	2,13
Compressive stiffness, $K_v$ ( $\times 10^3$ kN/m)	3 510	5 450	7 880

**7.2.2 In case of HDR**

**7.2.2.1 Loading conditions and dimensional characteristics of isolators**

- Compressive force:  $P = 1\,020\,0$  (kN)
- Outer diameter:  $d_0 = 1\,000,0$  (mm)
- Inner diameter:  $d_i = 25,0$  (mm)
- Unit rubber layer thickness:  $t_r = 6,7$  (mm)
- Number of rubber layers:  $n = 30$
- Effective area:  $A = \frac{\pi}{4} \cdot (d_0^2 - d_i^2) = \frac{\pi}{4} \cdot (1\,000^2 - 25^2) = 7\,085 \times 10^2$  (mm<sup>2</sup>)
- Compressive stress:  $\sigma = \frac{P}{A} = 10\,200 \times 10^3 / (7\,085 \times 10^2) = 13,0$  (MPa)  
 $< 15,0$  (MPa), nominal stress: OK
- First shape factor:  $S_1 = \frac{d_0 - d_i}{4 \cdot t_r} = 1\,000 / (30 \cdot 6,7) = 4,98$

- Second shape factor:  $S_2 = \frac{d_0}{n \cdot t_r} = 1\,000 / (30 \cdot 6,7) = 4,98$

### 7.2.2.2 Value of material constants used

- Young's modulus:  $E_0 = 7,6$  (MPa)
- Bulk modulus:  $E_\infty = 1\,500$  (MPa)
- Correction factor:  $\kappa = 1,0$

$E_0 = 7,6$  (MPa) is derived from experimental approach introduced in ISO 22762-3:2010, Annex E, E.4.  
 $K$  is supposed as 1,0.

- Equivalent shear modulus at strain,  $\gamma$

$$G_{\text{eq}} = a_0 + a_1 \cdot \gamma + a_2 \cdot \gamma^2 + a_3 \cdot \gamma^3 + a_4 \cdot \gamma^4 + a_5 \cdot \gamma^5 + \dots = \sum_{j=0}^n a_j \cdot \gamma^j \quad (20)$$

- Equivalent damping ratio at strain

$$h_{\text{eq}} = \sum_{j=0}^n b_j \cdot \gamma^j \quad (21)$$

Coefficients in polynomial Formulae (7.1) and (7.2) for calculation of  $G_{\text{eq}}$  and  $h_{\text{eq}}$  are shown for the example compound in [Table 42](#).

**Table 42 — Coefficients of polynomial formulae for  $G_{\text{eq}}$  and  $h_{\text{eq}}$**

	$a_0, b_0$	$a_1, b_1$	$a_2, b_2$	$a_3, b_3$	$a_4, b_4$
$G_{\text{eq}}$	2,855	-3,878	2,903	-1,016	0,136 4
$h_{\text{eq}}$	0,915 0	0,236 4	-0,180 4	0,0290 2	0,0

### 7.2.2.3 Computation of design value

#### 7.2.2.3.1 Compressive properties

- 1) Computation according to E.3.1, Formula (1):

$$E_{\text{ap}} = E_0 (1 + 2\kappa S_1^2) = 7,6 \cdot (1 + 2 \cdot 1,0 \cdot 36,4^2) = 20\,147,0 \text{ (MPa)}$$

$$E_c = \left[ \frac{1}{E_{\text{ap}}} + \frac{1}{E_\infty} \right]^{-1} = (1/1500 + 1/20\,147,0)^{-1} = 1\,396,1 \text{ (MPa)}$$

Compressive stiffness,  $K_v$ , is calculated as follows:

$$K_v = \frac{A \cdot E_c}{n \cdot t_r} = (7085 \times 10^2) \cdot 1\,396,1 / (30 \cdot 6,7) = 5\,450,0 \times 10^3 \text{ (kN/m)} \quad (22)$$

- 2) Computation according to E.3.1, Formula (2):

For HDR, the value of  $G_{eq}$  is dependent on the shear strain,  $\gamma$ . For a compressed rubber layer, the average shear strain in the rubber can be estimated from the expression:

$$\gamma = \sqrt{6S_1 \cdot \varepsilon} \quad (23)$$

where  $\varepsilon$ , the compressive strain in the rubber layer is given by:

$$\varepsilon = \sigma / E_{ap} \quad (24)$$

Because calculation of  $\tilde{\alpha}$  requires knowledge of  $E_{ap}$ , it is necessary to use an iterative procedure to obtain a value of  $G_{eq}$  consistent with the compressive strain imposed by  $\sigma$ . It should be noted that only the compression associated with  $E_{ap}$  produces a shear strain within the rubber layer.

Assuming an average shear strain of 0,1, gives a value of  $G_{eq} = 2,50$  MPa according to the coefficients in [Table 8](#). Thus

$$E_{ap} = 3 \cdot 2,5 (1 + 2 \cdot 36,4^2) = 19\,900 \text{ (MPa)}$$

With this value of  $E_{ap}$  and  $\sigma = 13$  (MPa),  $\varepsilon = 0,000\,65$  and  $\gamma = 0,058$ . Thus, assumed average shear strain is too high.

Assuming an average shear strain of 0.04, gives a value of  $G_{eq} = 2,70$  (MPa) according to the coefficients in [Table 8](#). Thus

$$E_{ap} = 3 \cdot 2,7 (1 + 2 \cdot 36,4^2) = 21\,500 \text{ N/mm}^2$$

With this value of  $E_{ap}$  and  $\sigma = 13$  MPa,  $\varepsilon = 0,000\,60$  and  $\gamma = 0,054$ . Thus assumed average shear strain is slightly too low.

Assuming an average shear strain of 0,05, gives a value of  $G_{eq} = 2,67$  (MPa) according to the coefficients in [Table 8](#). Thus

$$E_{ap} = 3 \cdot 2,67(1 + 2 \cdot 36,4^2) = 21\,300 \text{ (MPa)}$$

With this value of  $E_{ap}$  and  $\sigma = 13$  (MPa),  $\varepsilon = 0,000\,61$  and  $\gamma = 0,054$ . The assumed and calculated average shear strains are sufficiently close.

This value of  $E_{ap}$  can be used to determine  $E_c$ , and hence,  $K_v$ .

### 7.2.2.3.2 Shear properties

At nominal stress,  $\gamma_{nom} = 100$  (%)

Shear stiffness,  $K_h$ , and equivalent damping ratio,  $h_{eq}$ , for a shear strain of 1,0 are calculated by Formulae (7.1) and (7.2) as follows:

$$G_{eq} = G_{eq}(1,0) = 0,620 \text{ (MPa)}$$

$$K_h = G_{eq} \frac{A}{n \cdot t_r} = 0,620 \cdot 7\,085 \cdot 10^2 / (30 \cdot 6,7) = 2,42 \times 10^3 \text{ (kN/m)}$$

$$h_{eq} = h_{eq}(1,0) = 0,240$$

### 7.2.2.4 Examples of design results

Examples of isolator design by specified design rules are given in [Table 43](#).



Table 43 — Examples for isolator design of HDR

Equivalent shear modulus, $G_{eq}$ (N/mm <sup>2</sup> )	0,620		
Outer diameter, $d_0$ (mm)	800	1 000	1 200
Inner diameter, $d_i$ (mm)	20	25	55
Unit rubber layer thickness, $t_r$ (mm)	5,4	6,7	8,0
Number of rubber layers, $n$	37	30	25
First shape factor, $S_1$	36,1	36,4	35,8
Second shape factor, $S_2$	4,0	5,0	6,0
Compressive stress, $\sigma$ (N/mm <sup>2</sup> )	10,5	15,0	15,0
Shear stiffness, $K_h$ ( $\times 103$ kN/m)	1,56	2,42	3,50
Equivalent damping ratio, $h_{eq}$	0,24		
Compressive stiffness, $K_v$ ( $\times 103$ kN/m)	3 370	4 220	5 060

### 7.2.3 In case of LRB

#### 7.2.3.1 Loading conditions and dimensional characteristics of isolators

- Compressive force:  $P = 16\,000$  (kN)
- Outer diameter:  $d_0 = 1\,200,0$  (mm)
- Lead plug diameter:  $d_i = 240,0$  (mm)
- Unit rubber layer thickness:  $t_r = 7,0$  (mm)
- Number of rubber layers:  $n = 29$
- Effective area:  $A = \frac{\pi}{4} \cdot (d_0^2 - d_i^2) = \frac{\pi}{4} \cdot (1\,200^2 - 240^2) = 1\,086 \times 10^3$  (mm<sup>2</sup>)
- Lead plug area:  $A_p = \frac{\pi \cdot d_i^2}{4} = \frac{\pi \cdot 240^2}{4} = 45,24 \times 10^3$  (mm<sup>2</sup>)
- Compressive stress:  $\sigma = \frac{P}{A} = 16\,000 \times 10^3 / (1\,086 \times 10^3) = 14,7$  (MPa)  
 $\leq 15,0$ , nominal stress (MPa): OK
- First shape factor:  $S_1 = \frac{d_0}{4 \cdot t_r} = 1\,200 / (4 \cdot 7,0) = 42,86$
- Second shape factor:  $S_2 = \frac{d_0}{n \cdot t_r} = 1\,200 / (29 \cdot 7,0) = 5,9$

#### 7.2.3.2 Value of material constant used

- Young's modulus:  $E_0 = 1,44$  (MPa)
- Bulk modulus:  $E_\infty = 1\,960$  (MPa)
- Correction factor:  $\kappa = 0,85$
- Shear modulus at design shear strain,  $\gamma_0$ :  $G = 0,392$  (MPa)
- Yield stress of lead plug:  $\tau_p = 8,33$  (MPa)
- Apparent shear modulus of lead plug:  $\alpha = 0,588$  (MPa)

7.2.3.3 Computation of design value

7.2.3.3.1 Compressive properties [according to E.3.1, Formula (1)]

$$E_{ap} = E_0 (1 + 2\kappa S_1^2) = 1,44 \cdot (1 + 2 \cdot 0,85 \cdot 42,86^2) = 4\,498 \text{ (MPa)}$$

$$E_c = \left[ \frac{1}{E_{ap}} + \frac{1}{E_\infty} \right]^{-1} = (1/4\,498 + 1/1\,960)^{-1} = 1\,365 \text{ (MPa)}$$

Compressive stiffness,  $K_v$ , is calculated as follows:

$$K_v = \frac{A \cdot E_c}{n \cdot t_r} = (1\,086 \times 10^3) \cdot 1\,365 / (29 \cdot 7,0) = 7\,300 \times 10^3 \text{ (kN/m)}$$

7.2.3.3.2 Shear properties

Post-yield stiffness,  $K_d$ , and characteristic strength,  $Q_d$ , are calculated by Formulae (F.12) and (F.10) in Annex E of ISO 22762-3:2010 as follows:

$$K_r = G \frac{A}{n t_r} = 0,392 \cdot 1\,086 \times 10^3 / (29 \cdot 7,0) = 2,097 \times 10^3 \text{ (kN/m)}$$

$$K_p = \alpha \frac{A_p}{n t_r} = 0,588 \cdot 45,24 \times 10^3 / (29 \cdot 7,0) = 1,310 \times 10^3 \text{ (kN/m)}$$

$$K_d = C_r(\gamma) \cdot K_r + C_p(\gamma) \cdot K_p = 1,0 \cdot 2,097 \times 10^3 + 1,0 \cdot 1,310 \times 10^3 = 2,23 \times 10^3 \text{ (kN/m)}$$

where

$$\begin{cases} C_r(\gamma = 100\%) = 1,0 \\ C_p(\gamma = 100\%) = 1,0 \end{cases}$$

$$Q_d = \tau_p \cdot A_p = 8,33 \cdot 45,24 \times 10^3 = 377 \times 10^6 \text{ (N)} = 377 \times 10^3 \text{ (kN)}$$

7.2.3.4 Examples of design results

Examples of isolator design by specified design rules are given in [Table 44](#).

Table 44 — Examples for isolator design of LRB

Shear modulus, $G$ (N/mm <sup>2</sup> )	0,392		
Outer diameter, $d_0$ (mm)	800	1 000	1 200
Lead plug diameter, $d_i$ (mm)	160	200	240
Unit rubber layer thickness, $t_r$ (mm)	5,0	7,0	7,0
Number of rubber layers, $n$	40	29	29
First shape factor, $S_1$	40,0	35,7	42,9
Second shape factor, $S_2$	4,0	4,9	5,9
Compressive stress, $\sigma$ (N/mm <sup>2</sup> )	15,0	15,0	15,0
Post-yield stiffness, $K_d$ ( $\times 103$ kN/m)	1,00	1,55	2,23

**Table 44** (continued)

Characteristic strength, $Q_d$ (kN)	167	262	377
Compressive stiffness, $K_v$ ( $\times 10^3$ kN/m)	3 290	5 070	7 300

**8 Guidance on the use of Clause 8 of ISO 22762-3**

No guidance is given.

**9 Guidance on the use of Clause 9 of ISO 22762-3**

No guidance is given.

**10 Guidance on the use of Clause 10 of ISO 22762-3**

No guidance is given.

**11 Guidance on the use of Clause 11 of ISO 22762-3**

No guidance is given.

.....

---

---

**ICS 83.140.99;91.120.25**

Price based on 31 pages